



# LUND UNIVERSITY

## Statistics of InAs/InGaAsSb/GaSb TFETs with sub-50 mV/decade operation at VDS of 0.3V

Memisevic, Elvedin; Svensson, Johannes; Lind, Erik; Wernersson, Lars-Erik

2017

*Document Version:*  
Other version

[Link to publication](#)

*Citation for published version (APA):*

Memisevic, E., Svensson, J., Lind, E., & Wernersson, L.-E. (2017). *Statistics of InAs/InGaAsSb/GaSb TFETs with sub-50 mV/decade operation at VDS of 0.3V*. Paper presented at Compound Semiconductor Week 2017, Berlin, Berlin, Germany.

*Total number of authors:*  
4

### General rights

Unless other specific re-use rights are stated the following general rights apply:

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

Read more about Creative commons licenses: <https://creativecommons.org/licenses/>

### Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

LUND UNIVERSITY

PO Box 117  
221 00 Lund  
+46 46-222 00 00

# Statistics of InAs/InGaAsSb/GaSb TFETs with sub-50 mV/decade operation at $V_{DS}$ of 0.3V

E. Memisevic\*, J. Svensson, E. Lind, and L.-E. Wernersson

*Lund University, Box 118, 221 00 Lund, Sweden*

Tunnel Field-Effect Transistors (TFETs) have the potential to provide better subthreshold characteristics ( $SS < 60$  mV/dec), and to enable a reduction of the power supply voltage with maintained drive current as compared to MOSFETs.<sup>1</sup> One promising structure for TFETs is gate-all-round, axial InAs/InGaAsSb/GaSb nanowire heterostructures where the wrap gate provides excellent electrostatic control and the nanowire geometry allows for combination of materials with large lattice mismatch.<sup>2</sup>

In this work, InAs/InGaAsSb/GaSb nanowires were grown on Si (111)-substrates with a 200-nm-thick InAs n+-layer<sup>3</sup>, using the vapor-liquid-solid growth mechanism. Utilizing electron beam lithography and a PMMA based lift-off process Au-seed particles were positioned in arrays with 1 to 8 particles with diameter of 40 nm. The nanowires were grown in a metal-organic-vapor-phase-epitaxy (MOVPE) reactor by using the precursors trimethylindium, arsine, trimethylgallium and trimethylantimony for the growth of the three segments. The bottom half of the InAs segment was n-doped with tetraethyltin, and the InGaAsSb/GaSb section was p-doped with diethylzinc. After growth, the nanowires were digitally etched using repeated cycles of ozone oxidation and citric acid etching, reducing the InAs diameter to 20 nm. The InGaAsSb was etched at a lower rate and no visible etching of GaSb was observed. A gate dielectric was deposited using atomic layer deposition with 5/36 cycles of Al<sub>2</sub>O<sub>3</sub>/HfO<sub>2</sub> (EOT~1.4 nm). The bottom spacer was fabricated using thermal evaporation of SiO<sub>x</sub>. It was followed by gate-formation using sputtering of W, and the gate length was set by an etchback process. A top spacer was formed using a spin-on resist and etchback process. The high-k was removed from the top of the nanowires using diluted HF, followed by sputtering of a Ni/Au-bilayer and UV-lithography to define the probing-pads.

The best device exhibits excellent electrostatics with a low DIBL of 25 mV/V, and a subthreshold swing ( $S$ ) of 48 mV/dec for  $V_{DS}$  of 0.1-0.5V. Using  $I_{off} = 1$  nA/ $\mu$ m and  $V_{DS} = 0.3$ V, an  $I_{on}$  of 10.6  $\mu$ A/ $\mu$ m and a record high  $I_{60}$  of 0.31  $\mu$ A/ $\mu$ m are achieved demonstrating a TFET that operates at high currents and still below the thermal limit of 60 mV/dec.<sup>4</sup> Statistical data for the devices show a trend of increasing  $I_{60}$  current with decreasing  $S$ , due to an increasing voltage range in which the device operates in the sub-60 region. The on-current shows no dependence on the number of the nanowires in the arrays. The peak-to-valley current ratio increases with decreasing number of nanowires reaching 14.6 for the best device. The best  $S$  are achieved in a device with a single nanowire, although most devices still reach sub-60 mV/dec operation for the lower drive voltages. Since the performance at low supply voltages surpasses that of state-of-the-art Si MOSFETs the results are highly encouraging for future low-power electronic applications.<sup>4</sup>

## Acknowledgments

This work has been supported by Swedish Foundation for Strategic Research (SSF) and the European Union 7<sup>th</sup> Framework Program E2SWITCH (Grant Agreement No. 619509).

## References

- [1] A.M. Ionescu et al, *Nature*, Vol. 479, pp. 329-337, 2011
- [2] M. Borg et al, *Nano Lett.*, Vol. 10, pp. 4080-4085, 2010
- [3] S. Gorji Ghalamestani et al, *J. Cryst. Growth*, Vol. 332, pp. 12-16, 2011
- [4] E. Memisevic et al, IEDM, 2016

All currents are normalized to the circumference of the InAs and the number of the nanowires in the devices.

\*Corresp. author: Elvedin.memisevic@eit.lth.se

## Figures

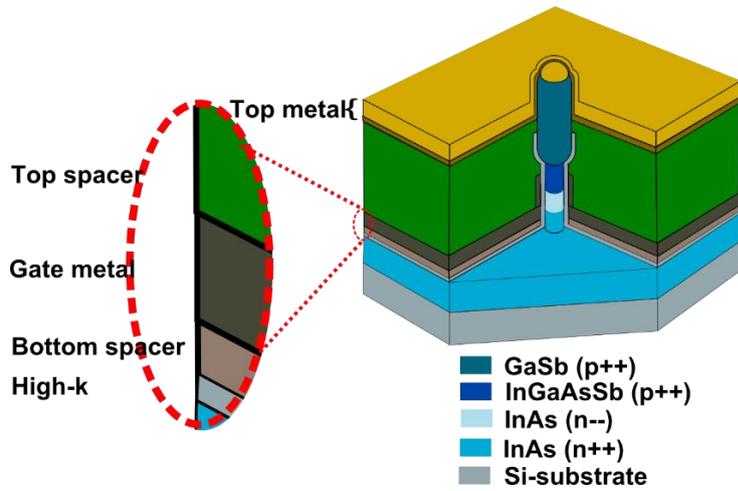


Fig. 1. Schematic image of the vertical InAs/InGaAsSb/GaSb TFET showing different sections of the nanowire and layers.

- - Definition of Au-seed particles using EBL
- - MOVPE growth of nanowires
- - Digital etching
- - Apply high-k ( $\text{Al}_2\text{O}_3/\text{HfO}_2$ ) using ALD
- - Evaporate  $\text{SiO}_x$  to form bottom spacer
- - Sputter on W
- - Define gate-length and gate-pad
- - Organic top spacer
- - Etch out gate-via and drain-via
- - Sputter on Ni and Au to form top-metal
- - Define gate, drain and source contact-pads with UV

Fig. 2. Process-flow for the device fabrication. EOT for the high-k is 1.4 nm.

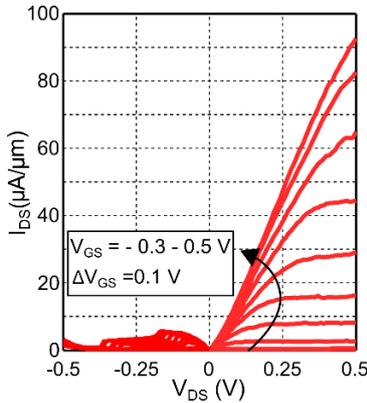


Fig. 3. Output data for the best device, reaching  $92 \mu\text{A}/\mu\text{m}$  at  $V_{\text{GS}} = V_{\text{DS}} = 0.5 \text{ V}$ . Peak to valley current ratio for the device is 14.5.

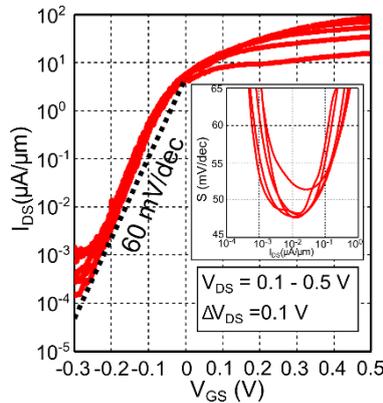


Fig. 4. Transfer data for the best device, showing small DIBL of 25 mV/V and reaching 48 mV/dec at voltages 0.1-0.5 V as shown in insert.

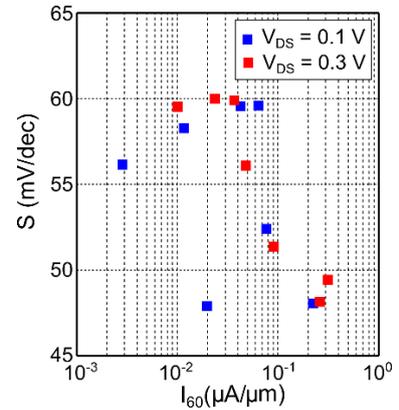


Fig. 5. Subthreshold swing vs  $I_{60}$ , for  $V_{\text{DS}}$  of 0.1 V and 0.3 V, for several devices with different number of nanowires.

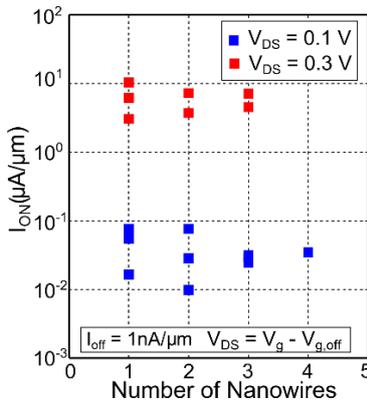


Fig. 6.  $I_{\text{on}}$  vs number of nanowires in each device.

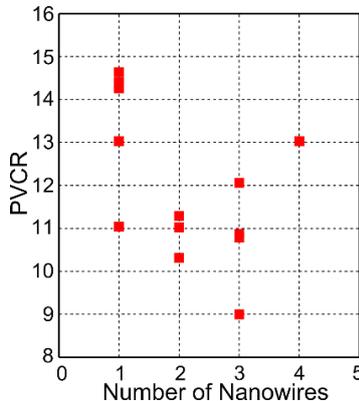


Fig. 7. Peak to valley current ratio vs number of nanowires in the device.

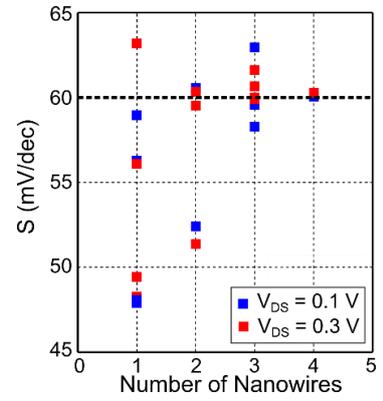


Fig. 8. Subthreshold swing vs number of nanowires in the devices.

\*All currents presented in this work are normalized using circumference of the InAs segment and number of nanowires.