



# LUND UNIVERSITY

## Moisture penetration in a chair seat as a response to daily RH variations in the indoor air

Svennberg, Kaisa; Wadsö, Lars; Hansen, Kurt Kielsgaard

*Published in:*  
[Host publication title missing]

2005

[Link to publication](#)

*Citation for published version (APA):*  
Svennberg, K., Wadsö, L., & Hansen, K. K. (2005). Moisture penetration in a chair seat as a response to daily RH variations in the indoor air. In *[Host publication title missing]*

*Total number of authors:*  
3

### General rights

Unless other specific re-use rights are stated the following general rights apply:  
Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

Read more about Creative commons licenses: <https://creativecommons.org/licenses/>

### Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

LUND UNIVERSITY

PO Box 117  
221 00 Lund  
+46 46-222 00 00



# Moisture penetration in a chair seat as a response to daily RH variations in the indoor air

Climatic chamber measurements and calculations

*Kaisa Svennberg, Lic. Eng., M. Sc.*

*Building Physics, Lund Institute of Technology, Lund University;*

[kaisa.svennberg@byggtek.lth.se](mailto:kaisa.svennberg@byggtek.lth.se)

*Johan Claesson, Prof., Ph.D.*

*Building Physics, Lund Institute of Technology, Lund University and*

*Building Physics, Chalmers University of Technology*

[claesson@bt.chalmers.se](mailto:claesson@bt.chalmers.se)

*Kurt Kielsgaard Hansen, Ass. Prof. Ph.D.,*

*Dept. of Civil Engineering, Technical University of Denmark*

[kkh@byg.dtu.dk](mailto:kkh@byg.dtu.dk)

**KEYWORDS:** *Moisture variations, indoor air, measurements, calculation model, upholstery, furniture, chair, felted wool*

## SUMMARY:

*In the indoor environment there are a number of materials with potential to act as moisture buffers including both building materials and furnishing materials. For daily moisture variations in the indoor air furniture with upholstery can play an important role as moisture buffers. Material properties and calculation models describing the response to moisture variations in the ambient climate for these material combinations are limited. In this project the moisture properties for a chair seat with a wool fabric and plastic foam padding were determined. The moisture penetration in the chair seat was measured using small temperature and relative humidity sensors. A numerical calculation model describing the step-response as well as the response to ramp variations is described. A comparison between measurements and theoretical calculations was performed. The difficulties with determination of material properties for highly permeable materials are also discussed as well as suitable methods and special considerations.*

## 1. Introduction

Materials found in the indoor environment form a heterogeneous group with both typical building materials and furnishing materials. Several of the materials exposed to the indoor air have the potential to act as moisture buffers.

There are different ways to categorize the materials in the indoor environment (Martin, 1986) suggested a division into slow and fast materials. (Plathner, 2002) described the furnishing materials as soft and hard. Textiles and upholstery are examples of soft furnishing materials and wooden furniture and hard flooring are examples of hard furnishing materials.

(Svennberg, 2003) suggested that the materials should be divided into different categories depending on their basic moisture properties in varying timescales. These materials may play an important role in buffering the daily moisture variation (Svennberg, 2004).

## 2. Materials

The measurements as well as the theoretical calculations were performed on a chair seat from an industrially manufactured office chair.

The chair seat consisted of a 5 mm plastic board, 31 mm polyether foam and a 2.5 mm felted wool fabric as a cover. The plastic board was covered underneath with a non-woven synthetic

fabric. The chair seat in cross section with the placing of the RH-and temperature sensors is shown in Fig. 1 and the thickness and density of the materials used are given in Table 1.

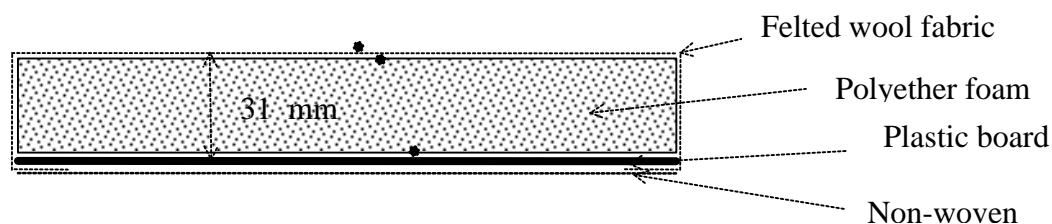


FIG. 1: A schematic drawing showing the structure of the chair seat used for measurements and calculations. The placement of the temperature and RH-sensors is indicated with a (•).

Table 1. Thickness and density

Material	Thickness (mm)	Density (kg/m <sup>3</sup> )
Polyether foam	31	36
Felted wool fabric (100% wool)	2.5	176

### 3. Methods

#### 3.1 Determination of moisture properties of the materials

The sorption isotherms as well as the water vapor resistances ( $Z$ ) were determined for the felted wool fabric and the polyether foam.

##### 3.1.1 Sorption balance

The sorption isotherms for the felted wool fabric and the polyether foam were determined using a sorption balance (DVS 1000, Surface Measurement Systems, London, UK (Anderberg, 2004)). The initial weights of the material samples were 57.7 mg and 21.2 mg respectively. The samples were initially dried in the instrument in dry nitrogen. The RH inside the instrument is generated with high precision by mixing dry and water vapor saturated nitrogen gas. Both absorption and desorption were determined in steps of 10 %RH (Svennberg, 2005). The temperature during the experiment was 21 °C.

The diffusivity for the felted wool fabric was evaluated from the step-change measurements provided by the sorption balance measurements mentioned earlier. The mass change is plotted against the square root of time and gives an essentially linear curve for the initial part of the step. From this the diffusivity,  $D$ , can be evaluated using an evaluation method based on (Crank, 1975). The method is presented in detail by (Anderberg, 2004). From the diffusivity and the air speed the vapor resistance  $Z_t$  of the textile layer can be calculated.

##### 3.1.2 Cup method

The vapor resistance for the 31 mm polyether foam was determined using the cup method according to EN ISO 12572:2001 in two intervals of RH, i.e. 75-49 %RH and 33-49 %RH with the exceptions given below. The cup shown in Fig. 2 was used for the measurements. The specimen was fastened to a plexiglass ring by use of silicone mastic, and the plexiglass ring with the specimen was fastened to the cup by use of rubber sealing as the tightening top was screwed to the cup. Inside the cup a supplementary glass cup containing the saturated salt solution was placed. By use of this supplementary glass cup the air layer thickness inside the cup was 6 mm. The area of cross-section of flow path was 5000 mm<sup>2</sup>.

Technical drawing of the experimental device for measuring the permeability of a specimen. The diagram shows a cross-section of the apparatus. A central specimen is held between two glass cups. The specimen is surrounded by a silicone layer, which is in turn surrounded by a rubber sealing layer. The entire assembly is held together by a Plexiglas ring and a tightening top. The specimen has a thickness of 31 mm. The silicone layer has a thickness of 8 mm. The rubber sealing layer has a thickness of 8 mm. The glass cup has a thickness of 8 mm. The Plexiglas ring has a thickness of 8 mm. The tightening top has a thickness of 8 mm. The net has a thickness of 8 mm. The salt solution is contained in the cup. The overall dimensions are given as e 190 mm and e 79.8 mm.

Labels in the diagram include:

- Plexiglas ring
- Silicone
- Specimen
- Net
- Tightening top
- Cup
- Specimen thickness 31 mm
- Rubber sealing
- Air layer thickness 8 mm
- Glass cup
- Salt solution


Dimensions:

- e 190 mm
- e 79.8 mm

The measured water vapor resistance  $Z_m$  is primarily the resistance in the specimen material itself  $Z_p$ , but also the surface resistances at the specimen surfaces  $Z_1$  and  $Z_2$  and the resistance in the air layer inside the cup  $Z_a$  must be taken into account. Refer Equation 1, which includes these resistances:

The surface diffusion resistances  $Z_1$  and  $Z_2$  may be found by Lewis' law, and the diffusion resistance  $Z_a$  for an air layer thickness of  $L_a$  is  $Z_a = L_a / \delta_a$ , where  $\delta_a$  is the water vapor permeability (WVP) in air. An analogy to heat transfer calculations is used to find water vapor pressure  $p_{1s}$  and  $p_{2s}$  and the corresponding relative humidities  $\phi_{1s}$  and  $\phi_{2s}$  at the specimen surfaces when the different diffusion resistances  $Z_a$ ,  $Z_1$ ,  $Z_2$  and  $Z_p$  are known (Hansen, 1990). The KOPLYSE 3.0 program (Mullit, 1993) which calculates water vapor resistance  $Z_m$  without corrections and the resistance in the specimen material itself  $Z_p$  with corrections together with the corresponding relative humidities  $\phi_{1s}$  and  $\phi_{2s}$  at the specimen surfaces was used in the evaluation.

The penetration measurements of the complete chair seat were performed in a full-scale well-insulated and moisture- and air tight climatic chamber (the PASSYS cell), see Fig. 3. In the climatic chamber the chair seat was subjected to a ramp variation in RH.



The indoor humidification, that represents the moisture production of an inhabited room, was provided by evaporation of moisture from a reservoir of water heated by an electric coil. Humidity was withdrawn from the air by a dehumidifier draining into the same reservoir. The drying represents the removal of humidity from the room that would normally take place by ventilation. The water reservoir was suspended in a load cell, and the rates of humidification and drying was controlled according to a predefined schedule. Padfield (1998) has used the principle in a small ( $0.5 \text{ m}^3$ ) test chamber in the laboratory. The climatic chamber is instrumented with sensors for measuring both the outdoor climate and the indoor conditions. The indoor relative humidity is measured with capacitive moisture sensors with an accuracy of about  $\pm 2 \text{ \%RH}$ . Two small fans were placed on the floor in both ends of the test cell to ensure a well-mixed airflow.

Three combined temperature and relative humidity sensors were applied on the chair seat for moisture penetration measurements. The first sensor was placed on top of the felted wool fabric. The second sensor was placed on top of the polyether foam but under the felted wool fabric and the third and last sensor was placed under the polyether foam. The sensors were placed somewhat displaced so that interference from the other sensors was minimized, see Fig 1.

### 3.3 Analytical solution

The measured water vapor content in the textile and at different depth in the polyether foam will be compared to the analytical solution, where the diffusion in the foam is coupled to the textile layer with its moisture capacity and the imposed vapor content in the air above.

#### 3.3.1 Mathematical problem

The water vapor content  $v(x,t)$  shall satisfy the diffusion equation. The initial value at  $t = 0$  is  $v_{in}$ . The moisture flux is zero at the boundary  $x = L$ . We have

$$0 < x < L: \quad \frac{1}{D_m} \cdot \frac{\partial v}{\partial t} = \frac{\partial^2 v}{\partial x^2}, \quad v(x,0) = v_{in}; \quad \left. \frac{\partial v}{\partial x} \right|_{x=L} = 0. \quad (2)$$

At the boundary  $x = 0$ , there is a textile layer with the moisture capacity  $C_{sm}$ . The moisture flow resistance to the outside air with the prescribed moisture content  $v_0(t)$  is  $Z_s$ . The moisture balance at the boundary  $x = 0$  becomes

$$C_{sm} \cdot \frac{\partial}{\partial t} [v(0,t)] = \frac{v_0(t) - v(0,t)}{Z_s} + d_v \cdot \left. \frac{\partial v}{\partial x} \right|_{x=0} \quad (3)$$

The two right-hand terms are the moisture fluxes from air and from the underlying material. We may multiply the equation by  $Z_s$ . The boundary condition then involves a time  $t_0 = C_{sm} \cdot Z_s$ , which is the decline time for the textile against air without flux from the underlying material. It also involves a length  $L_0 = Z_s \cdot d_v$ , which is a measure of the surface resistance  $Z_s$ .

The moisture content  $v_0(t)$  in the air varies in a “triangular” way between  $v_{in}$  and  $v_1$  with a time period  $t_p$ , see Fig. 4.

#### 3.3.2 Superposition of ramp solutions

The solution  $v(x,t)$  may be obtained from a basic *ramp* solution by suitable superposition. This is described in detail in (Claesson, 2005). Let  $v_r(x,t)$  be the solution for a ramp function:

$$v_0(t) = \begin{cases} t & t \geq 0 \\ 0 & t < 0 \end{cases} \quad v_r(x,0) = 0 \quad (4)$$

The ramp solution starts from zero:  $v_r(x,0) = 0$ ,  $0 \leq x \leq L$ .

We use the transformation

$$v(x, t) = v_{\text{in}} + \frac{v_1 - v_{\text{in}}}{t_p} \cdot v'(x, t) \quad (5)$$

The solution during the first period  $0 = t = t_p$  (and for  $t < 0$ ) is now  $v'(x, t) = v_r(x, t)$ . In the next period  $t_p \leq t \leq 2 \cdot t_p$ , we have to subtract two times the ramp solution that starts at  $t = t_p$ :

$$v'(x, t) = v_r(x, t) - 2 \cdot v_r(x, t - t_p), \quad t \leq 2t_p \quad (6)$$

In the next period, we have to add  $2 \cdot v_r(x, t - 2 \cdot t_p)$ , and so on. In general we have:

$$v'(x, t) = v_r(x, t) + 2 \cdot \sum_{m=1}^M (-1)^m \cdot v_r(x, t - m \cdot t_p), \quad t \leq (M + 1) \cdot t_p \quad (7)$$

### 3.3.3 Fourier solution

The basic ramp problem in (5) may be solved by a Fourier series expansion. A detailed report of this is given in (Claesson, 2005). The solution for  $t \geq 0$  is given by:

$$v_r(x, t) = t - \frac{LL_0 + D_m t_0 + xL - x^2/2}{D_m} + \sum_{n=0}^{\infty} B_n \cos[\mathbf{a}_n(1 - x/L)] \cdot e^{-\mathbf{a}_n^2 D_m t / L^2} \quad (8)$$

Here, the Fourier coefficients are

$$B_n = \frac{2L^4}{D_m \mathbf{a}_n^2} \cdot \frac{\cos(\mathbf{a}_n)}{L_0 L \mathbf{a}_n^2 + \cos^2(\mathbf{a}_n) \cdot (D_m t_1 \mathbf{a}_n^2 + L^2)} \quad (9)$$

The eigenvalues  $\mathbf{a}_n$  are the solution to

$$\frac{L}{L_0 \cdot \mathbf{a}_n} - \frac{D_m t_1}{L^2} \cdot \mathbf{a}_n = \tan(\mathbf{a}_n), \quad 0 < \mathbf{a}_0 < \mathbf{a}_1 < \dots \quad (10)$$

The series solution converges very rapidly except for small times. An alternative solution from Laplace transformation is then used. The complete solution is implemented in Mathcad. The result with five-digit accuracy is obtained requiring very little computer time (less than 2 s for the case of Fig.4). All these details are reported in (Claesson, 2005).

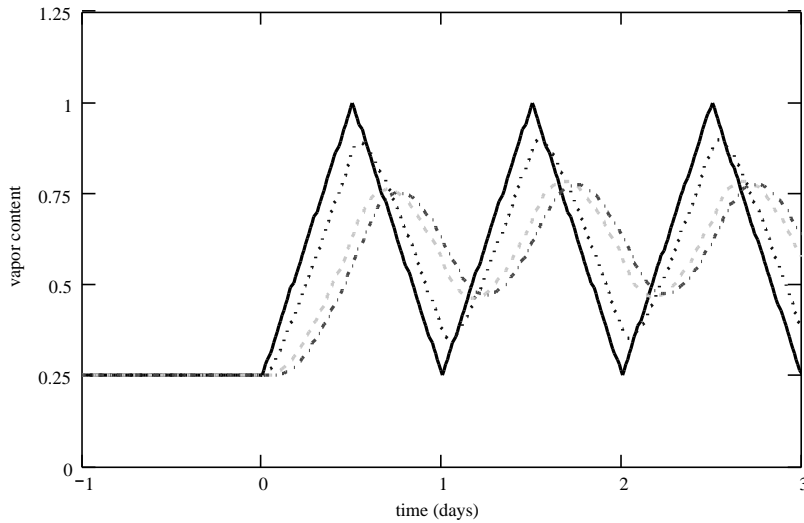


FIG. 4: Water vapor content  $v_0(t)$  (solid black line) in the air at the boundary  $x=0$ , normalized values of all parameters was used (all equal to 1). The dashed lines represent different depths in the foam: dotted black – under fabric, light grey - half depth in the foam, medium grey - under the foam.

## 4. Results

### 4.1 Determination of material moisture properties

The sorption isotherms for the felted wool fabric and polyether foam shows a great difference in moisture capacity see Fig. 5. The diffusivity for the wool fabric in the range 35-75 %RH was estimated to  $450 \cdot 10^{-6} \text{ m}^2/\text{s}$ .

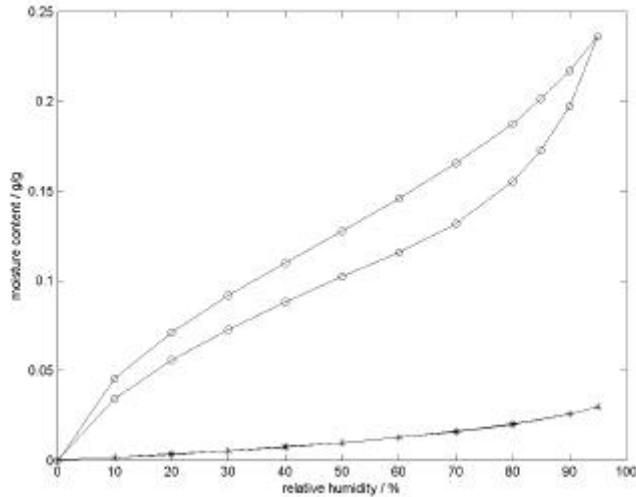


FIG. 5: The sorption isotherm for the felted wool fabric (o) and the polyether foam (\*).

The results of the water vapor resistance  $Z_m$  without corrections, and the resistance in the specimen material itself  $Z_p$  with corrections for  $Z_a$ ,  $Z_1$  and  $Z_2$  for the 31 mm polyether foam is shown in table 2.

Table 2. The results of the water vapor resistance  $Z_m$  without corrections and the resistance in the specimen material itself  $Z_p$  with corrections for  $Z_a$ ,  $Z_1$  and  $Z_2$  for the 31 mm polyether foam. The RH inside the cups was 75 %RH for cups no. 1-3 and 33 %RH for cups no. 4-6.

Cup no.	Without corrections		With corrections	
	$Z_m$ (GPa·s·m <sup>2</sup> /kg)	$Z_{m\text{-average}}$ (GPa·s·m <sup>2</sup> /kg)	$Z_p$ (GPa·s·m <sup>2</sup> /kg)	$Z_{p\text{-average}}$ (GPa·s·m <sup>2</sup> /kg)
1	0.34	0.34	0.27	0.27
2	0.33		0.26	
3	0.35		0.28	
4	0.35	0.35	0.28	0.28
5	0.35		0.28	
6	0.36		0.29	

The material parameters used in the calculation of the analytical solution is shown in table 3.

Table 3. Material properties used in the theoretical calculations.

Material	Diffusivity $D$ (m <sup>2</sup> /s)	Moisture capacity $x$ (-)	Surface resistance $Z_{sv}$ (s/m)	Surface resistance $Z_{sp}$ (GPa·s·m <sup>2</sup> /kg)
Felted wool fabric	$450 \cdot 10^{-6}$	0.44	100	0.014
Polyether foam	$0.36 \cdot 10^{-6}$	0.025	-	-

### 4.2 Comparison between chair measurements and analytical solution

The analytical solution uses an ideal triangular variation for the ambient climate (e.g. boundary conditions) and is therefore not capable of taking the small fluctuations caused by



the climatic system. Still the analytical solution provides a good representation of the moisture penetration in the chair seat. An addition of internal resistance in the analytical solution as well as using truer boundary conditions would improve the already satisfactory agreement between measurement and theoretical calculations even more.

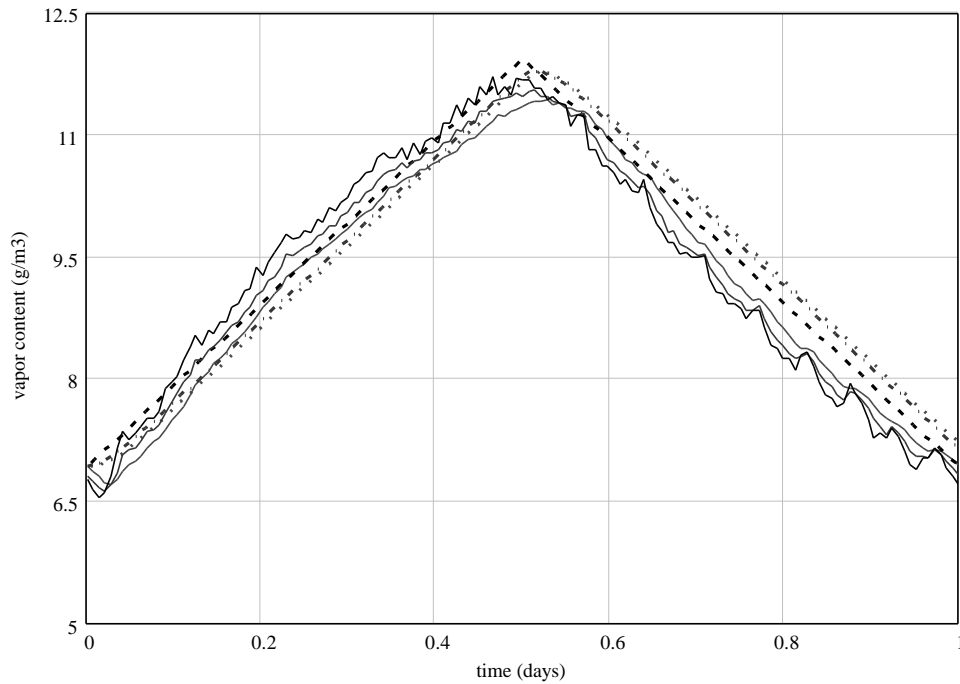


FIG.6: Comparison between the measured vapor content in the chair seat during the climatic chamber experiments (thin solid lines: black – the top surface, medium grey - under the fabric, light grey – under the polyether foam) and the analytical solution (thick dashed lines: black – the top surface, dashed grey- under the fabric, dotted grey – under the polyether foam).

## 5. Discussion

The results of the water vapor resistance  $Z_m$ -average without corrections for the 31 mm polyether foam are in range 0.34-0.35  $\text{GPa}\cdot\text{s}\cdot\text{m}^2/\text{kg}$  for the two intervals of RH, which gives the results of the water vapor resistance  $Z_p$ -average with corrections for  $Z_a$ ,  $Z_1$  and  $Z_2$  in the same range 0.27-0.28  $\text{GPa}\cdot\text{s}\cdot\text{m}^2/\text{kg}$  for the two intervals of RH. The corrections are in the range 0.07  $\text{GPa}\cdot\text{s}\cdot\text{m}^2/\text{kg}$  which is 20 % of  $Z_m$ .

In the measurements the air layer thickness inside the cup was 6 mm, while EN ISO 12572:2001 recommends 15 mm air layer thickness. Smaller air space between sorption material and specimen gives higher RH on specimen surface against cup for the interval 75-49 %RH, as resistance of air layer is smaller. But also the overall measured diffusion resistance for the test  $Z_m$  for this very porous polyether foam is highly influenced by the air layer thickness. The large influence of the resistance in the air gap makes the traditional cup method unsuitable for thin and permeable textile layers. The method to evaluate the diffusivity from the step measurements made in the sorption balance is promising but need further validation. They also provide simultaneous determination of sorption isotherms and moisture transport properties.

The determination and estimation of surface and internal resistance to the type of multi-layered material combinations that this chair seat represent are also a matter for more investigations since they have a rather large impact on calculated results.

## 6. Conclusions

The presented analytical solution and measured data commence a better understanding of the moisture dynamics for furnishing such as textiles and soft furniture for daily variations in the indoor climate. More work is needed to find ways to couple this to room or building simulation tools. The methods to assess material properties used in this study showed to be useful for highly permeable materials.

## References

- Anderberg, A. (2004). Moisture properties of selflevelling flooring compounds. Lund, Building Materials, Lund University.
- Claesson, J. and K. Svennberg (2005). Moisture dynamics of a textile sheet with an underlying polymer slab. Analytical solution for a piece-wise linear air humidity. Lund, Building Physics, Lund University.
- Crank, J. (1975). Mathematics of diffusion, Oxford Science Publisher.
- Hansen, K. K. and H. B. Lund (1990). Cup method for determination of water vapour transmission properties of building materials. Sources of uncertainty in the method. 2nd Symp. Building Physics in the Nordic Countries, Trondheim.
- Martin, P. C. and J. D. Verschoor (1986). Cyclical moisture desorption/absorption by building construction and furnishing materials. Symposium on Air, Infiltration, Ventilation and Moisture Transfer, Fort Worth, TX, USA, Building Thermal Co-ordinating Council.
- Mullit, P. (1993). KOPLYSE ver.3.0. Program til analyse af måleresultater opsamlet i KOP-udstyr., Lab. for Bygningsmaterialer, DTH.
- Plathner, P. and M. Woloszyn (2002). "Interzonal air and moisture transport i a test house. Experiment and modeling." Building and Environment 37: 189-199.
- Svennberg, K. (2003). Determination of Moisture Properties for Materials Exposed to the Indoor Air. Lund, Building Physics, Lund University.
- Svennberg, K. (2005). Sorption isotherms for textile fabrics and foam used in the indoor environment. Lund, Building Physics, Lund University.
- Svennberg, K., L. Hedegaard, & C. Rode (2004). Moisture Buffer Performance of a Fully Furnished Room. Whole Building Envelope IX. Clearwater Beach, FL, ASHRAE.

## Acknowledgement

The experimental help from Anders Anderberg and Dr. Lars Wadsö at Lund University and Lone Hedegaard and Dr. Carsten Rode at the Technical University of Denmark is gratefully acknowledged. The work was carried out with support from FORMAS and IKEA.