



LUND UNIVERSITY

Pulp faction

3d printed material assemblies through microbial biotransformation

Goidea, Ana; Floudas, Dimitrios; Andréen, David

Published in:
Fabricate 2020

2020

Document Version:
Publisher's PDF, also known as Version of record

[Link to publication](#)

Citation for published version (APA):

Goidea, A., Floudas, D., & Andréen, D. (2020). Pulp faction: 3d printed material assemblies through microbial biotransformation. In J. Burry, J. Sabin, B. Sheil, & M. Skavara (Eds.), *Fabricate 2020: Making resilient architecture* (pp. 42-49). (FABRICATE). UCL Press.

Total number of authors:
3

Creative Commons License:
CC BY

General rights

Unless other specific re-use rights are stated the following general rights apply:
Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

Read more about Creative commons licenses: <https://creativecommons.org/licenses/>

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

LUND UNIVERSITY

PO Box 117
221 00 Lund
+46 46-222 00 00

FA RICA TE

UCLPRESS

JANE BURRY / JENNY SABIN / BOB SHEIL / MARILENA SKAVARA


FABRICATE 2020

MAKING RESILIENT ARCHITECTURE

JANE BURRY / JENNY SABIN / BOB SHEIL / MARILENA SKAVARA



Cornell AAP
Architecture Art Planning

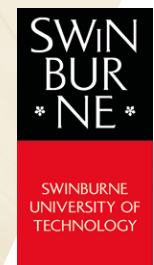

CONTENTS

4

Foreword

Christoph Lindner
Zoe Laughlin
Frédéric Migayrou

6

Acknowledgements

8

Introduction

Jane Burry
Jenny Sabin

12

From Making Digital Architecture to Making Resilient Architecture

Bob Sheil

1

BIO-MATERIALITY

22

MUD Frontiers

Virginia San Fratello
Ronald Rael

28

The Design and Fabrication of Confluence Park

Andrew Kudless
Joshua Zabel
Chuck Naeve
Tenna Florian

36

The Role of Robotic Milling in the Research and Development of the Cork Construction Kit

Oliver Wilton
Matthew Barnett Howland
Peter Scully

42

Pulp Faction: 3D printed material assemblies through microbial biotransformation

Ana Goidea
Dimitrios Floudas
David Andréen

50

From Machine Control to Material Programming: Self-shaping wood manufacturing of a high performance curved CLT structure – Urbach Tower

Dylan Wood
Philippe Grönquist
Simon Bechert
Lotte Aldinger
David Riggenbach
Katharina Lehmann
Markus Rüggeberg
Ingo Burgert
Jan Knippers
Achim Menges

58

Bending the Line: Zippered wood creating non-orthogonal architectural assemblies using the most common linear building component (the 2x4)

Blair Satterfield
Alexander Preiss
Derek Mavis
Graham Entwistle
Marc Swackhamer
Matthew Hayes

66

Biocomposites from Annually Renewable Resources Displaying Vision of Future Sustainable Architecture: Design and fabrication of two 1:1 demonstrators

Hanaa Dahy
Jan Petrš
Piotr Baszyński

74

Cellulosic Biocomposites for Sustainable Manufacturing

Stylianios Dritsas
Yadunund Vijay
Samuel Halim
Ryan Teo
Naresh Sanandiya
Javier G. Fernandez

2

SYNTHESISING DESIGN AND PRODUCTION

84

Kuwait International Airport Terminal 2: Engineering and fabrication of a complex parametric megastructure

Lucio Blandini
Guido Nieri

92

A Factory on the Fly: Exploring the structural potential of cyber-physical construction

Asbjørn Søndergaard
Radu Becus
Gabriella Rossi
Kyle Vansice
Rahul Attraya
Austin Devin

100

Direct-to-Drawing: Automation in extruded terracotta fabrication

Scott Overall
John Paul Rysavy
Clinton Miller
William Sharples
Christopher Sharples
Sameer Kumar
Andrea Vittadini
Victoire Saby

108

The Tide [Phase 1]: Greenwich Peninsula, London

Emmanuel Verkinderen
Bryce Suite
Ryan Neiheiser
Edoardo Tibuzzi
Jeg Dudley

116

Making Form Work: Experiments along the grain of concrete and timber

Sasa Zivkovic
Leslie Lok

124

Additive Fabrication of Concrete Elements by Robots: Lightweight concrete ceiling

Georg Hansemann
Robert Schmid
Christoph Holzinger
Joshua P. Tapley
Hoang Kim Huy
Valentino Sliskovic
Bernhard Freytag
Andreas Trummer
Stefan Peters

130

DFAB House: A comprehensive demonstrator of digital fabrication in architecture

Konrad Graser
Marco Baur
Aleksandra Anna Apolinarska
Kathrin Dörfler
Norman Hack
Andrei Jipa
Ena Lloret-Fritschi
Timothy Sandy
Daniel Sanz Pont
Daniel M. Hall
Matthias Kohler

140

Knit-Castella: Challenging the construction, logistics, waste and economy of concrete-shell formwork

Mariana Popescu
Matthias Rippmann
Tom Van Mele
Philippe Block

150

Q&A 1

Antoine Picon with Julia Barfield and Kai Strehlke

Moderated by Jenny Sabin

156

Q&A 2

Monica Ponce de Leon with Cristiano Ceccato

Moderated by Jenny Sabin

162

Q&A 3

Carl Bass with Philippe Block

Moderated by Jane Burry

168

Q&A 4

Mette Ramsgaard Thomsen with Meejin Yoon

Moderated by Jane Burry

174

Q&A BIOGRAPHIES

3

OPTIMISATION FOR A CHANGING WORLD

178

Architectural Scale Kagome Weaving: Design methods and fabrication concepts

Phil Ayres
Adam Orlinski
Moritz Heimrath
Soraya Bornaz
Alison Grace Martin

186

Rethinking Efficient Shell Structures with 3D-Printed Formwork

Xiang Wang
Chun Pong So
Liming Zhang
Zhewen Chen
Philip F. Yuan

194

Knit-Castella: Challenging the construction, logistics, waste and economy of concrete-shell formwork

Mariana Popescu
Matthias Rippmann
Tom Van Mele
Philippe Block

202

Printed Assemblages: A co-evolution of composite tectonics and additive manufacturing techniques

Roland Snooks
Laura Harper

210

Large-Scale Free-Form Timber Grid Shell: Digital planning of the new Swatch headquarters in Biel, Switzerland

Hanno Stehling
Fabian Scheurer
Sylvain Usai

218

Optimisation of Robotic Printing Paths for Structural Stiffness Using Machine Learning

Zeynep Aksöz
Samuel Wilkinson
Giannis Nikas

226

The Anatomy of a Skeleton: Hybrid processes for large-scale robotic fabrication

Emmanuel Vercruysse

234

BUGA Fibre Pavilion: Towards robotically-fabricated composite building structures

Serban Bodea
Niccolo Dambrosio
Christoph Zechmeister
Marta Gil Pérez
Valentin Koslowski
Bas Rongen
Moritz Dörstelmann
Ondrej Kyjanek
Jan Knippers
Achim Menges

246

Embedded Architecture: Ada, driven by humans, powered by AI

Jenny E. Sabin
John Hilla
Dillon Pranger
Clayton Binkley
Jeremy Bilotti

256

Diagrams of Entropic Forces: Design for new dissipative fabrication

Phillip Beesley

264

Discrete Timber Assembly

Gilles Retsin

272

Towards Discrete Automation

Mollie Claypool

280

House #05: Incremental construction in digital practice

Paul Loh
David Leggett

286

Concrete Choreography: Prefabrication of 3D-printed columns

Ana Anton
Patrick Bedarf
Angela Yoo
Lex Reiter
Timothy Wangler
Robert J. Flatt
Benjamin Dillenburger

294

Little Island: Sculptural structure through digital design and fabrication

Yong-Wook Jo
Rosario Gallo
David Farnsworth
Jacob Wiest

302

Hudson Yards Vessel, New York

Edoardo Tibuzzi
Pablo Zamorano
Peter Romvari
Jeg Dudley

310

Editors: Biographies

311

Contributors: Biographies

320

Partners / Colophon

PULP FACTION

3D PRINTED MATERIAL ASSEMBLIES THROUGH MICROBIAL BIOTRANSFORMATION

ANA GOIDEA / DIMITRIOS FLOUDAS / DAVID ANDRÉEN
LUND UNIVERSITY

The world is currently facing an ecological crisis of unprecedented scale and urgency and, as the building sector is a significant contributor to the current state, it must look towards radical change to achieve a sustainable practice. The most destructive environmental impact is found in material extraction, processing and discharge. This paper presents an alternative to industrially mined and synthesised materials by utilising biological growth processes as passive engines for the transformation of renewable materials. This is achieved through fungal-lignocellulosic composites which have been developed along with the design and fabrication processes that are necessary for their application in the construction industry.

Plant-derived materials are abundantly and sustainably available on both local and global scales, particularly in the form of by-products and recycled waste. Additive fabrication provides an opportunity to create high value products from this material, but comes with its own challenges. In particular, most of the strength of the wood is lost as fibres are ground down so that the material can pass through the extrusion nozzle. Rather than relying on thermosetting plastics or synthetic binders, this project explores the controlled growth of fungal mycelium within


the printed material post-extrusion as a binder of lignocellulosic biomass.

Fungal-lignocellulosic materials inherit properties from both wood and mycelium, resulting in lightweight and strong bio-composites. Generally, they exhibit good insulative performance for both heat and sound, are hydrophobic, and have good tension and compression resistance (Yang et al., 2017; Elsacker, 2019). In addition, the raw materials for such composites are low in cost, locally sourced, renewable, and able to capture and store carbon dioxide.

Mycelium Bio-Composites

The main components of mycelium composites are the biopolymers cellulose and chitin, followed by lignin and hemicellulose. Mycelium is the vegetative part of a fungus, made up from a dense network of long, branching filamentous structures termed hyphae. The cell wall of the hyphae is made of chitin – a tough, resilient, inert and non-water-soluble modified polysaccharide that has promising potential in biotechnology (Latgé and Calderon, 2006). When the fungus colonises a substrate, it first grows on the surface and gradually, depending on



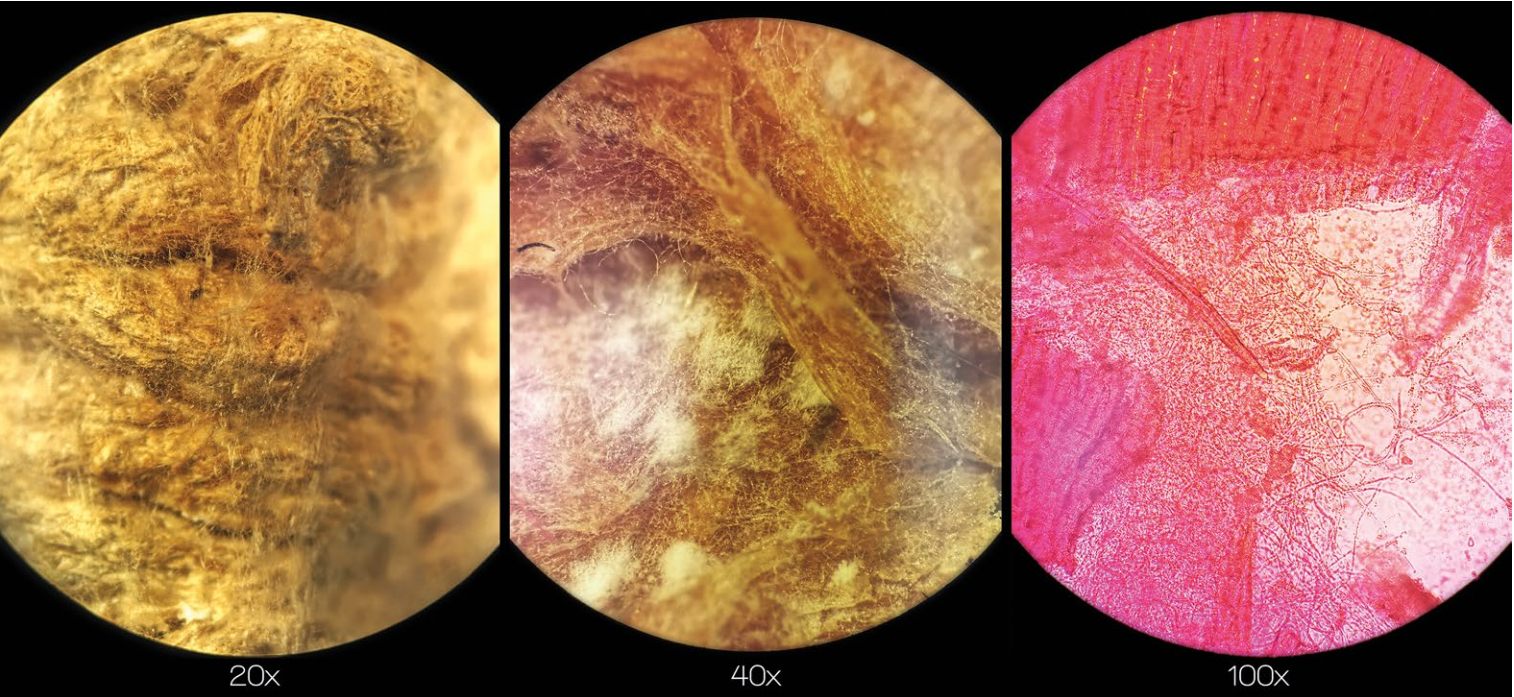

2

the properties of the material, it spreads its mycelium throughout it in a complex three-dimensional binding matrix (Boyce and Andrianopoulos, 2006) (Fig. 4). During growth, the fungus secretes extracellular polymeric substances (EPS), which are mainly composed of polysaccharides and proteins (Gazzé et al., 2013). Their role is to facilitate growth and allow the anchoring of the cells on the substrate, acting as a glue between the hyphae and the substrate. Moreover, EPS allow for the conglomeration of particles around the hyphae, resulting in an irreversible fusing of the material (Fig. 2).

3D Bio-Printing

Most precedents using lignocellulosic substrate and mycelial growth for creating bio-composites use casting as the means of production, for example: The Living’s Hy-Fi Tower (Nagy et al., 2015); Block Research Group’s MycoTree (Heisel et al., 2018); Mogu panels (Appels et al., 2019). Such methods are relatively straightforward and therefore well-suited for industrial mass-production. However, the casting process limits the customisation of the products as well as geometrical complexity that can be employed for functional performance. In addition, the strength of the material is markedly determined by the extent of the mycelium coverage (Yang et al., 2017). As this is dependent on oxygen, growth is limited to the material surface. When cast in solid volume, the mycelium

covers a smaller percentage of the total volume, limiting the potential strength of the composite.

These limitations can be overcome through the use of digital additive fabrication which allows for a complex meso-scale structure, radically increasing the surface area within a given volume and thus ensuring maximum distribution of hyphae within the composite.

The strategy of additively fabricating mycelium composites is not unprecedented in nature. Mound-building macrotermites have evolved to a symbiotic existence together with fungus of the genus *Termitomyces*. The termites harvest plant-based material and carry it back to the mound where the regulated internal climate is suitable for fungi. The fungus processes the plant matter, turning it into nutrients that both the termites and fungus live on (Turner, 2005). The fungal combs (Fig. 3) have a particular geometry which, on the one hand provides access to the termites for managing the comb, and on the other enable a convective flow of air and respiratory gases near the comb surfaces. This flow is facilitated by vertical channels and assisted by the thermal buoyancy generated by the metabolic heat of the fungus. The combs are constructed as an intricately folded and interconnected sheet with an even thickness of approximately 4mm, likely corresponding to the depth at which the mycelium can effectively grow while maintaining access to oxygen. The

1. Section of a column showing an assembly of the fungal-lignocellulosic components. Bonding between the segments is proposed to be achieved by extrusion of a connective tissue consisting of a modified version of the live pulp.

2. Substrate under microscope. The different magnifications showing: (1) The print layers covered in mycelium. (2) The fusion of mycelium and substrate. (3) The partial decomposition of the cellulose and lignin fibres by the fungus.



3

fungus comb provided an initial set of assumptions for a design that could provide a suitable balance of parameters in the project.

Integrated Research Protocols

The research presented in this article concerns the finding of a set of processes for additive fabrication of fungal-lignocellulosic materials and the evaluation of their suitability for architectural fabrication. The primary intent was to address the questions that arise from the interdependencies between these processes through a transdisciplinary approach. Focus has been on testing feasibility, building a protocol, and establishing a foundation for informed speculation.

The research was guided by the following questions: How can a process of bio-fabrication best be structured to achieve desirable artefacts? How does the introduction of fungal mycelium affect the material properties? And how could the developed processes be utilised for fabrication at architectural scales?

To answer these questions, the presented work explored the interconnections between (1) the living system, (2) the digital fabrication, and (3) the computational design strategy. Subsequently, a number of material performance tests were carried out on the resulting samples. The protocol presented here led to the most successful outcomes with regards to rate of growth, extrudability, stability and resulting material properties.

3. *Termitomyces* fungus comb. This symbiotic structure is additively assembled by macrotermites from dead plant matter inoculated with fungal spores. The fungus slowly digests the plant matter into components which the termites can ingest as food, while it simultaneously acts to regulate the humidity of the mound’s internal climate.

4. Living printed composite after two weeks of incubation.



4

Live Pulp

The pulp consists of a substrate that has been inoculated with fungus. The substrate was developed to comply with two primary criteria: its ability to support the growth and development of the fungus, and its suitability for fabrication which includes both extrudability and the stability of the material in the print and growth phases. The main components of the substrate are fine woodchips, paper pulp, and kaolin clay, which are mixed with water. Wood and paper pulp compose the bulk of the material and provide the nutrients for the fungus; during incubation, these are partially transformed into fungal biomass. As the substrate doesn’t have an immediate bonding agent, it remains unstable during printing. Therefore, clay was added to the mixture to provide stability during the fabrication and incubation phases. The substrate also contains a thickening agent which allows the solid and liquid components to form a coherent aggregate (Fig. 10).

Two fungal strains were used in the experiments, a strain of *Byssomerulius corium* and a strain of *Gloeophyllum* sp. They are both wood decomposers, but follow different strategies of wood decomposition termed white rot and brown rot, respectively. Both fungal strains were propagated on a malt-yeast medium. When the mycelial growth was sufficient, the fungus was introduced into the autoclaved substrate. The inoculated substrate was left for an incubation period of one week, in which the mycelium propagated through the substrate and adapted to the new environment, enabling it to resist contaminants introduced when sterile conditions were no longer maintained.

Following the initial incubation, the pulp was 3D printed, after which it went through a second and longer incubation period. This allowed the mycelium to grow through the printed artefacts and transform the substrate into the desired bio-composite. Once the growth had reached the target state, the printed component was desiccated to reach its final and stable form, stopping the decomposition process.

Fabrication Strategy

The live pulp was 3D printed using Vormvrij Lutum v4, which relies on a combination of pressurised air and a rotating auger to extrude material. A nozzle diameter of 3.5mm was used in combination with a layer height of 1.5mm, which provided a working balance of resolution, stability, and print speed.

Several factors influence the stability of the print, and the ability to produce artefacts with the desired geometric variation. A larger nozzle and consequently greater wall thickness make for more stable prints, but have the drawback of lower resolution and decrease in surface to volume ratio, which reduces the amount of mycelial growth on the material. Straight vertical walls are prone to both deformation and collapse. To reduce this, the curvatures have been maximised and additional interconnections between walls were introduced.

During desiccation, the material contracts in volume by approximately 30%. In order to minimise the resulting distortion, a set of aluminium meshes with vertical channels were used as print base and cover. These secure the position of the first and last layers, thereby constraining the contraction to the Z-axis. Mesh-print adhesion was improved by the explorative growth of the mycelium. The meshes allow vertical airflows through the print, supporting biological growth by ensuring even moisture levels and the circulation of respiratory gases, and eventually facilitate rapid and even desiccation.

Design Strategy


In addition to the architectural scale constraints, the design of the components had to accommodate both the biological requirements of the fungus and the mechanical constraints of the printing process. A reaction-diffusion simulation based on the the Gray-Scott model generated the basis for the form-finding of the fabricated geometries. The scale of the pattern was derived from the fungus comb reference. This generative model has been developed by increasing the feed rate along the vertical axis. The boundaries of the geometry have been created at the



5



6

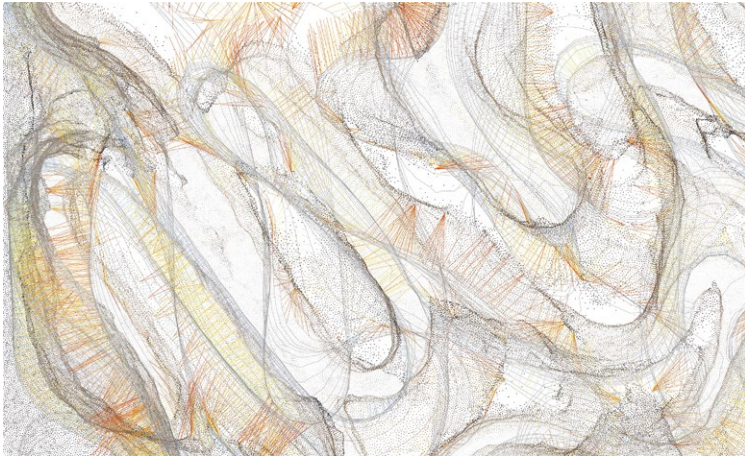


7

transition points between the two simulated substances. Subsequently, the resulting geometry consists of two (internal and external) interwoven volumes that never converge, lending itself to functional use in the architectural outcome. Similar to the structure found in fungus combs, the model ensures significant vertical continuity that is beneficial to flows of both air and structural forces. (Fig. 5)

The curves that constitute the print layers are taken through a secondary algorithmic transformation which connects all curves into a single curve on a per-layer basis. This transformation allows for a continuous extrusion rate along an uninterrupted toolpath which improves speed, stability and precision in the print process. This also ensures that the entire printed component is cohesive and that additional stabilising cross-bracings are created without disturbing the continuity and separation of the two sets of volumes. In order to maintain thin extrusions while increasing the print height, the design strategy combined vertical continuity with recurring interconnections, while strengthening through double curvature.

Results

Three different material samples (designated *So*, *S1*, and *S2*) were tested for the resulting material properties and their suitability for architectural application. *So* was printed substrate with no fungal inoculation, *S1* was pulp with the fungal species *Byssomerulius corium*, and *S2* was pulp with a *Gloeophyllum* sp. (Fig. 6). Three tests were carried out: a bending test to evaluate stiffness, a test for dispersion in water, and a test for water absorption properties. Since the results from these tests indicated that the *Gloeophyllum* pulp composite has the most desirable properties, additional samples were produced and further scanned to

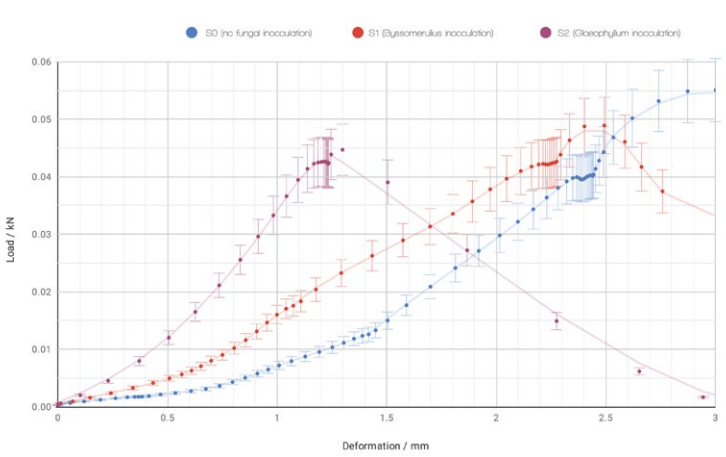

8

characterise the distortion of the material during drying (Fig. 7). This is notable since most other mycelium-based materials use white rot fungus, while here it was found that the brown rot fungus, *Gloeophyllum*, gave the better result.

Mechanical Performance

The bending test showed that the samples with more extensive hyphae distribution exhibited significantly higher stiffness than the mycelium-free sample and afforded a slightly higher force before failure (Fig. 8). The deformation before failure was twice as high for *So* as *S2*, with *S1* falling in between. The hardness of the material as perceived when cutting the samples with a sharp knife was significantly higher with increased hyphae coverage (*S2* > *S1* > *So*).

Dispersion in Water

The resilience of the material bond when wet was tested by submerging the samples in water for a period of 10 hours. After this period, the water and samples were stirred (Fig. 9). The sample without mycelium (*So*) quickly swelled and completely disintegrated upon agitation. *S1* and *S2* remained intact during stirring.

Hydrophobicity

A droplet of water was placed on each of the surfaces of the three samples, and the subsequent absorption was observed. The droplets on *So* and *S1* were quickly absorbed, while the droplet placed on *S2* did not absorb but maintained its shape, indicating strong hydrophobicity on the material surface (Fig. 11). The samples' capacity for buffering water in vapour form was also measured, and remained equally high in all three samples.


Bio-Integrated Design:
Architecture as Multi-Scalar Interfaces

The printed prototypes and tests conducted on the resulting bio-composite demonstrate some of the advantages of the proposed approach. The resulting components were highly hydrophobic with a retained capacity of moisture buffering, and remained stable even when exposed to prolonged submersion in water. The transformation of the material by the fungus resulted in improved stiffness and hardness, and eliminated the tendency of the samples to delaminate between printed layers. The surface hardness of the resulting material was markedly different from many other reported mycelium-based materials. This may be due to the use of a brown rot fungus instead of white rot, and this strain’s interaction with the substrate. However, further studies are required to investigate these relationships.

The ability to fabricate larger scale elements relies on navigating the requirements in the design space, and the stability and predictability of the printed components in the growth and desiccation phases. The robustness of the process was improved by the inclusion of clay to the substrate as well as the use of stabilising meshes. Equally, the component design is of critical significance, both in terms of enabling the growth of the mycelium and stabilising the material during and after fabrication. This resulted in a requirement for a high surface area, high curvature form.

When engaging with the agency of microorganisms as well as with highly responsive and interdependent materials, significant constraints are placed on the design. These constraints require integration between the multiple scales of the project, from the microscopic scale of microbial behaviour, through the material arrangement at the centimetre scale, all the way to the component and assembly, and eventually human scales. Rather than considering these constraints as limitations, they present an opportunity for responsive and functional architectures.

The demonstrated components (Fig. 1) assemble into a column that retains several of the properties that allow the fungus to thrive: it has a high surface area ratio, the vertical interstitial spaces allow for convective flow, and the material exhibits an active interaction with air and water vapour. These properties remain after the element is constructed, and can be utilised to affect and modulate the environment in direct proximity to the column. Rather than a passive load-carrying element, such a structure should be considered a part of a building’s vascular

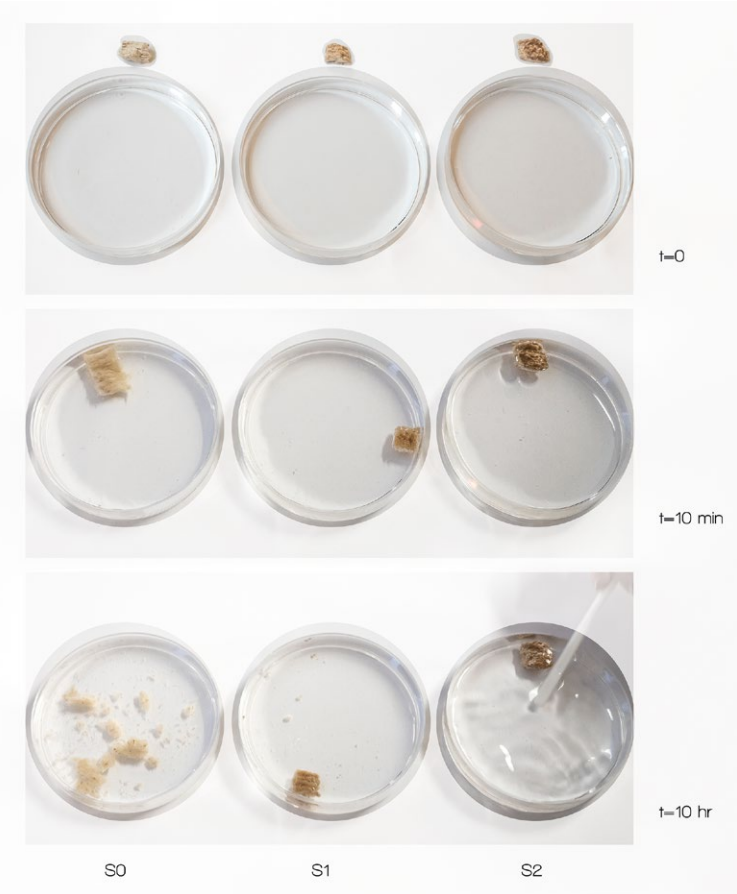

system, mediating and enabling flows that drive an active modulation of the micro-climates which the occupants inhabit.

Conclusion

The project demonstrates both the challenges and the potential of additive fabrication of mycelium composites. The introduction of fungus improves the properties of the resulting material in multiple ways, resolving difficulties associated with wood printing through improved water resistance and increased stiffness and hardness. Compared to previous fungus composites which are typically fabricated through casting, additive fabrication can improve the conditions for fungus growth, enabling faster growth rates and more complete coverage. This can result in better material performance and more efficient manufacturing. The process enables complex and customised form beyond what can be achieved through casting, opening up new functional potential in the resulting products.

The biologically active process adds constraints, such as the need for sterile material processing and the prolonged wet state. However, it was demonstrated how a combination of material composition, design integration and fabrication processes can be used to overcome these challenges, potentially enabling the use of such materials in the construction industry. If implemented at large scales, such a shift could radically reduce the building industry’s ecological footprint by lessening the need for extraction of non-renewable minerals and for energy intense chemical processing, while ensuring environmentally safe and biodegradable properties.

Acknowledgements

This research has been funded by The Crafoord Foundation and Boverket, the Swedish National Board of Housing, Building and Planning. We would also like to extend our gratitude to Eva Frühwald Hansson and Maria Fredriksson at Lund University for their assistance with the material testing.

References

Appels, F.V.W., Camere, S., Montalti, M., Karana, E., Jansen, K.M.B., Dijksterhuis, J., Krijgsheld, P. and Wösten, H.A. 2019. 'Fabrication factors influencing mechanical, moisture- and water-related properties of mycelium-based composites', *Materials & Design*, 161, pp. 64-71.

Boyce, K.J. and Andrianopoulos, A. 2006. 'Morphogenesis: Control of Cell Types and Shape', in Kües U., Fischer R. (eds), *Growth, Differentiation and Sexuality vol 1: The Mycota (A Comprehensive Treatise on Fungi as Experimental Systems for Basic and Applied Research)*, Berlin, Heidelberg: Springer, pp. 3-20.

Elsacker, E., Vandelook, S., Brancart, J., Peeters, E. and De Laet, L. 2019. 'Mechanical, physical and chemical characterisation of mycelium-based composites with different types of lignocellulosic substrates', *PLoS ONE* 14(7), p. e0213954. (doi: 10.1371/journal.pone.0213954)

Gazzè, S.A., Saccone, L., Smits, M.M., Duran, A.L., Leake, J.R., Banwart, S.A., Ragnarsdottir, K.V. and McMaster, T.J. 2013. 'Nanoscale Observations of Extracellular Polymeric Substances Deposition on Phyllosilicates by an Ectomycorrhizal Fungus', *Geomicrobiology Journal*, 30(8), pp. 721-730.

Heisel, F., Lee, J., Schlesier, K., Rippmann, M., Saeidi, N., Javadian, A., Nugroho, A., Mele, T., Block, P. and Hebel, D. 2018. 'Design, Cultivation and Application of Load-Bearing Mycelium Components: The MycoTree at the 2017 Seoul Biennale of Architecture and Urbanism', *International Journal of Sustainable Energy Development*, 6(1), pp. 296-303.

Latgé, J. P. and Calderone, R. 2006. 'The Fungal Cell Wall', in Kües U., Fischer R. (eds), *Growth, Differentiation and Sexuality vol 1: The Mycota (A Comprehensive Treatise on Fungi as Experimental Systems for Basic and Applied Research)*, Berlin, Heidelberg: Springer, pp. 73-104.

Nagy, D., Locke, J. and Benjamin, D. 2015. 'Computational Brick Stacking for Constructing Free-Form Structures', in Thomsen M., Tamke M., Gengnagel C., Faircloth B. and Scheurer F. (eds), *Modelling Behaviour*, Cham: Springer, p. 203-212.

Turner, J. S. 2005. 'Extended physiology of an insect-built structure', *American Entomologist*, 51(1), pp. 36-38.

Yang, Z., Zhang, F., Still, B., White, M. and Amstislavski, P. 2017. 'Physical and Mechanical Properties of Fungal Mycelium-Based Biofoam', *Journal of Materials in Civil Engineering*, 29(7). (doi: 10.1061/(ASCE)MT.1943-5533.0001866)

9. Dispersion in water. The fungus-free sample disintegrates completely, while the two fungal composites exhibit minimal swelling and remain intact after stirring.

10. Substrate development prototype, here without fungus. The substrate was tested for extrudability, as well as for the design – material compatibility.

11. Hydrophobicity. From left: S0, S1, S2.

EDITORS BIOGRAPHIES

Jane Burry

Jane Burry is an architect, professor and Dean of the School of Design at Swinburne University of Technology, Melbourne, Australia. She is lead author of *The New Mathematics of Architecture* (Thames & Hudson, 2010), editor of *Designing the Dynamic* (Melbourne Books, 2013) and co-author of *Prototyping for Architects* (Thames & Hudson, 2016), and has over a hundred other publications. Burry has practiced and taught internationally, including involvement as a project architect in the technical office at Antoni Gaudí's Sagrada Família Basilica with partner Mark Burry. She is co-curator of the 2018 International Exhibition 'Dynamics of Air'. Recent funded research explores the opportunities for leveraging digital fabrication with simulation and feedback to create better, more sensitive, human-centric spaces; and manipulating geometry and materiality of architecture to fine tune the acoustic, thermal and air flow aesthetics for higher quality environments. Other partnered research investigates rich environmental data gathering and its application to designing better urban environments.

Jenny E. Sabin

Jenny E. Sabin is an architectural designer whose work is at the forefront of a new direction for 21st century architectural practice – one that investigates the intersections of architecture and science and applies insights and theories from biology and mathematics to the design of responsive material structures and adaptive architecture. Sabin is the Arthur L. and Isabel B. Wiesenberger Professor in Architecture and Associate Dean for Design at Cornell College of Architecture, Art, and Planning where she established a new advanced research degree in Matter Design Computation. She is principal of Jenny Sabin Studio, an experimental architectural design studio based in Ithaca and Director of the Sabin Lab at Cornell AAP.

Sabin holds degrees in ceramics and interdisciplinary visual art from the University of Washington and a Master of Architecture from the University of Pennsylvania. She was awarded a Pew Fellowship in the Arts 2010 and was named a USA Knight Fellow in Architecture. In 2014, she was awarded the prestigious Architectural League Prize. Her work has been exhibited internationally including at the FRAC Centre, Cooper Hewitt Design Triennial, MoMA, and most recently as part of Imprimer Le Monde at the Centre Pompidou. Her book *LabStudio: Design Research Between Architecture and Biology*, co-authored with Peter Lloyd Jones, was published in 2017. Sabin won MoMA & MoMA PS1's Young Architects Programme with her submission, *Lumen* (2017).

Bob Sheil

Bob Sheil is Professor in Architecture and Design through Production at The Bartlett School of Architecture UCL, and has been Director of School since 2014. He is the author of multiple book chapters, refereed papers and articles on design, making and technology. He has co-designed and built six artefacts/built works, and his work has been exhibited internationally on eleven occasions. He has edited seven books, including three issues of *Architectural Design: Design through Making* (2005), *Protoarchitecture* (2008), and *High Definition: Negotiating Zero Tolerance* (2014); an AD Reader, *Manufacturing the Bespoke*, published in 2012; and *55/02: A sixteen*(makers) Monograph* (also 2012). He is a Co-Founder of the FABRICATE conference and book for which he was Co-Chair and Co-Editor in 2011 (London) and 2017 (Zurich).

Marilena Skavara

Marilena Skavara is a London-based architect and interaction designer. She is a co-founder and partner at Codica Ltd., a London-based digital product design practice focused on outcome-driven innovation. She has led and contributed to transformational projects for Mercedes Benz, UCL, M&S, HM Government and several leading start-ups in fintech, automotive, AI, health, femtech and media. She has also been involved in social impact projects for non-profits in the US, UK and EU.

Prior to that, she ran physical computing workshops for The Bartlett, UCL, the Architectural Association (AA) in London, Ecole Speciale d' Architecture in Paris, and other universities in Sweden and Denmark. Skavara is one of the founding members and editors of FABRICATE — a triennial international peer-reviewed conference and publication, which explores the progressive integration of digital design with manufacturing processes, and its impact on design and making in the 21st century. She holds a MSc (Hons) degree in Architecture from the National Technical University in Athens and a MSc (Hons) Adaptive Architecture & Computation (AAC) from The Bartlett, UCL. Her MSc graduate project 'Adaptive fa[ca]de' was extensively exhibited, published and presented at conferences and publications.

CONTRIBUTORS BIOGRAPHIES

1: BIO-MATERIALITY

MUD Frontiers

Virginia San Fratello with her partner Ronald Rael, draws, builds, 3D prints, teaches and writes about architecture as a cultural endeavour, deeply influenced by craft traditions and contemporary technologies. Through their studio, RAE SAN FRATELLO, they speculate about the social agency of design, particularly along the borderlands between the USA and Mexico. Their drawings, models and objects are in the permanent collections of the Museum of Modern Art, the Cooper Hewitt Smithsonian Design Museum, and the San Francisco Museum of Modern Art. They are founding partners of the Oakland-based make-tank Emerging Objects.

Ronald Rael, with his partner Virginia San Fratello, draws, builds, 3D prints, teaches and writes about architecture as a cultural endeavour, deeply influenced by craft traditions and contemporary technologies. Through their studio, RAE SAN FRATELLO, they speculate about the social agency of design, particularly along the borderlands between the USA and Mexico. Their drawings, models and objects are in the permanent collections of the Museum of Modern Art, the Cooper Hewitt Smithsonian Design Museum, and the San Francisco Museum of Modern Art. They are founding partners of the Oakland-based make-tank Emerging Objects.

The Design and Fabrication of Confluence Park

Andrew Kudless is a designer based in Houston, Texas where he is the Bill Kendall Memorial Endowed Professor at the University of Houston's Hines College of Architecture Design and Director of the Advanced Media Technology Lab. In 2004, he founded Matsys, a design studio exploring the emergent relationships between architecture, engineering, biology and computation. The work of Matsys has been exhibited internationally and is in the permanent collections of the San Francisco Museum of Modern Art, the Centre Pompidou in Paris, and the FRAC Centre in Orleans, France. His work on Confluence Park has won a number of awards including a 2019 AIA Honor Award.

Joshua Zabel is the Vice President of Business Development at Kreysler & Associates, a world-class composites fabrication facility in the Bay Area, San Francisco. He has been at K&A since 2005 and has filled many roles. As Director of Digital Fabrication he was involved in the digital aspects of nearly every project to pass through K&A's shop. Projects have ranged widely: architectural façades, submarine hulls, giant bat skeletons, and dark matter satellites, to name a few. He has developed an expert understanding of composites, and is at the forefront of AEC and the composites industry's efforts to maximise their architectural potential.

Chuck Naeve is Founding Principal of Architectural Engineers Collaborative. Naeve has managed structural engineering projects and business activities of engineering firms for over thirty years. He has practiced extensively in the United States, as well as internationally. Naeve is known for creating architectural structures in support of building architecture, and for developing sustainable building structures in harmony with the natural environment. Chuck Naeve has been recognised with honorary membership of the American Institute of Architects, Austin and Texas chapters, for his significant contributions to the field of architecture and to the built environment.

Tenna Florian is a Partner with LakelFlato Architects in San Antonio, Texas. She was drawn to LakelFlato because of their place-based approach to sustainable design. As a leader of

the Eco-Conservation studio at LakelFlato, her focus is on highly sustainable projects that integrate into the natural environment. Florian has been active in developing green initiatives for her firm and for the city of San Antonio. Her work includes: Naples Botanical Garden in Naples, FL; the Dixon Water Foundation Josey Pavilion in Decatur, TX – the ninth certified Living Building Challenge project in the world; and an AIA Honor Award winning project, Confluence Park.

The Role of Robotic Milling in the Research and Development of the Cork Construction Kit

Oliver Wilton is Director of Technology and Lecturer in Environmental Design at The Bartlett School of Architecture, UCL. He contributes to developing, augmenting and leading the school's strategy for technology in architecture. His research and teaching covers design, habitation, material technology, environmental and energy performance, and new forms of construction. Wilton is a director at architecture practice WW Studio. He has over two decades of experience, including involvement in a range of innovative award-winning built projects and consultancy ranging from technical assessment for the Ashden Awards to co-delivering Sustainable Urban Development consultancy to the Taiwanese government.

Matthew Barnett Howland is Director of Research and Development at CSK Architects in Eton, where he is responsible for developing a life-cycle approach to making buildings. He led on the research, design and construction of the multi-award winning Cork House, a pilot project for an innovative solid cork construction kit with outstanding whole life performance. Howland is an architectural tutor, and has taught diploma units at the Architectural Association, University of Cambridge and London Met, where he was awarded the RIBA Tutor Prize in 2004.

Peter Scully is the technical director of B-made, The Bartlett Manufacturing and Design Exchange, and Technical Director of The Bartlett's Design for Manufacture Master's programme. He has worked in bespoke manufacturing for 25 years, developing a special focus on design at the interface between disciplines, and has run companies that play a key role in the realisation of bespoke architectural and artistic works. Scully has worked with architects, engineers and artists, deploying holistic project stakeholder understanding throughout the full process to curate workflows toward buildable outcomes. He has contributed to a range of built projects internationally, utilising procedural and tacit knowledge within design.

Pulp Faction: 3D printed material assemblies through microbial biotransformation

Ana Goidea is a PhD candidate at Lund University, where she investigates the potentials of additive manufacturing in architecture through computational design. She received her Master's of Architecture from CITAstudio at The Royal Danish Academy of Fine Arts, after which she has been teaching and working at studios with different strategies for digital fabrication. Her research combined with industry through the design and co-fabrication of one of the first 3D-printed buildings in Europe. Her interests are at the intersection between living systems, complex geometries and material performance, currently manifested through a project on bio-hybrid materials for 3D printing.

Dimitrios Floudas is a researcher at the Biology Department of Lund University. He is a fungal biologist who received his doctorate in evolutionary biology and systematics of fungi at Clark University, Massachusetts. His research interests