



# LUND UNIVERSITY

## Imaginable effects of limestone filler on chloride transport

Fagerlund, Göran

2005

[Link to publication](#)

*Citation for published version (APA):*

Fagerlund, G. (2005). *Imaginable effects of limestone filler on chloride transport*. (Report TVBM (Intern 7000-rapport); Vol. 7187). Division of Building Materials, LTH, Lund University.

*Total number of authors:*

1

### General rights

Unless other specific re-use rights are stated the following general rights apply:

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

Read more about Creative commons licenses: <https://creativecommons.org/licenses/>

### Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

LUND UNIVERSITY

PO Box 117  
221 00 Lund  
+46 46-222 00 00



LUND INSTITUTE OF TECHNOLOGY  
LUND UNIVERSITY

---

Division of Building Materials

IMAGINABLE EFFECTS  
OF LIMESTONE FILLER ON  
CHLORIDE TRANSPORT

Göran Fagerlund

Report TVBM-7187

---

Lund, May 2005

# Contents

	Page
List of symbols	2
1. Introduction and summary	3
2. The chloride diffusion coefficient	6
2.1 Without chloride binding	6
2.2 With chloride binding	6
3. Bound and free chloride	8
3.1 Introduction	8
3.2 Linear relation	8
3.3 Non-linear relations	10
3.4 Conclusions concerning binding of chloride	15
4. Limestone filler in concrete – possible effects on chloride penetration	17
5. Experimental methods for determination of the effect of limestone filler on chloride diffusion and binding	19
5.1 Introduction	19
5.2 The “steady state” diffusion coefficient	19
5.3 Chloride binding	20
6. Conclusions	24
References	25
 ANNEX 1: Chloride binding as function of the water-cement ratio and age	 27
 ANNEX 2: Effective chloride diffusion coefficient as function of the water-cement ratio and age	 33
 ANNEX 3 Evaluation of a diffusion cell test	 43
 ANNEX 4 Determination of the “active” porosity for dissolving chloride	 47

## List of symbols

C	Cement content in mix (kg per m <sup>3</sup> of concrete)
C'	Cement content (g per cm <sup>3</sup> of concrete) (Note: C'=10 <sup>-3</sup> ·C)
F	Amount of limestone filler (kg per m <sup>3</sup> of concrete)
K	Steady state chloride diffusion coefficient at 100% porosity (m <sup>2</sup> /s)
P <sub>cap</sub>	Capillary porosity (m <sup>3</sup> per m <sup>3</sup> concrete or cement paste)
P <sub>tot</sub>	Total porosity (m <sup>3</sup> per m <sup>3</sup> concrete or cement paste)
P <sub>w</sub>	Water-filled porosity (m <sup>3</sup> per m <sup>3</sup> concrete or cement paste)
Q <sub>bound</sub>	Amount of bound chloride in a specimen (g)
Q <sub>C</sub>	Cement content in a specimen (g)
Q <sub>free</sub>	Amount of free chloride in a specimen (g)
Q <sub>gel</sub>	Amount of hydration products ("cement gel") (kg per m <sup>3</sup> concrete)
Q <sub>gel</sub> '	Amount of hydration products ("cement gel") in a specimen (g)
Q <sub>tot</sub>	Total chloride in a specimen (g)
R	Ratio between bound and free chloride defined by R=c <sub>b</sub> /c (-). Note: R≠c' <sub>b</sub> /c'.
W	Water Content in fresh mix (kg per m <sup>3</sup> of concrete)
W <sub>p</sub>	Total amount of pore water (m <sup>3</sup> per m <sup>3</sup> of concrete)
W <sub>p,cap</sub>	Amount of capillary pore water (m <sup>3</sup> per m <sup>3</sup> of concrete)
W <sub>w</sub>	Amount of pore water dissolving chloride (m <sup>3</sup> per m <sup>3</sup> of concrete)
V	Specimen volume (m <sup>3</sup> )
c	Concentration of free chloride in concrete or in a bath surrounding a specimen (kg per m <sup>3</sup> water)
c'	Amount of free chloride (kg per m <sup>3</sup> of concrete)
c''	Concentration of free chloride (g per litre pore water). (Note: c''=c)
c'''	Concentration of free chloride (g per cm <sup>3</sup> pore water). (Note: c'''=10 <sup>-3</sup> ·c)
c <sub>b</sub>	Amount of chloride extracted from pore water by chemical and physical binding to the solid material (kg per m <sup>3</sup> pore water)
c <sub>b</sub> '	Amount of bound chloride (kg per m <sup>3</sup> of concrete)
c <sub>b</sub> ''	Amount of bound chloride (mg per g cement). (Note: c <sub>b</sub> ''=10 <sup>3</sup> ·c <sub>b</sub> '/C)
c <sub>b,gel</sub>	Amount of bound chloride in the cement gel (g per g gel, or kg per kg gel)
c <sub>tot</sub> '	Sum of bound and free chloride –total chloride (kg per m <sup>3</sup> of concrete)
c <sub>tot,s</sub> '	Total chloride at the exposed surface (kg per m <sup>3</sup> of concrete)
k	Efficiency factor of limestone filler (-)
q	Flow of chloride ions (kg per m <sup>2</sup> )
r	Ratio between filler and cement (-)
t	time (s)
vbt <sub>C</sub>	Water-binder ratio with only cement in the mix (-)
vbt <sub>F</sub>	Water-binder ratio with filler in the mix (-)
w <sub>w</sub>	Amount of water dissolving chloride in a specimen (g=cm <sup>3</sup> )
w <sub>w,cap</sub>	Amount of capillary water in a specimen (g=cm <sup>3</sup> )
w <sub>w,tot</sub>	Total amount of water in a saturated specimen (g=cm <sup>3</sup> )
x	Distance from chloride exposed surface (m)
α	Degree of hydration (-)
γ	Coefficient describing amount of pore water dissolving chloride- equation (17) (-)
δ <sub>0</sub>	Diffusion coefficient of chloride ions with no binding "steady state" diffusion coefficient (m <sup>2</sup> /s)
δ <sub>eff</sub>	Effective diffusion coefficient of chloride (m <sup>2</sup> /s)

# 1 Introduction and summary

There is some experimental evidence that the addition of limestone filler to concrete with unchanged water-cement ratio might increase the chloride ingress in concrete; e.g. Persson (2001) and Boubitsas (2005). This means that the filler has, what can be called, a negative “efficiency factor” with regard to chloride uptake, in contrast to other reactive fillers (mineral admixtures) such as fly ash and ground granulated blastfurnace slag. This negative effect might occur also when limestone filler is used in self-compacting concrete, Persson (2001).

The efficiency factor of a mineral admixture, like filler, with regard to chloride diffusivity expresses the amount of ordinary cement that can be replaced by a given amount of filler at unchanged diffusivity. In case of limestone filler no cement can be replaced. On the contrary, *more cement has to be added in order to maintain the same resistance to chloride uptake.*

The definition and calculation of the efficiency factor is illustrated by Figure 1.  $\delta_{\text{eff}}$  is the effective diffusion coefficient, see equation (4).

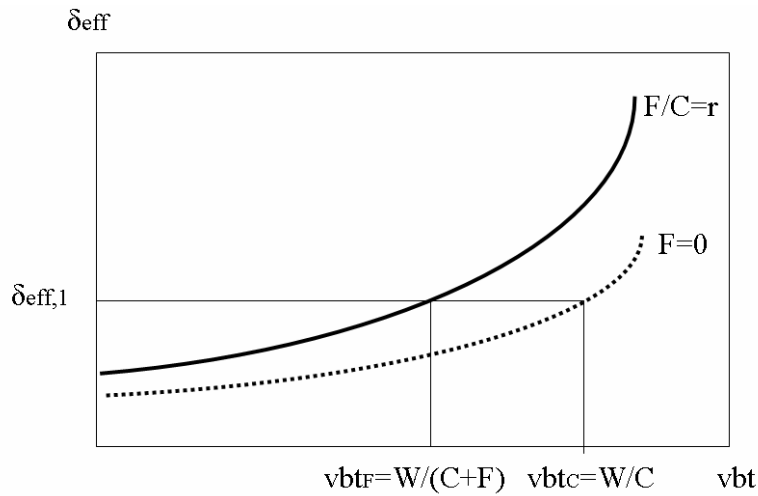


Figure 1: Illustration of the efficiency factor.

With filler the water-binder ratio for a given diffusivity is:  $vbt_F = W/(C+F) = W/C(1+r)$

Without filler the required water-cement ratio for the same diffusivity is:  $vbt_C = W/C$

The same effective diffusion coefficient as for concrete with pure cement is also obtained for the concrete with filler if an effective water-binder ratio is used:  $vbt_{F,\text{eff}} = W/C(1+k \cdot r)$ .

Where  $k$  is the *efficiency factor*. This is obtained by combination of the expressions above:

$vbt_F = W_1/[C_1(1+r)]$  where  $W_1$  and  $C_1$  are the water content and cement content in concrete with filler. Thus  $W_1/C_1 = vbt_F(1+r)$ .

By definition,  $vbt_{F,\text{eff}} = W_1/C_1(1+k \cdot r) = vbt_C$ . Inserting  $W_1/C_1 = vbt_F(1+r)$  and redistributing the terms gives:

$$k = [\text{vbt}_f(1+r) - \text{vbt}_c] / \text{vbt}_c \cdot r \quad (1)$$

**Example 1**

For a given chloride diffusivity a water-cement ratio  $\text{vbt}_c = 0.4$  is needed when there is no filler in the concrete.

For the same chloride diffusivity a water-binder ratio  $\text{vbt}_f = 0.3$  is needed when the concrete contains 20% filler ( $r = 0.20$ ).

The efficiency factor becomes:  $k = [0.3(1+0.20) - 0.4] / 0.4 \cdot 0.20 = -0.50$

The negative efficiency factor means that more cement is needed for maintaining the same chloride diffusivity.

**Example 2**

The same as Example 1.

The efficiency factor -0.50 can be used for calculating the extra cement.

The amount of mixing water is assumed to be  $170 \text{ l/m}^3$ .

Cement content with no filler:  $C_0 = 170 / 0.4 = 425 \text{ kg/m}^3$

Cement content with 20% filler (provided filler does not change the required water content for constant workability):

$C_1 = 170 / [0.4(1 - 0.5 \cdot 0.2)] = 472 \text{ kg/m}^3$

In the report a discussion is carried out on factors determining chloride ingress in concrete and on possible effects of limestone filler on these factors.

**In paragraph 2**, the difference between the “steady state” chloride diffusion coefficient and the effective chloride diffusion coefficient is pointed out. The relation between the two coefficients is described by the ratio R between the bound chloride, which is extracted from the pore solution, and the free chloride, which is remaining in the pore solution; equation (3).

**In paragraph 3**, a limited literature review of the relation between bound and free chloride is performed. Some measurements indicate that there is a linear relationship, other measurements that the relationship is non-linear. In both cases it is found that the relation is a function of the water-cement ratio; the higher the w/c-ratio, the lower the fraction of bound chloride. Furthermore, some results indicate that the fraction of bound chloride decreases with increased alkalinity of the pore solution.

Experiments indicate, quite reasonably, that the fraction of bound chloride is directly proportional to the amount of hydration products.

Theoretical analyses of the effect of water-cement ratio and concrete age on chloride binding and transport, using the linear relation between bound chloride and amount of hydration products, are carried out in **ANNEX 1** and **ANNEX 2**.

In ANNEX 1 it is shown that the coefficient R describing chloride binding decreases with increased w/c-ratio and increases with increased degree of hydration.

In ANNEX 2 it is shown theoretically that the effective coefficient of chloride diffusion increases linearly with increasing w/c-ratio. This is in accordance with experiments.

**In paragraph 4**, a hypothesis is put forward that the negative effect of limestone filler might depend on a reduced chloride binding capacity caused by reaction between the filler and chloride-binding components in the cement, mainly  $C_3A$ .

An additional explanation could be that the filler causes increased “steady state” chloride permeability due to structural changes of the cement paste. This explanation is less probable, however, since the main reaction products determining the pore structure are the calcium silicates, and the reaction products of these are hardly affected by limestone filler.

**In paragraph 5**, methods for investigating mechanisms behind the effect of limestone filler on chloride transport are suggested. The effect on the basic properties *steady state diffusion coefficient* (denoted  $\delta_0$  in equation (2)) and *chloride binding capacity* (denoted  $R=c_b/c$  in equation (4)) should be investigated. Suggestions for test methods are given. Evaluation techniques are presented in ANNEX 3 and ANNEX 4.

## 2 The chloride diffusion coefficient

### 2.1 Without chloride binding

Uni-directional transport of chloride ions into the pore space of a concrete specimen stored in a solution containing chloride ions is in the simplest way described by (Fick's second law):

$$dq/dt = \delta_0 \cdot d^2c/dx^2 \quad (2)$$

where  $q$  is the ion flow in one square-meter of concrete ( $\text{kg}/\text{m}^2$ ),  $\delta_0$  is the diffusion coefficient ( $\text{m}^2/\text{s}$ ),  $c$  is the chloride concentration in the pore water ( $\text{kg}$  per  $\text{m}^3$  pore water),  $x$  is the coordinate along the flow axis ( $\text{m}$ ).

This equation is based on the assumption that there is no chemical or physical binding of chloride ions. The diffusion coefficient  $\delta_0$  can be determined in a steady state test in which a thin slice of the concrete is placed as a partition wall between two chambers; one, initially containing a chloride-free solution, and the other containing a solution with chloride; see Figure 8. The chloride transport rate is evaluated from frequent chloride analyses of the liquid in the two chambers. The transport coefficient is obtained when steady state flow has been reached.

### 2.2 With chloride binding

A certain fraction of chloride ions is bound in concrete, mostly chemically in the hydration products, but also physically to the pore walls. As a first approximation it is assumed that binding is linear, i.e. the amount of chloride extracted from the pore water,  $c_b$ , by binding ( $\text{kg}$  per  $\text{m}^3$  pore water) is directly proportional to the amount of free chloride left to migrate in the pore water,  $c$  ( $\text{kg}$  per  $\text{m}^3$  pore water):

$$c_b = R \cdot c \quad (3)$$

where  $R$  is the proportionality coefficient (-).

*Note:*  $R$  is a *dimensionless* entity, since the bound chloride is expressed in terms of chloride extracted from the pore solution. Thus, in order to calculate  $R$  the chloride in the pore solution must be re-calculated to the same unit as the bound chloride, e.g.  $\text{kg}/\text{m}^3$  of concrete, or the bound chloride must be re-calculated to the same unit as the free chloride, e.g.  $\text{kg}/\text{m}^3$  of pore solution. In both cases, this means that the volume of pore solution must be known.

Chloride transport can now be formulated:

$$dq/dt = \delta_0 \cdot d^2c/dx^2 - dc_b/dt \quad (4)$$

Inserting eq (3) gives:

$$dq/dt = [\delta_0/(R+1)] \cdot d^2c/dx^2 = \delta_{\text{eff}} \cdot d^2c/dx^2 \quad (5)$$

Where  $\delta_{\text{eff}} = \delta_0/(R+1)$  is an *effective diffusion coefficient* valid under non-steady state conditions ( $\text{m}^2/\text{s}$ ).

The effective diffusion coefficient  $\delta_{\text{eff}}$  can be calculated from the measured *profile of total chloride*  $c_{\text{tot}}'$  (the sum of free and bound chloride) reached in a specimen after a known exposure time in a chloride solution with constant concentration. The solution to equation (5) is used with the free concentration  $c$  exchanged for the total concentration  $c_{\text{tot}}'$ .

$$c_{\text{tot}}'/c_{\text{tot},s}' = 1 - \text{erf}[x/(4 \cdot \delta_{\text{eff}} \cdot t)^{1/2}] \quad (6)$$

where  $c_{\text{tot}}'$  is the measured total amount of chloride (kg per m<sup>3</sup> concrete -or kg per kg concrete, or kg per kg cement) on the distance  $x$  (m) from the surface after the exposure time  $t$  (s).  $c_{\text{tot},s}'$  is the total amount of chloride at the surface part of concrete. erf is the “error function”. A table over the error function can be found in Crank (1985).

Since the surface amount of chloride is impossible to determine experimentally, one can instead use the measured concentration  $c_{\text{tot},1}'$  and  $c_{\text{tot},2}'$  on two different depths,  $x_1$  and  $x_2$ . From the two measurements both the value of  $c_{\text{tot},s}'$  (a fictitious value) and  $\delta_{\text{eff}}$  can be evaluated. By using many interlinked values  $c_{\text{tot},i}'$  and  $x_i$  a more accurate value of  $\delta_{\text{eff}}$  is of course obtained.

The *profile of free chloride*  $c'$  (kg per m<sup>3</sup> concrete) can be calculated from the profile of the total chloride by using equation (3) expressed as:

$$c' = c_{\text{tot}}' - c_b' = c_{\text{tot}}' / (1 + R) \quad (7)$$

Thus, in order to obtain the profile of free chloride, expressed in terms of kg per m<sup>3</sup> of concrete,  $c'$ , the bound total chloride profile is divided by a constant factor  $(1 + R)$ .

For obtaining the concentration of free chloride in the pore water  $c$  (kg per m<sup>3</sup> pore water),  $c'$  is divided by the amount of pore water dissolving chloride,  $W_w$  (m<sup>3</sup> per m<sup>3</sup> of concrete):

$$c = c' / W_w \quad (8)$$

*Note:* In reality the relation between free and bound chloride is not always linear; see next paragraph. This means that equations (4) to (6) do not give a correct description of chloride transport. Chloride transport with non-linear chloride binding is treated in Tang (1996).

### 3 Bound and free chloride

#### 3.1 Introduction

The relation between free and bound chloride is not very well known. One of the first to make experimental determinations of the relation was Tuutti (1982). He used so called pore pressing to analyse the free chloride content, and chemical analysis for determination of the total chloride content. The relations between free and bound chloride he found were linear; Figure 2 and 3. Linear relations have also been obtained in research by Arya & Newman (1990).

In other investigations, non-linear binding has been observed, Sandberg & Larsson (1993), Tang & Nilsson (1993); Figures 4 and 5. These measurements were made with another technique in which the material was stored for so long time in chloride solution that there was equilibrium between the chloride concentration in the pores and the outer solution, see Figure 9. Analysis of the total chloride content and pore volume made it possible to calculate both free and bound chloride.

Some examples of relations between free and bound chloride are given below.

#### 3.2 Linear relation

Examples of linear relations between bound and free chloride are shown in Figure 2 and 3; Tuutti (1982). The cement is a high alkali OPC with about 8%  $C_3A$ .

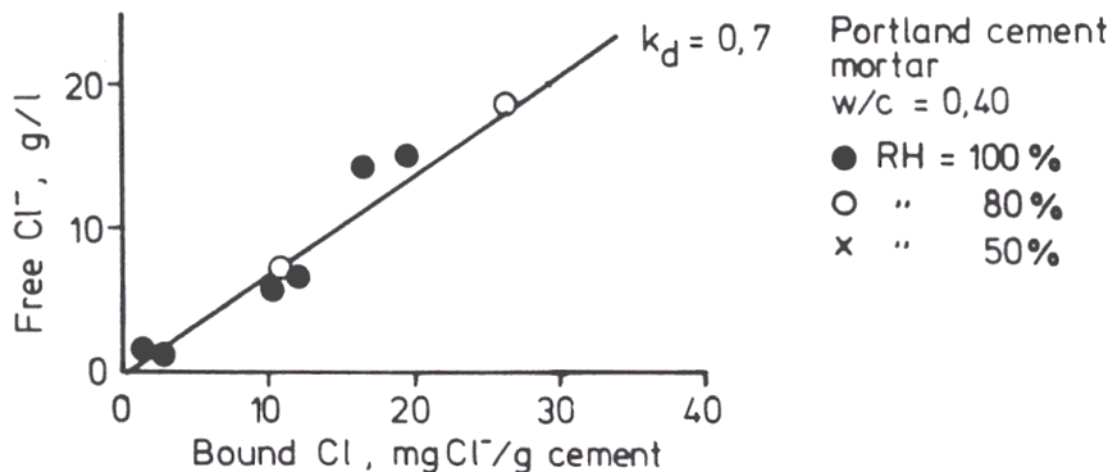


Figure 2: Relation between free ( $c''$ ), and bound ( $c_b''$ ) chloride.  $w/c$  0.4. Tuutti (1982). Specimens pre-conditioned to different RH.

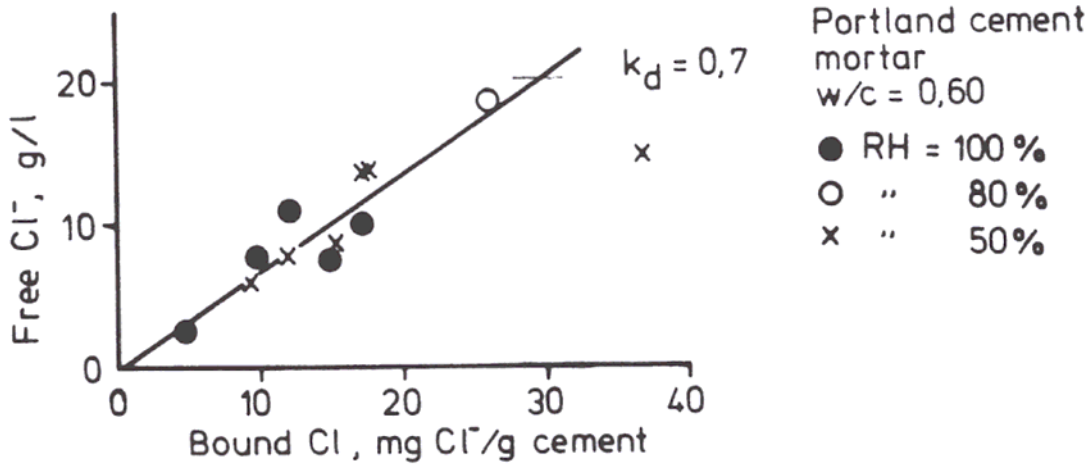


Figure 3: Relation between free ( $c''$ ) and bound ( $c_b''$ ) chloride. w/c 0.6. Tuutti (1982).

In the figures above, free chloride  $c''$  is expressed in the unit gram per litre pore water. But  $c''$  (g/litre) =  $c$  (kg/m<sup>3</sup>).

Bound chloride  $c_b''$  is in the figures expressed in the unit mg per g cement. The total bound chloride in 1 m<sup>3</sup> of concrete,  $c_b'$  (kg per m<sup>3</sup> concrete) is:

$$c_b' = c_b'' \cdot 10^{-3} \cdot C \quad (9)$$

Where  $C$  is the cement content (kg per m<sup>3</sup> concrete). The total pore water volume in 1 m<sup>3</sup> of saturated OPC concrete  $W_p$  (m<sup>3</sup> pore water per m<sup>3</sup> concrete) is:

$$W_p = C(W/C - 0.19\alpha) / 1000 \quad (10)$$

Where  $\alpha$  is the degree of hydration and 1000 is the density of water (kg/m<sup>3</sup>). Thus, the amount of chloride extracted from the pore water by adsorption or chemical binding,  $c_b$  (kg chloride per m<sup>3</sup> pore water), to be used in equation (4) is (provided all pore water is able to dissolve chloride to the same extent, i.e. that all pore water is active in chloride transport):

$$c_b = c_b' / W_p = c_b'' \cdot 1000 / (W/C - 0.19\alpha) \quad (11)$$

The coefficient  $R$  in equation (3) and (4) becomes:

$$R = c_b / c = (c_b'' / c) / (W/C - 0.19\alpha) \quad (12)$$

Since binding is linear the value of  $R$  is independent of the total amount of chloride. The following examples give the value of  $R$  for the materials in Figure 2 and 3.

**Example 3:** Figure 2:  $W/C=0.40$ ,  $\alpha=0.6$ :  
 $c \approx 20$  g/l = 20 kg/m<sup>3</sup> when  $c_b'' = 30$  mg/g cement.

$$R = (30/20) / (0.4 - 0.19 \cdot 0.6) = 5.2$$

**Example 4:** Figure 3:  $W/C=0.60$ ,  $\alpha=0.8$ :

$c \approx 20$  g/l when  $c_b' = 30$  mg/g cement.

$$R = (30/20) / (0.60 - 0.19 \cdot 0.8) = 3.4$$

As said above, these values are based on analysis of pore water forced out of the concrete by so-called pore pressing. The higher relative value of bound chloride in the specimen with w/c-ratio 0.40 might to a certain extent depend on that it was not possible to “squeeze out” all free water in this dense cement paste. A higher chloride binding in concrete with lower w/c-ratio is not unexpected, however, since the amount of hydration products is higher while the amount of pore water is smaller; see examples 6,8 and 9 below.

The cement in Figures 2 and 3 has the following composition of components influencing chloride binding.

- C<sub>3</sub>A: 8 %
- C<sub>4</sub>AF: 7 %
- Na<sub>2</sub>Oeq: 1.1 %
- Limestone filler: 5 %

### 3.3 Non-linear relations

As said above, some researchers have found a non-linear relation between free and bound chloride. Examples are given in Figure 4 and 5.

#### A: Chloride binding as function of the amount of cement gel; Figure 4

An example of *non-linear* chloride binding is shown in Figure 4; Tang & Nilsson (1993). The cement is almost the same as in Figure 2 and 3. The bound chloride is expressed in terms of *mg per g cement gel*, and the free chloride in terms of *concentration in pore water*. The chloride binding curve, expressed in these units, turns out to be independent of the water-cement ratio, which is very reasonable since it is only cement gel (hydration products) that is capable of binding chloride physically and chemically; i.e. the higher the amount of cement gel, the higher is the capacity to bind chloride.

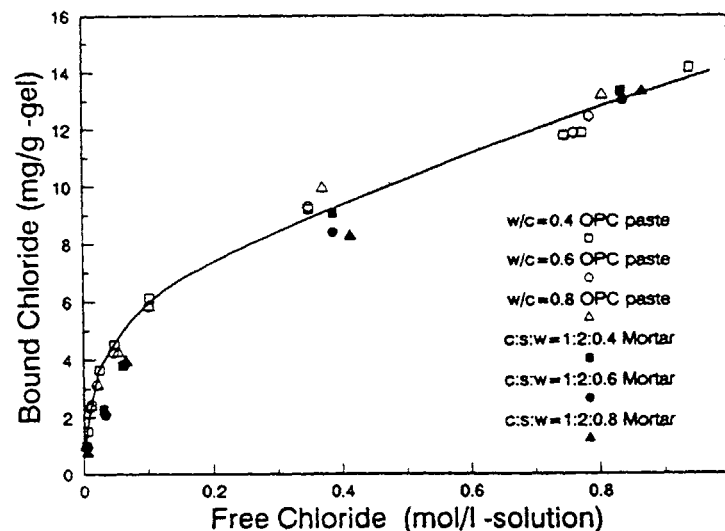


Figure 4: Relation between free and bound chloride; Tang & Nilsson (1993).

The weight of cement gel,  $Q_{gel}$  (kg per  $m^3$  concrete, mortar or cement paste) in OPC concrete is:

$$Q_{gel} = 1.25 \cdot \alpha \cdot C \quad (13)$$

Where  $\alpha$  is the degree of hydration, and  $C$  is the cement content (kg per  $m^3$  concrete).

*Note:* This equation assumes that all hydration products are included in the “gel”, also products created by  $C_3A$  and  $C_4AF$ . Moreover, calcium hydroxide formed is included in the concept “gel”. Thus, weight of “gel” is the same as weight of all hydration products. It must also be observed that the equation (13) is only supposed to be valid for OPC. Other cements, or addition of limestone filler, might change the amount of hydration products.

The higher the amount of free chloride the lower is the fraction of bound chloride. The relation between free and bound chloride is illustrated by some examples. In all examples it is assumed that *all pore water dissolves chloride to the same extent*. Furthermore, it is assumed that all pore water (also gel water) acts as transport medium for chloride diffusion. If not, the fraction of bound chloride will be increased and so will the value of  $R$ ; see paragraph 5.2.

#### Examples 5-7: $w/c=0.4$ ( $\alpha=0.6$ )

##### **Example 5**

Bound chloride: 6 mg/g cement gel

Weight of cement gel:  $Q_{gel} = 1.25 \cdot 0.6 \cdot C = 0.75C$  kg/ $m^3$  cement paste

Thus, bound chloride is  $6 \cdot 10^{-3} \cdot 0.75C = 4.5 \cdot 10^{-3}C$  kg bound chloride per  $m^3$  cement paste

The pore water volume is  $W_p = C(0.4 - 0.19 \cdot 0.6) / 1000$   $m^3$  per  $m^3$  cement paste =  $2.86 \cdot 10^{-4}C$   $m^3/m^3$  cement paste

Thus, bound chloride is  $c_b = 4.5 \cdot 10^{-3}C / 2.86 \cdot 10^{-4}C = 15.7$  kg per  $m^3$  pore water

Free chloride is 0.1 mole/l =  $c = 3.55$  kg per  $m^3$  pore water

The relation between bound and free chloride is  $R = c_b/c = 15.7/3.55 = 4.4$

##### **Example 6**

Bound chloride: 10 mg/g cement gel

Weight of cement gel is the same as in Example 5;  $0.75C$  kg/ $m^3$  cement paste

Thus, bound chloride is  $10 \cdot 10^{-3} \cdot 0.75C = 7.5 \cdot 10^{-3}C$  kg bound chloride per  $m^3$  cement paste

The pore water volume is the same as in Example 5;  $2.86 \cdot 10^{-4}C$   $m^3/m^3$  paste

Thus, bound chloride is  $c_b = 7.5 \cdot 10^{-3}C / 2.86 \cdot 10^{-4}C = 26.2$  kg per  $m^3$  pore water

Free chloride is 0.5 mole/l =  $c = 17.8$  kg per  $m^3$  pore water

The relation between bound and free chloride is  $R = c_b/c = 26.2/17.8 = 1.5$

**Example 7**

Bound chloride: 14 mg/g cement gel

Weight of cement gel is the same as in Example 5;  $0.75C \text{ kg/m}^3$  cement paste

Thus, bound chloride is  $14 \cdot 10^{-3} \cdot 0.75C = 10.5 \cdot 10^{-3}C$  kg bound chloride per  $\text{m}^3$  cement paste

The pore water volume is the same as in Example 5;  $2.86 \cdot 10^{-4}C \text{ m}^3/\text{m}^3$  paste

Thus, bound chloride is  $c_b = 10.5 \cdot 10^{-3}C / 2.86 \cdot 10^{-4}C = 36.7$  kg per  $\text{m}^3$  pore water

Free chloride is 0.95 mole/l =  $c = 33.7$  kg per  $\text{m}^3$  pore water

The relation between bound and free chloride is  $R = c_b/c = 36.7/33.7 = 1.1$

**Example 8:  $w/c = 0.6$  ( $\alpha = 0.75$ )****Example 8**

Bound chloride: 10 mg/g cement gel

The weight of cement gel is,  $Q_{\text{gel}} = 1.25 \cdot 0.75 \cdot C = 0.94C \text{ kg/m}^3$  cement paste

Thus, bound chloride is  $10 \cdot 10^{-3} \cdot 0.94C = 9.4 \cdot 10^{-3}C$  kg bound chloride per  $\text{m}^3$  cement paste

The pore water volume is  $W_p = C(0.6 - 0.19 \cdot 0.75) / 1000 \text{ m}^3$  per  $\text{m}^3$  cement

paste =  $4.58 \cdot 10^{-4}C \text{ m}^3/\text{m}^3$  cement paste

Thus, bound chloride is  $9.4 \cdot 10^{-3}C / 4.58 \cdot 10^{-4}C = c_b = 20.5$  kg per  $\text{m}^3$  pore water

Free chloride is 0.5 mole/l =  $c = 17.8$  kg per  $\text{m}^3$  pore water

The relation between bound and free chloride is  $R = c_b/c = 20.5/17.8 = 1.2$

**Example 9:  $w/c = 0.8$  ( $\alpha = 0.8$ )****Example 9**

Bound chloride: 10 mg/g cement gel

The weight of cement gel is,  $Q_{\text{gel}} = 1.25 \cdot 0.8 \cdot C = 1.0C \text{ kg/m}^3$  cement paste

Thus, bound chloride is  $10 \cdot 10^{-3} \cdot 1.0C = 10 \cdot 10^{-3}C$  kg bound chloride per  $\text{m}^3$  cement paste

The pore water volume is  $W_p = C(0.8 - 0.19 \cdot 0.8) / 1000 \text{ m}^3$  per  $\text{m}^3$  cement

paste =  $6.48 \cdot 10^{-4}C \text{ m}^3/\text{m}^3$  cement paste

Thus, bound chloride is  $10 \cdot 10^{-3}C / 6.48 \cdot 10^{-4}C = c_b = 15.4$  kg per  $\text{m}^3$  pore water

Free chloride is 0.5 mole/l =  $c = 17.8$  kg per  $\text{m}^3$  pore water

The relation between bound and free chloride is  $R = c_b/c = 15.4/17.8 = 0.9$

A comparison between Examples 8, 9 and 6 shows that the relation between free and bound chloride, as defined by the coefficient  $R$ , depends on the water-cement ratio. The reason is that the amount of pore water is dependent on the  $w/c$ -ratio. A similar effect of water-cement ratio was observed in Examples 3 and 4.

**B: Chloride binding as function of the alkalinity of the pore water; Figure 5**

Figure 5 shows that the amount of bound chloride is reduced when the alkalinity of the pore water is increased by adding extra hydroxide.

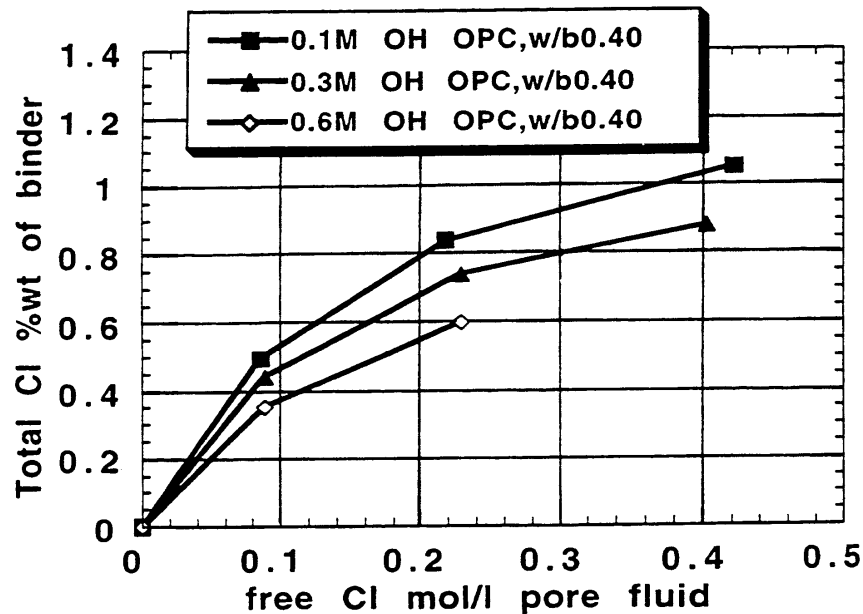


Figure 5: Relation between free and total chloride as function of the OH-ion concentration of the pore water; Sandberg & Larsson (1993). w/c-ratio=0.40.

The relation between free and bound chloride as function of alkalinity and chloride concentration are shown by some examples. The degree of hydration is supposed to be 0.6 in all examples.

**Examples 10 - 12; OH-concentration 0.3 mole/litre**

**Example 10: Total chloride:  $0.004 \cdot C$  kg per  $m^3$  concrete.**  
 Free chloride is  $0.08$  mole/l =  $2.8$  g per litre pore water =  $c = 2.8$  kg per  $m^3$  pore water (figure 5).  
 The pore water volume is  $W_p = C(0.4 - 0.19 \cdot 0.6) / 1000$   $m^3$  per  $m^3$  concrete =  $= 2.86 \cdot 10^{-4} C$   $m^3 / m^3$  concrete  
 Thus, the free chloride is  $2.8 \cdot 2.86 \cdot 10^{-4} C$  kg per  $m^3$  concrete =  $8 \cdot 10^{-4} C$  kg per  $m^3$  concrete  
 Bound chloride is  $0.004C - 0.0008C = 0.0032C$  kg per  $m^3$  concrete  
  
 The relation between bound and free chloride is  $R = c_b / c = 0.0032 / 0.0008 = 4$

**Example 11: Total chloride:  $0.006 \cdot C$  kg per  $m^3$  concrete.**

Free chloride is  $0.16 \text{ mole/l} = 5.7 \text{ g per litre pore water} = 5.7 \text{ kg per } m^3 \text{ pore water}$ .

The pore water volume is  $2.86 \cdot 10^{-4} C \text{ m}^3/\text{m}^3 \text{ concrete}$  (same as Example 10)

Thus, the free chloride is  $5.7 \cdot 2.86 \cdot 10^{-4} C \text{ kg per } m^3 \text{ concrete} = 1.6 \cdot 10^{-3} C \text{ kg per } m^3 \text{ concrete}$

Bound chloride is  $0.006C - 0.0016C = 0.0044C$

The relation between bound and free chloride is  $R = c_b/c = 0.0044/0.0016 = 2.8$

**Example 12: Total chloride:  $0.01 \cdot C$  kg per  $m^3$  concrete.**

Free chloride is  $0.36 \text{ mole/l} = 12.8 \text{ g per litre pore water} = 12.8 \text{ kg per } m^3 \text{ pore water}$ .

The pore water volume is  $2.86 \cdot 10^{-4} C \text{ m}^3/\text{m}^3 \text{ concrete}$  (same as Example 10)

Thus, the free chloride is  $12.8 \cdot 2.86 \cdot 10^{-4} C \text{ kg per } m^3 \text{ concrete} = 3.7 \cdot 10^{-3} C \text{ kg per } m^3 \text{ concrete}$

Bound chloride is  $0.008C - 0.0037C = 0.0043C$

The relation between bound and free chloride is  $R = c_b/c = 0.0043/0.0037 = 1.2$

### **Example 13; OH-concentration 0.1 mole/litre**

**Example 13: Total chloride:  $0.006 \cdot C$  kg per  $m^3$  concrete.**

Free chloride is  $0.13 \text{ mole/l} = 4.6 \text{ g per litre pore water} = 4.6 \text{ kg per } m^3 \text{ pore water}$ .

The pore water volume is  $2.86 \cdot 10^{-4} C \text{ m}^3/\text{m}^3 \text{ concrete}$  (same as Example 10)

Thus, the free chloride is  $4.6 \cdot 2.86 \cdot 10^{-4} C \text{ kg per } m^3 \text{ concrete} = 1.3 \cdot 10^{-3} C \text{ kg per } m^3 \text{ concrete}$

Bound chloride is  $0.006C - 0.0013C = 0.0047C$

The relation between bound and free chloride is  $R = c_b/c = 0.0047/0.0013 = 3.6$

### **Example 14; OH-concentration 0.6 mole/litre**

**Example 14: Total chloride:  $0.006 \cdot C$  kg per  $m^3$  concrete.**

Free chloride is  $0.24 \text{ mole/l} = 8.5 \text{ g per litre pore water} = 8.5 \text{ kg per } m^3 \text{ pore water}$ .

The pore water volume is  $2.86 \cdot 10^{-4} C \text{ m}^3/\text{m}^3 \text{ concrete}$  (same as Example 10)

Thus, the free chloride is  $8.5 \cdot 2.86 \cdot 10^{-4} C \text{ kg per } m^3 \text{ concrete} = 2.4 \cdot 10^{-3} C \text{ kg per } m^3 \text{ concrete}$

Bound chloride is  $0.006C - 0.0024C = 0.0036C$

The relation between bound and free chloride is  $R = c_b/c = 0.0036/0.0024 = 1.5$

A comparison between examples 11, 13 and 14 shows that the amount of bound chloride is highly dependent on the alkalinity of the pore water; the higher the alkalinity the lower the fraction of bound chloride.

The fraction of bound chloride, especially at high total chloride content, is considerably lower for the concrete in Figure 5 than for the concretes in Figures 2 and 3.

One reason could be the different composition of the cements used. The cement in Figure 5 has the following composition of components influencing chloride binding.

- C<sub>3</sub>A: 1.4 %
- C<sub>4</sub>AF: 14 %
- Na<sub>2</sub>O<sub>eq</sub>: 0.5 %
- Limestone filler: 0 %

Particularly the component C<sub>3</sub>A is considerably lower than for the cement in Figure 2, 3 and 4.

### 3.4 Conclusions concerning binding of chloride

The calculations made above, concerning the relation between bound and free chloride when this is expressed by the coefficient R, show that it is not possible to find any value of R that can be universally applied. See Figure 6 where all data from Examples 3-9 are collected.

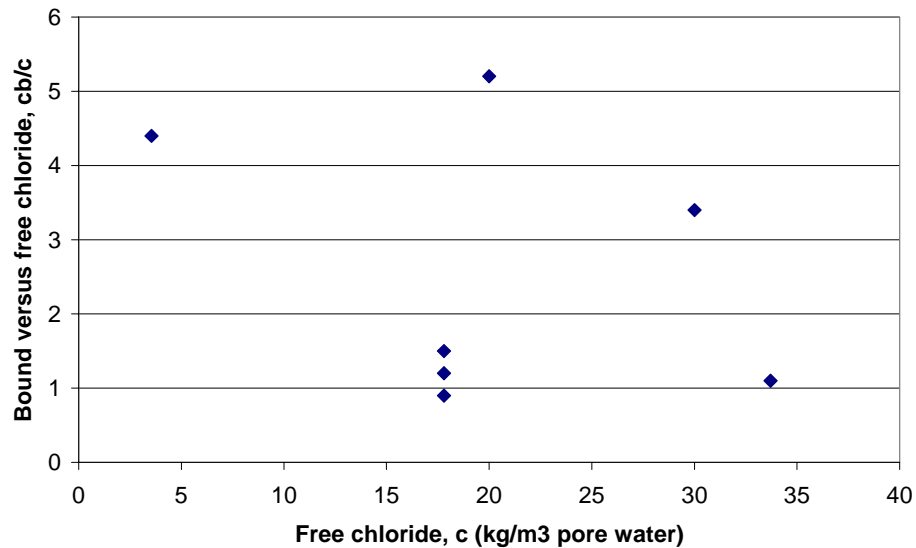


Figure 6: Relation between the free ( $c$ ) and bound chloride ( $c_b$ ). Data from Examples 3-9.

The best approach to describe bound chloride seems to be that used in Figure 4 where bound chloride is related to the amount of cement gel (hydration products). It is quite clear, however, that such a relation depends very much on the chemical composition of the cement, especially its contents of aluminates and alkali hydroxide. It is also probable that the use of partly reactive fillers such as limestone will have an effect on the binding capacity.

The examples indicate clearly that the relation between bound and free chloride as defined by coefficient R (kg per m<sup>3</sup> pore solution) is decreased with increased w/c-ratio. This is a direct consequence of the fact that binding is proportional to the amount of hydration products, while the free chloride is proportional to the amount of pore water. A plot of all data for bound chloride versus the w/c-ratio from Examples 3-9 are made in Figure 7.

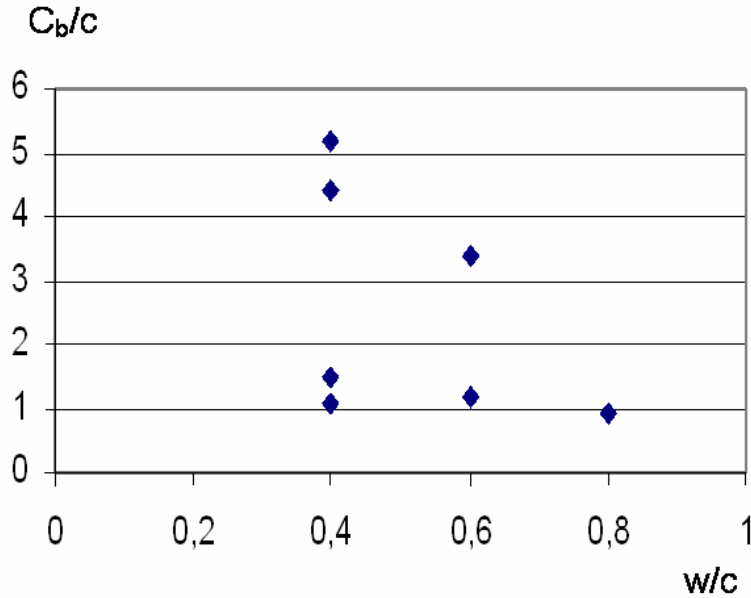


Figure 7: Relation between the free c and bound chloride (c<sub>b</sub>) versus the w/c-ratio. Data from Examples 3-9.

The effect of water-cement ratio on chloride binding, and thus on the effective chloride diffusion coefficient, is further discussed in ANNEX 1 and ANNEX 2.

## 4 Limestone filler in concrete – possible effects on chloride penetration

### Alt 1: The filler is completely inert

If a completely inert material is added to a concrete with fixed water-cement ratio there should be *no effect* on the rate of chloride ingress in concrete for the following reasons:

1. The “steady state” diffusion coefficient  $\delta_0$  should be unchanged since the inert filler does, by definition of “inert”, not create any new hydration products or modification of the ordinary hydration products. Thus, the chloride permeability  $\delta_0$  is unchanged.
2. The binding of chloride is unchanged since the filler is supposed to be inert also with regard to chloride. Thus, also the coefficient R in equation (3) is unchanged.
3. This means that the effective diffusion coefficient  $\delta_{\text{eff}} = \delta_0 / (R+1)$  is unaffected by the filler

### Alt 2: The filler does not change the pore structure but it reacts with components binding chloride

The main cement components determining the built-up of the pore structure, the calcium silicates  $C_3S$  and  $C_2S$ , are supposed not to be affected by the filler. Therefore, the pore structure and the permeability are supposed to be unchanged. On the other hand, the filler is supposed to react with components binding chloride, mainly  $C_3A$ , and possibly to some extent  $C_4AF$ ; Bonavetti, Rahal & Irassar (2001)

In this case, the filler might increase the rate of chloride ingress in concrete for the following reasons:

1. The “steady state” diffusion coefficient  $\delta_0$  is unchanged since the pore structure is unchanged.
2. The binding capacity for chloride is reduced since the reaction components formed by reaction of  $C_3A$  (and  $C_4AF$ ) with the filler is assumed not to be capable of binding chloride to the same extent as the normal reaction products of  $C_3A$  (formation of Friedel’s salt). Reduced binding capacity means that the coefficient R in equation (3) is reduced.
3. Consequently the effective diffusion coefficient  $\delta_{\text{eff}} = \delta_0 / (R+1)$  is increased.

The effect of filler is illustrated by two examples.

#### **Example 15 (based on Figure 2, Example 3)**

Before addition of filler the value of R is 5.2. The effective diffusion coefficient is assumed to be  $\delta_{\text{eff}} = 5 \cdot 10^{-12} \text{ m}^2/\text{s}$ .

Thus, the steady state diffusion coefficient is  $\delta_0 = (5.2+1)5 \cdot 10^{-12} = 31 \cdot 10^{-12} \text{ m}^2/\text{s}$ .

After addition of filler the binding capacity is halved; i.e.  $R=2.6$ . The effective diffusion coefficient becomes

$$\delta_{\text{eff}} = 31 \cdot 10^{-12} / (2.6+1) = 8.6 \cdot 10^{-12} \text{ m}^2/\text{s}$$

**Example 16 (Based on Figure 4, Example 6)**

Before addition of filler the value of R is 1.5. The effective diffusion coefficient is assumed to be  $\delta_{\text{eff}}=5 \cdot 10^{-12} \text{ m}^2/\text{s}$ .

The steady state diffusion coefficient is  $\delta_0=(1.5+1)5 \cdot 10^{-12}=12.5 \cdot 10^{-12} \text{ m}^2/\text{s}$ .

After addition of filler the binding capacity is halved; i.e.  $R=0.8$ . The effective diffusion coefficient becomes

$$\delta_{\text{eff}}=12.5 \cdot 10^{-12}/(0.8+1)=6.9 \cdot 10^{-12} \text{ m}^2/\text{s}$$

According to these examples the filler reaction has increased the diffusion coefficient by 72% (Example 15) or 38 % (Example 16) despite the fact that the w/c-ratio is unchanged. This shows that limestone-filler might have a detrimental effect. This can also be expressed in terms of limestone filler having a “*negative efficiency factor with regard to chloride ingress*”; i.e. each kilo of limestone filler added to the concrete requires increased cement content if the ingress of chloride shall not increase.

**Alt 3: The filler reacts with components binding chloride and also modifies the pore structure**

As in Alt 2 the filler is supposed to react with components binding chloride, mainly  $C_3A$ , and to some extent  $C_4AF$ , reducing their capacity for binding chloride. Furthermore, the pore structure is supposed to be changed by this reaction. In this case the filler might increase the rate of chloride ingress in concrete for the following reasons:

1. The “steady state” diffusion coefficient  $\delta_0$  is increased since the pore structure is changed in a way that gives an increased permeability. The new steady state diffusivity is  $(1+\Delta)\delta_0$  where  $\Delta$  is the increase in diffusivity. (In reality there will probably be a reduced value of  $\delta_0$ ).
2. The binding capacity for chloride is reduced by the same mechanism as in Alt 2. Reduced binding capacity means that the coefficient R in equation (3) is reduced.
3. Consequently, the effective diffusion coefficient  $\delta_{\text{eff}}=\delta_0/(R+1)$  is increased.

**Example 17 (based on Figure 2, Example 3)**

Before addition of filler the value of R is 5.2. The effective diffusion coefficient is assumed to be  $\delta_{\text{eff}}=5 \cdot 10^{-12} \text{ m}^2/\text{s}$ .

Thus, the steady state diffusion coefficient is  $\delta_0=(5.2+1)5 \cdot 10^{-12}=31 \cdot 10^{-12} \text{ m}^2/\text{s}$ .

After addition of filler the steady state diffusion coefficient is increased by 25%; i.e.  $\delta_0=1.25 \cdot 31 \cdot 10^{-12}=3.9 \cdot 10^{-11} \text{ m}^2/\text{s}$ . The binding capacity is halved; i.e.  $R=2.6$ .

The effective diffusion coefficient becomes

$$\delta_{\text{eff}}=3.9 \cdot 10^{-11}/(2.6+1)=10.8 \cdot 10^{-12} \text{ m}^2/\text{s}$$

The diffusion coefficient is increased by 116% by the addition of filler.

## 5 Experimental methods for determination of the effect of limestone filler on chloride diffusion and binding

### 5.1 Introduction

In order to investigate the effect of limestone filler on chloride penetration in concrete its effects on chloride diffusivity and chloride binding should be determined. This will elucidate the theoretical background to the observations made that limestone filler might have a negative “efficiency factor” with regard to chloride penetration.

The measurements should preferably be made on cement pastes or mortars with different fixed w/c-ratio. Thus, the filler should be used as *addition* and not as replacement of cement.

### 5.2 The “steady state” diffusion coefficient

The steady state diffusion coefficient reveals the effect of filler on the chloride permeability of the cement paste. If the filler is not inert, but reacts with the cement, one might suspect that the permeability is reduced, so that also the diffusion coefficient  $\delta_0$  is reduced.

A diffusion cell of the type shown in Figure 8 could be used. The solution in the two chambers should be an artificial pore solution in order to avoid leaching of OH<sup>-</sup> and lime from the mortar. One way of creating such a solution is to mix a cement paste or cement mortar with the actual composition, and after some time -just before the cement binds- extract the water in the paste or mortar by vacuum. The mix is poured in a funnel with filter paper placed in a vacuum flask. The technique is described in Fagerlund (1982).

The steady state diffusion coefficient can be identified by continuous measurements of the change in the Cl-concentrations in the two chambers.

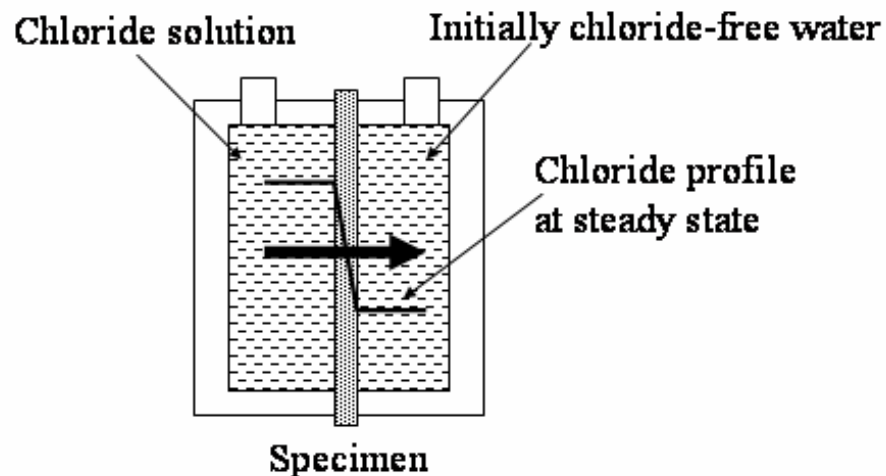


Figure 8: Diffusion cell for determination of the (steady-state) diffusion coefficient,  $\delta_0$

Measurements are made for mortar with different w/c-ratio and different amount of limestone filler of different quality. Comparisons are made with normal mortar without filler.

The evaluation technique is described in ANNEX 3.


### 5.3 Chloride binding

Bound chloride is the difference between total and free chloride:

$$c_b' = c_{tot}' - c' \quad (14)$$

where  $c_b'$ ,  $c_{tot}'$  and  $c'$  are the bound chloride, the total chloride and the free chloride respectively, all expressed in the unit kg per m<sup>3</sup> of dry material.

A thin slice of the material (cement paste or mortar) is immersed in a solution with known chloride concentration. The base-solution should preferably be as like the pore solution as possible in order to avoid leaching from the specimen; see above.

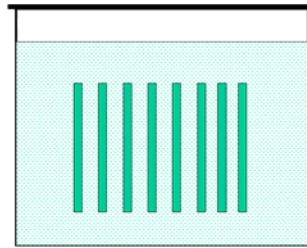

*Figure 9: Long-term storage of thin slices in chloride solution of known concentration,  $c$  kg/m<sup>3</sup>.*

After long time, there is equilibrium between the chloride concentration in the pores and the concentration of the outer solution. Then, the specimen is taken up, pulverised and dissolved in an acid that dissolves all chloride. The total chloride content  $c_{tot}'$  is determined by titration.

From the known pore volume the amount of dissolved chloride  $c'$  is calculated. The free chloride content becomes:

$$c' = c \cdot W_w \quad (15)$$

Where  $W_w$  is the amount of pore water able to dissolve chloride (m<sup>3</sup> per m<sup>3</sup> of concrete),  $c$  is the chloride concentration in the bath (kg per m<sup>3</sup>).

It is, as a first approximation, assumed that all evaporable pore water is capable of dissolving chloride; i.e.:

$$c' = c \cdot C(W/C - 0.19 \cdot \alpha) / 1000 \quad (16)$$

Where  $C$  is the cement content (kg per m<sup>3</sup> of concrete),  $\alpha$  is the degree of hydration, and 1000 is the density of water (kg/m<sup>3</sup>).

Possibly, the “gel-water” is not dissolving chloride to the same extent as the capillary water, and, therefore, not taking part in chloride transport. If this is the case, the bound chloride and the value of  $R$  will be higher as shown by the examples below.

The bound chloride  $c_b'$  can be calculated by equation (14). The chloride binding curves in Figures 3 and 4 were determined by this type of technique.

**Example 18: All pore water dissolves chloride. Low w/c-ratio**

- The specimen volume:  $V=24 \text{ cm}^3$  (Slice 3 mm thick, 10 cm diameter).
- $w/c=0.4$
- Degree of hydration: 0.6
- Cement content:  $C=600 \text{ kg/m}^3$ ;  $C'=0.6 \text{ g/cm}^3$ .
- The chloride concentration in the bath: 0.5 mole/litre  
( $=17.8 \text{ g/litre}=17.8 \cdot 10^{-3} \text{ g/cm}^3$ ).
- The total chloride content in the specimen found by titration after terminated test: 0.35 g
- The total water volume in the specimen:  $w_{w,\text{tot}}=C'(W/C-0.19 \cdot \alpha)V=0.6(0.4-0.19 \cdot 0.6)24=4.1 \text{ cm}^3$
- The total amount of free chloride in the specimen:  $17.8 \cdot 10^{-3} \cdot 4.1 \text{ g} = 0.073 \text{ g}$

The relation between bound and free chloride:  $R=(0.35-0.073)/0.073=3.8$

**Data later used in Examples 20 and 21**

- Cement content:  $Q_C=0.6 \cdot 24=14.4 \text{ g}$
- Amount of cement gel (hydration products):  $1.25 \cdot \alpha \cdot C' = 1.25 \cdot 0.6 \cdot 14.4=10.8 \text{ g}$
- Bound chloride in gel:  $(0.35-0.073)/10.8=0.0256 \text{ g/g}$

**Example 19: Only capillary pore water dissolves chloride. Low w/c-ratio**

The same experiment as above.

- The capillary water volume:  $w_{w,\text{cap}}=C'(W/C-0.39 \cdot \alpha)V=0.6(0.4-0.39 \cdot 0.6)24=2.4 \text{ cm}^3$
- The total amount of free chloride in the specimen:  $17.8 \cdot 10^{-3} \cdot 2.4 \text{ g} = 0.043 \text{ g}$

The relation between bound and free chloride:  $R=(0.35-0.043)/0.043=7.1$

These examples show that it is extremely important to use the correct pore volume in the calculation of free chloride.

According to Figure 4 the chloride binding is proportional to the amount of cement gel. This means that one might obtain a more correct relation between free and bound chloride by using concrete with low amount of gel pores; i.e. with material with high w/c-ratio. This is shown by the following examples.

**Example 20: All pore water dissolves chloride. High w/c-ratio**

The same bath and specimen size as above; i.e. 17.8 g/litre and 24 cm<sup>3</sup>

- w/c-ratio: 0.9
- Degree of hydration: 0.8
- Cement content:  $C=400 \text{ kg/m}^3$  ;  $C'=0.4 \text{ g/cm}^3$ .
- The amount of cement:  $Q_C=0.4 \cdot 24=9.6 \text{ g}$
- The amount of cement gel:  $1.25 \cdot \alpha \cdot Q_C=1.25 \cdot 0.8 \cdot 9.6=9.6 \text{ g}$
- Bound chloride in gel: 0.0256 g/g (same as in Example 18)
- Bound chloride after terminated test:  $0.0256 \cdot 9.6=0.246 \text{ g}$
- The total water volume in the specimen:  $w_{w,\text{tot}}=C'(W/C-0.19 \cdot \alpha)V=$   
 $=0.4(0.9-0.19 \cdot 0.8)24=7.2 \text{ cm}^3$
- The total amount of free chloride in the specimen:  $17.8 \cdot 10^{-3} \cdot 7.2 \text{ g} = 0.128 \text{ g}$
- Total chloride:  $0.246+0.128=0.564 \text{ g}$

The relation between bound and free chloride:  **$R=0.246/0.128=1.9$**

**Example 21: Only capillary pore water dissolves chloride. High w/c-ratio**

The same experiment and concrete as in Example 20

- The capillary water volume:  $w_{w,\text{cap}}=C'(W/C-0.39 \cdot \alpha)V=0.4(0.9-0.39 \cdot 0.8)24=$   
 $=5.6 \text{ cm}^3$
- The total amount of free chloride in the specimen:  $17.8 \cdot 10^{-3} \cdot 5.6 \text{ g} = 0.100 \text{ g}$
- Bound chloride: 0.246 g (same as Example 20)

The relation between bound and free chloride:  **$R=0.246/0.10=2.5$**

The difference between the two different ways of defining the pore volume that is able to dissolve chloride is now much smaller than when concrete with low w/c-ratio was used.

The true water volume that is able to dissolve chloride  $W_w$  (m<sup>3</sup> per m<sup>3</sup> concrete) is:

$$W_w = C(W/C-\gamma \cdot \alpha)/1000 \quad (17)$$

Where  $0.19 \leq \gamma \leq 0.39$ .

In ANNEX 4 an experimental method for determination of the “active” porosity, i.e. the coefficient  $\gamma$ , is outlined.

Instead of calculating the total pore volume, as is made in the examples above, one can determine it experimentally. The total pore volume is determined in the traditional way using vacuum saturation and weighing in air and water, subtracting air-pores and compaction pores, which are supposed not to take up water. The capillary pore volume can be approximately calculated as the difference between the water content at complete saturation (coarse air-pores and similar pores excluded) and the water content at equilibrium with about 45% RH.

Measurements of chloride binding by the method described shall be made for many different chloride concentrations and for mortar with different w/c-ratio and different amount of limestone filler of different quality. Comparisons are made with normal mortar without filler.

The time needed for establishing equilibrium with the outer solution depends on the thickness of the specimen, and on its chloride diffusivity. The time needed  $t$  (s) is given by the Fourier number  $Fo$ :

$$Fo=4\cdot\delta_{\text{eff}}\cdot t/L^2 \quad (18)$$

where  $L$  is the specimen thickness (m). Equilibrium is almost reached when  $Fo=1.5$ ; Crank (1985). This corresponds to the time:

$$t=1.5\cdot L^2/(4\cdot\delta_{\text{eff}}) \quad (18')$$

The lowest possible value of  $\delta_{\text{eff}}$  is about  $5\cdot 10^{-13}$  m<sup>2</sup>/s. For a specimen thickness 5 mm the time needed is then:

$$t=1.5\cdot(5\cdot 10^{-3})^2/(4\cdot 5\cdot 10^{-13})=1.9\cdot 10^7 \text{ s}=217 \text{ days}$$

For concrete of normal quality the time needed is shorter.

## **6. Conclusions**

Chloride ingress in concrete is a very complicated process. Above all, the binding of chloride by adsorption and chemical reaction is not very well understood. Some data from literature on chloride binding are reviewed. A promising approach is that exemplified in Figure 4; i.e. assuming that binding is proportional to the amount of hydration products. These can, as a first approximation, be described by equation (13), although this is only valid for OPC without addition of reactive material.

The use of limestone filler in concrete might have an impact on the rate by which chloride is entering the concrete. It might affect both the steady state chloride permeability by changing the pore structure, and change the chloride binding capacity by reacting with aluminates in the concrete. These effects ought to be investigated experimentally. Test methods are suggested.

## References

- Arya, C. & Newman, J.B (1990). An assessment of four methods of determining the free chloride content of concrete. *Materials and Structures*, Vol 23.
- Bonavetti, V.L., Rahhal, V.F., Irassar, E.F (2001). Studies on the carboaluminate formation in limestone filler-blended cement. *Cement and Concrete Research*, Vol 31.
- Boubitsas, D (2005). Studies on the efficiency of granulated blast furnace slag and limestone filler in mortars. Long-term strength and chloride penetration. Div. Building Research. Report TVBM-3125, Lund.
- Crank, J. (1985). *The mathematics of diffusion*. Clarendon Press, Oxford.
- Fagerlund, G (1982). The influence of slag cement on the frost resistance of the hardened concrete. Swedish Cement and Concrete Research Institute. Research Fo 1.82. Stockholm.
- Frederiksen, J.M., Sørensen, H.E., Andersen, A., Klinghoffer, O. (1997). The effect of water-cement ratio on chloride transport into concrete – immersion, migration and resistivity tests. Project "HETEK", The Danish Road Directorate, Report No. 54.
- Persson, B (2001). Assessment of the chloride migration coefficient, internal frost resistance, salt frost scaling and sulphate resistance of self-compacting concrete - with some interrelated properties. Div. Building Research. Report TVBM-3100, Lund.
- Sandberg, P. & Larsson, J (1993). Chloride binding in cement pastes in equilibrium with synthetic pore solutions. Proc. Nordic Seminar on Chloride Initiated Reinforcement Corrosion in Concrete. Chalmers Technical University, Div. Building Materials. Jan. 13-14, 1993. Gothenburg.
- Tang, L (1996). Chloride transport in concrete – Measurement and Prediction. Div. of Building Materials, Chalmers University of Technology, Report P-96:6, Gothenburg.
- Tang, L. & Nilsson, L-O (1993). Chloride binding capacity and binding isotherms of OPC pastes and mortars. *Cement and Concrete Research*, Vol 23.
- Tuutti, K (1982). Corrosion of steel in concrete. Swedish Cement and Concrete Research Institute. Research Fo 4. 82. Stockholm.



# ANNEX 1

## CHLORIDE BINDING AS FUNCTION OF THE WATER-CEMENT RATIO AND AGE

### A1.1 Theory

In this ANNEX an attempt is made to find a relation between the coefficient R describing chloride binding -see equation (3)- and the composition and age of the concrete.

It is assumed that chloride binding is directly proportional to the amount of cement gel; see Figure 4 and equation (15). The amount of bound chloride is:

$$c_b' = c_{b,gel} \cdot 1.25 \cdot \alpha \cdot C \quad (A1)$$

Where  $c_b'$  is the amount of bound chloride in unit volume of concrete (kg per m<sup>3</sup> concrete),  $c_{b,gel}$  is the amount of bound chloride in unit weight of gel (kg chloride per kg cement gel),  $1.25 \cdot \alpha \cdot C$  is the amount of gel in unit volume of concrete (kg gel per m<sup>3</sup> concrete),  $\alpha$  is the degree of hydration,  $C$  is the cement content (kg cement per m<sup>3</sup> concrete). Instead of considering a unit volume of concrete a unit volume of cement mortar or cement paste can be considered. It will not alter the equation.

The coefficient  $c_{b,gel}$  will depend on the chloride concentration of the pore solution as shown in Figure 4.

The amount of bound chloride will depend on the fraction of pore water dissolving chloride, and therefore participating in the chloride transport process, “delivering” chloride to be bound during the transport. Two possibilities are investigated:

- Alt A. All pore water participates.
- Alt B. only capillary pore water participates.

***Alt A: All pore water is assumed to dissolve chloride and therefore also assumed to take part in chloride transport***

The volume of pore water dissolving chloride is (provided the concrete is saturated and the aggregate is non-porous):

$$W_w = C(W/C - 0.19 \cdot \alpha) / 10^3 \quad (A2)$$

Where  $W_w$  is the volume of pore water in unit volume of concrete (m<sup>3</sup> pore water per m<sup>3</sup> of concrete).

The amount of bound chloride extracted from the pore solution during diffusion therefore is:

$$c_b = c_b' / W_w = c_{b,gel} \cdot 1.25 \cdot \alpha \cdot 10^3 / (W/C - 0.19 \cdot \alpha) \quad (A3)$$

Where  $c_b$  is the amount of extracted chloride by binding (kg bound chloride per m<sup>3</sup> pore solution).

The free chloride concentration in the pore water is  $c$  (kg chloride per  $m^3$  pore water). Thus, the coefficient  $R$  as defined by equation (3) becomes:

$$R = c_b/c = (c_{b,gel}/c) \cdot 1.25 \cdot \alpha \cdot 10^3 / (W/C - 0.19 \cdot \alpha) \quad (A4)$$

Where  $c_{b,gel}/c$  is given by the chloride binding isotherm (e.g. Figure 4).

For 75% degree of hydration equation (A4) becomes:

$$R = (c_{b,gel}/c) \cdot 0.94 \cdot 10^3 / (W/C - 0.14) \quad (A4')$$

Thus, for a given chloride concentration of pore water, the coefficient  $R$  is only a function of the water-cement ratio. Furthermore, the lower the w/c-ratio the bigger the value of  $R$ .

**Alt B: Only capillary pore water is assumed to dissolve chloride and therefore also assumed to take part in chloride transport**

The volume of pore water dissolving chloride ( $m^3$  per  $m^3$  of concrete) is:

$$V_w = C(W/C - 0.39 \cdot \alpha) / 10^3 \quad (A5)$$

The amount of bound chloride extracted from the pore solution during diffusion therefore is:

$$c_b = c_b' / V_w = c_{b,gel} \cdot 1.25 \cdot \alpha \cdot 10^3 / (W/C - 0.39 \cdot \alpha) \quad (A6)$$

Thus, the coefficient  $R$  as defined by equation (3) becomes:

$$R = c_b/c = (c_{b,gel}/c) \cdot 1.25 \cdot \alpha \cdot 10^3 / (W/C - 0.39 \cdot \alpha) \quad (A7)$$

For 75% degree of hydration equation (A4) becomes:

$$R = (c_{b,gel}/c) \cdot 0.94 \cdot 10^3 / (W/C - 0.29) \quad (A7')$$

## A1.2 Results

Some examples of equations (A4') and (A7') showing the effect of w/c-ratio on the coefficient  $R$  are given in Table A1. The data for  $c$  and  $c_{b,gel}$  are taken from Figure 4.

Table A1: The coefficient  $R$  based on the chloride binding curve in Figure 4. Degree of hydration 0.75.

Free chloride $c$		Bound chloride $c_{b,gel}$ (kg/kg)	R equation (A4')			R equation (A7')		
mole/litre	kg/m <sup>3</sup>		w/c 0.4	w/c 0.5	w/c 0.6	w/c 0.4	w/c 0.5	w/c 0.6
0.2	7.1	$7 \cdot 10^{-3}$	3.6	2.6	2.0	8.4	4.4	3.0
0.4	14.2	$9 \cdot 10^{-3}$	2.3	1.7	1.3	5.4	2.8	1.9
0.8	28.4	$13 \cdot 10^{-3}$	1.7	1.2	0.9	3.9	2.0	1.4

The data in Table A1 are also plotted in Figure A1, A2 and A3.

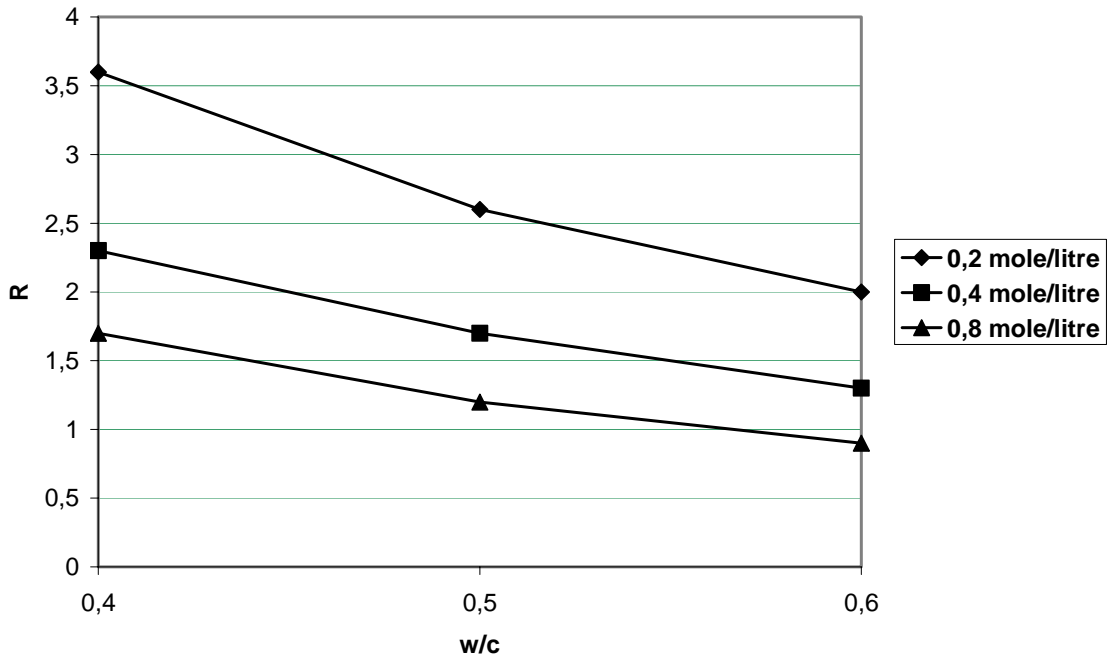


Figure A1. Effect of w/c-ratio on the coefficient R. Data from Table A1. All pore water participates in chloride transport; equation (A4). Degree of hydration 0.75.

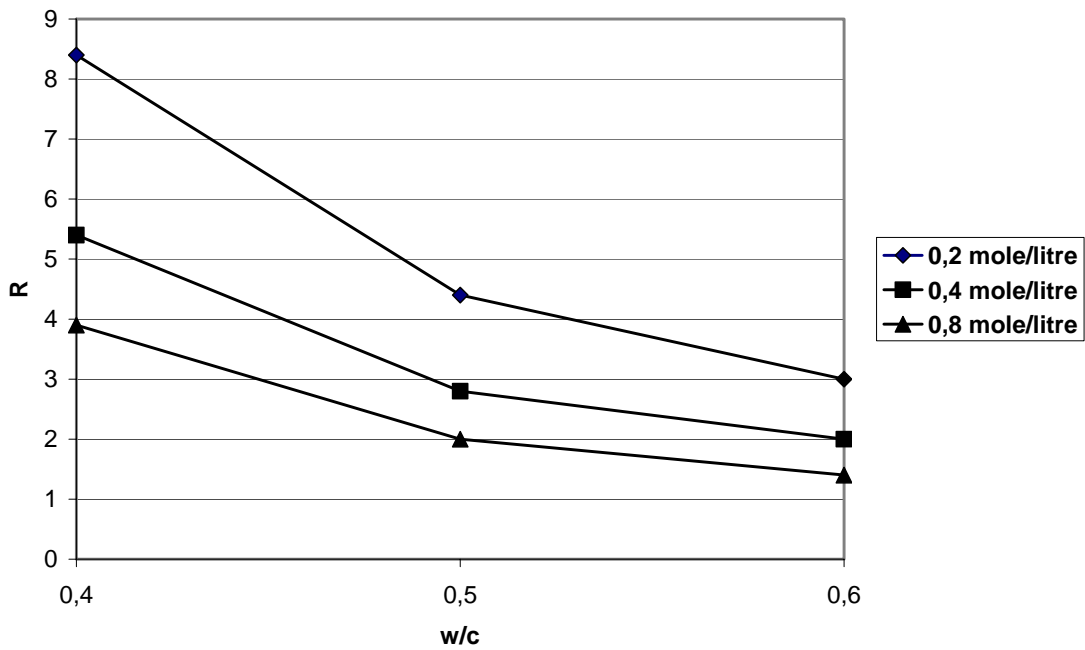


Figure A2. Effect of w/c-ratio on the coefficient R. Data from Table A1. Only capillary pore water participates in chloride transport; equation (A7). Degree of hydration 0.75.

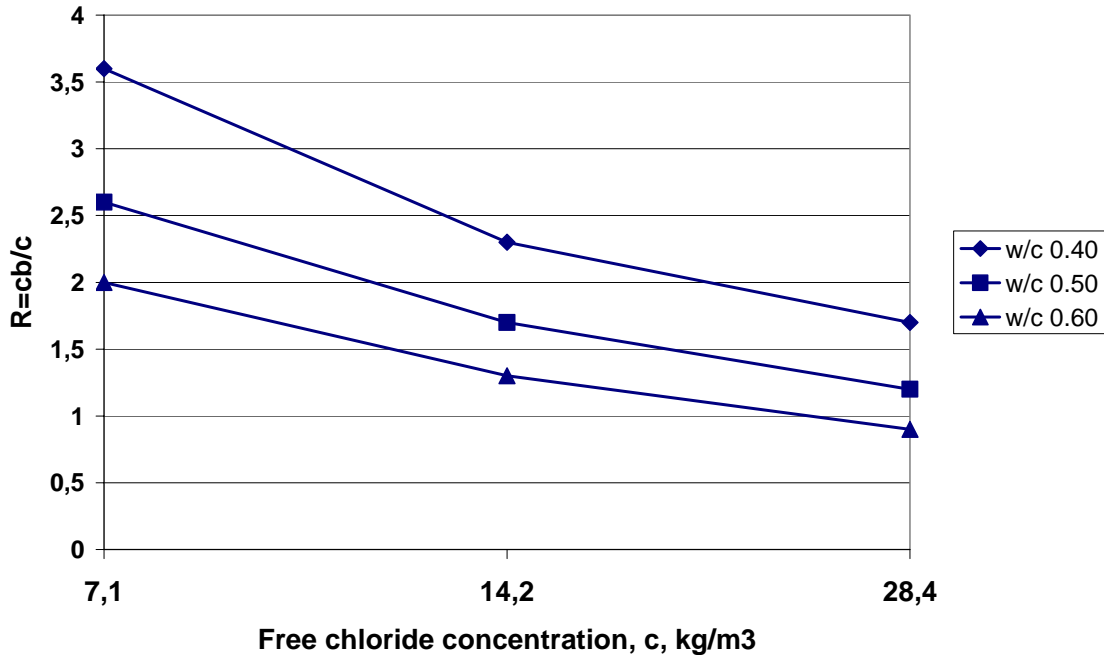


Figure A3. Effect of the free chloride concentration on the coefficient R. Data from Table A1. All pore water participates in chloride transport; equation (A4). Degree of hydration 0.75.

The analysis shows that the chloride binding is bigger, and therefore has a larger retarding effect on the chloride transport, the lower the w/c-ratio is.

It is also shown that the difference between different ways of defining volume of pore solution is very big for low free concentration and low w/c-ratio.

Furthermore, chloride binding has bigger effect the higher the degree of hydration is. This is illustrated by Example A1.

<b>Example A1: Data from Figure 4; <math>c=14.2 \text{ kg/m}^3</math>, <math>c_{b, \text{gel}}=9 \cdot 10^{-3} \text{ kg/kg}</math> <math>W/C = 0.50</math></b>		
	<i>Equation (A4)</i>	<i>Equation (A7)</i>
$\alpha = 0.25$	R = 0.44	R = 0.49
$\alpha = 0.50$	R = 0.98	R = 1.30
$\alpha = 0.75$	R = 1.66	R = 2.86
$\alpha = 1.0$	R = 2.56	R = 7.20

More examples on the effect of degree of hydration on chloride binding are given in Figure A4.

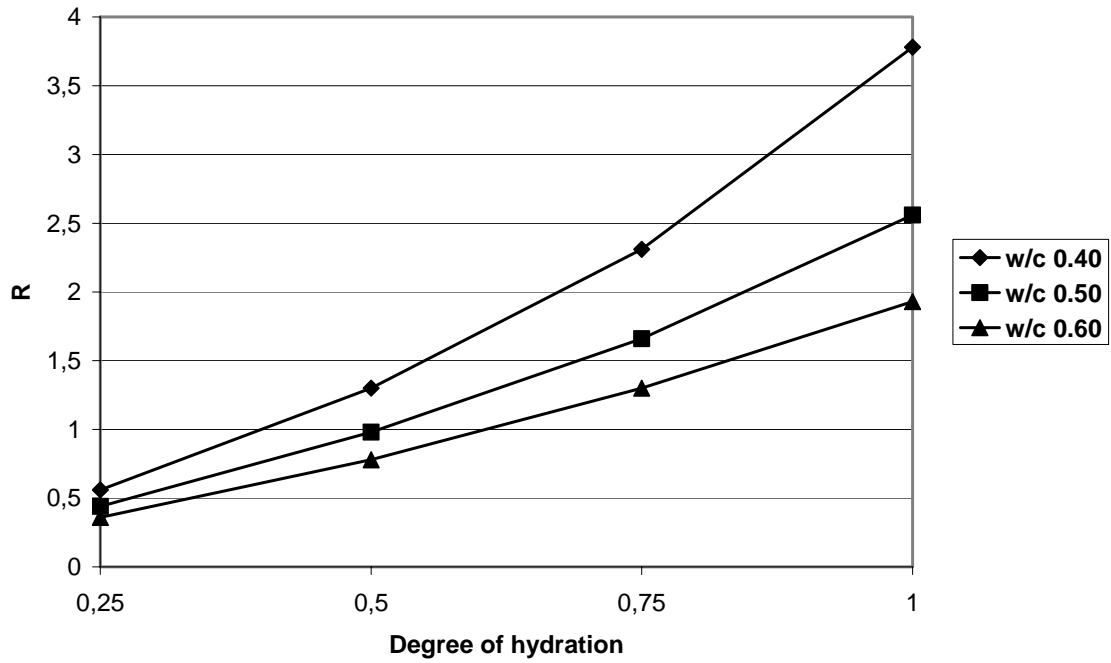


Figure A4. Effect of the degree of hydration on the coefficient R. Data from Figure 4. Calculations based on equation (A4).

### A1.3 Imaginable effect of limestone filler

As described in paragraph 4, limestone filler might change *chloride binding* by changing the parameter  $c_{b,gel}$ . Thus, Figure 4 can hardly be applied also to concrete with limestone filler. New interrelated values between the free concentration  $c$  and the bound chloride  $c_{b,gel}$  must be determined, e.g. by the technique described in paragraph 5.3. The hypothetical effect of limestone filler on the “chloride binding isotherm” is shown in Figure A5. In the figure it is assumed that the hydration products (the “gel”) bind less chloride in concrete with limestone filler.

It is assumed that the pore water volumes described by equations (A2) and (A5) are valid also for concrete with limestone filler. Principally, this hypothesis should be tested by comparative measurements of porosity and water sorption isotherms on cement paste (or mortar) with and without filler.

This means that equations (A4) and (A7) can also be used for concrete with limestone filler but with other values of  $c_{b,gel}$ .

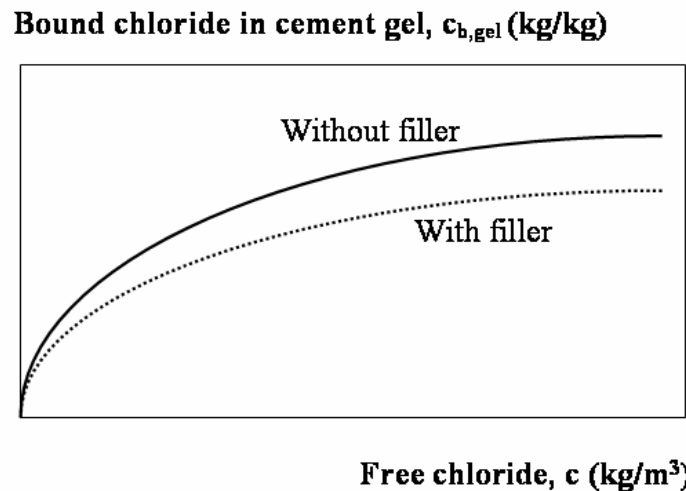


Figure A5: Effect of limestone filler on chloride binding. Hypothetic relations.

## ANNEX 2

### EFFECTIVE CHLORIDE DIFFUSION COEFFICIENT AS FUNCTION OF THE WATER-CEMENT RATIO AND AGE

#### A2.1 The *relative* effective diffusion coefficient

The relative effective diffusion coefficient is -see equation (5):

$$\delta_{\text{eff}}/\delta_0 = 1/(R+1) \quad (\text{A8})$$

Where  $\delta_0$  is the “steady state” diffusion coefficient.

Inserting equations (A4) and (A7) in equation (A8) gives:

*Alt A: All pore water takes part in chloride transport -equation (A4):*

$$\delta_{\text{eff}}/\delta_0 = 1/\{[(c_{\text{b,gel}}/c) \cdot 1.25 \cdot \alpha \cdot 10^3]/[W/C - 0.19\alpha] + 1\} \quad (\text{A9})$$

*Alt B: Only capillary pore water takes part in chloride transport – equation (A7)*

$$\delta_{\text{eff}}/\delta_0 = 1/\{[(c_{\text{b,gel}}/c) \cdot 1.25 \cdot \alpha \cdot 10^3]/[W/C - 0.39\alpha] + 1\} \quad (\text{A10})$$

Table A2 shows the calculated effective diffusivity for concrete with 75% degree of hydration. Data for the coefficient R are taken from Table A1.

*Table A2: The **relative** effective chloride diffusion coefficient. Data from Table A1.  
Degree of hydration 0.75.*

Free chloride c mole/litre	$\delta_{\text{eff}}/\delta_0$ equation (A9)			$\delta_{\text{eff}}/\delta_0$ equation (A10)		
	w/c 0.4	w/c 0.5	w/c 0.6	w/c 0.4	w/c 0.5	w/c 0.6
0.2	0.22	0.28	0.33	0.11	0.19	0.25
0.4	0.30	0.37	0.43	0.16	0.26	0.34
0.8	0.37	0.45	0.53	0.20	0.33	0.42

The data in Table A2 are plotted in Figure A6 and A7.

The theoretical analysis shows that there is an almost linear relation between the diffusion coefficient and the w/c-ratio. Such linear relations have also been found experimentally; e.g. Frederiksen et al. (1997).

The reduction in chloride diffusivity caused by binding is bigger the lower the w/c-ratio and the lower the outer concentration of free chloride are.

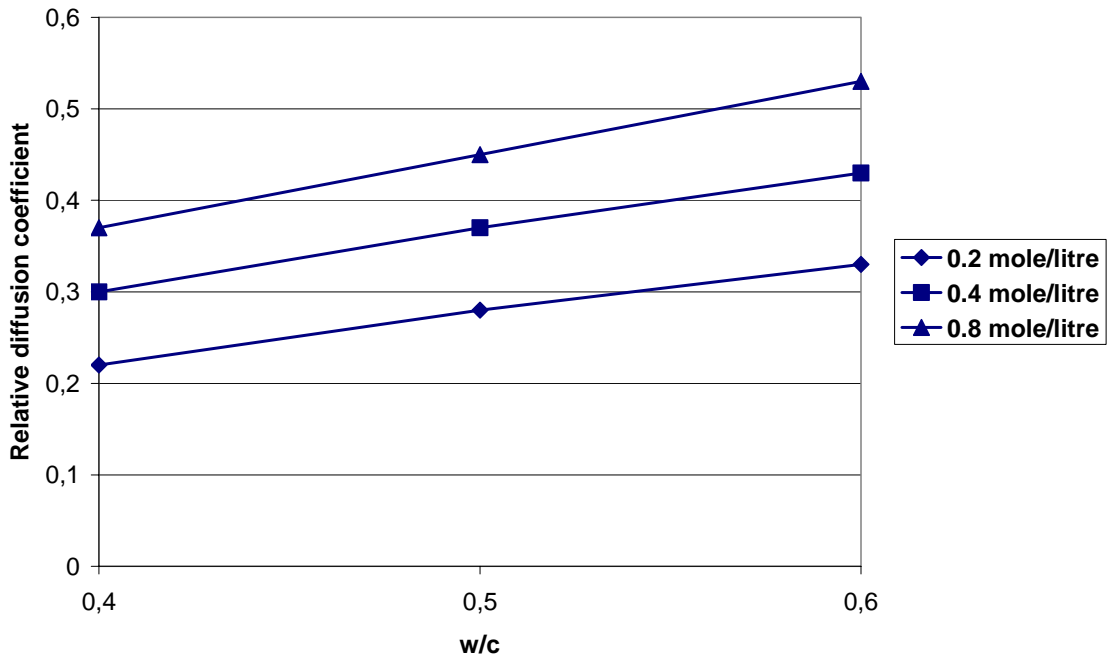


Figure A6: Effect of the w/c-ratio on the relative chloride diffusion coefficient ( $\delta_{eff}/\delta_0$ ). Data from Table A2. All pore water participates in chloride transport – equation (A9). Degree of hydration 0.75.

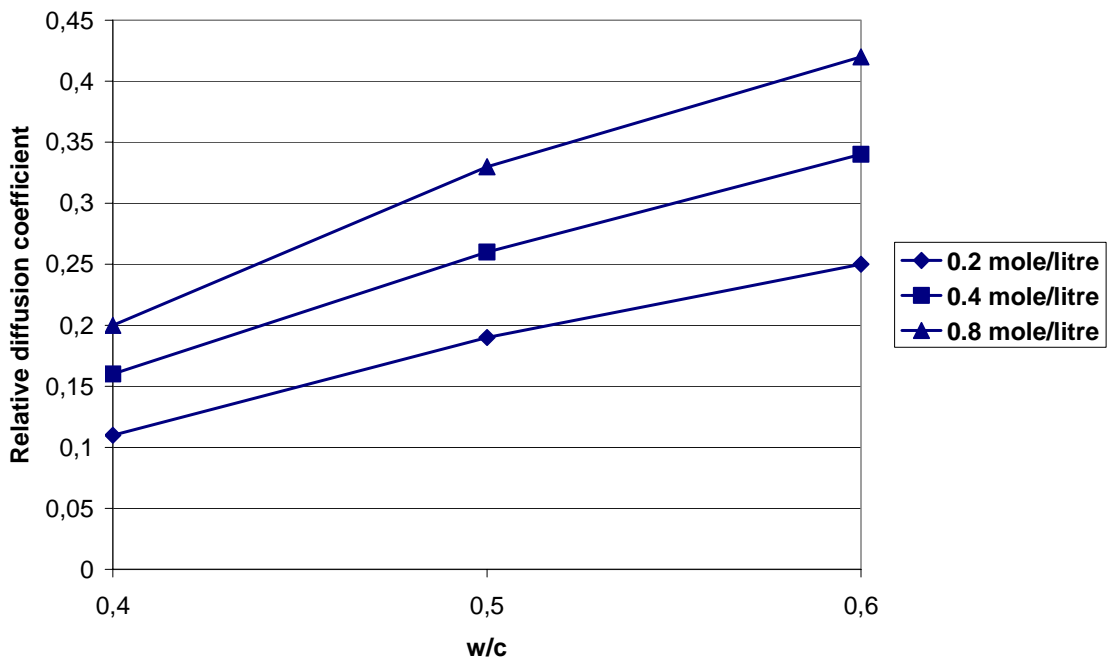


Figure A7: Effect of the w/c-ratio on the relative chloride diffusion coefficient ( $\delta_{eff}/\delta_0$ ). Data from Table A2. Only capillary pore water participates in chloride transport – equation (A10). Degree of hydration 0.75.

A consequence of equation (A9) and (A10) is that *the effective diffusion coefficient* is reduced with increased degree of hydration. This is illustrated by Example A2.

***Example A2: Values of R taken from Example A1 (W/C 0.50)***

$$\delta_{\text{eff}} = \delta_0 / (R+1)$$

	<i>Equation (A9)</i>	<i>Equation (A10)</i>
$\alpha = 0.25$	$\delta_{\text{eff}}/\delta_0 = 1/1.44 = 0.69$	$\delta_{\text{eff}}/\delta_0 = 1/1.49 = 0.67$
$\alpha = 0.50$	$\delta_{\text{eff}}/\delta_0 = 1/1.98 = 0.51$	$\delta_{\text{eff}}/\delta_0 = 1/2.30 = 0.43$
$\alpha = 0.75$	$\delta_{\text{eff}}/\delta_0 = 1/2.66 = 0.38$	$\delta_{\text{eff}}/\delta_0 = 1/3.86 = 0.26$
$\alpha = 1.0$	$\delta_{\text{eff}}/\delta_0 = 1/3.56 = 0.28$	$\delta_{\text{eff}}/\delta_0 = 1/8.20 = 0.12$

## A2.2 The *absolute* effective diffusion coefficient

The steady state diffusion coefficient  $\delta_0$  as defined by Equation (2) is valid for the entire concrete surface, which is composed of both solid and porous phases. But chloride is only moving in the porous phase. Thus, the bigger the portion of porous phase the bigger is the value of  $\delta_0$ . Therefore,  $\delta_0$  can, as a first approximation, be assumed to be *directly proportional* to the water-filled porosity,  $P_w$ ; i.e.:

$$\delta_0 = K \cdot P_w \quad (A11)$$

Where  $K$  is a coefficient describing a *fictitious* diffusivity for 100% porosity.  $K$  is *independent* of the w/c-ratio.

For a saturated concrete  $P_w = P_{tot}$  which is the total porosity; i.e.:

$$\delta_0 = K \cdot P \quad (A11')$$

Since it is only the cement paste that is porous (neglecting interfaces between stone and cement paste) the porosity in equation (A11') can be exchanged for the cement paste porosity.

The total porosity of cement paste is:

$$P_{tot} = (W/C - 0.19 \cdot \alpha) / (W/C + 0.32) \quad (A12)$$

The capillary porosity of cement paste is:

$$P_{cap} = (W/C - 0.39 \cdot \alpha) / (W/C + 0.32) \quad (A13)$$

Thus the steady state diffusion coefficient depends on how big part of the porosity that takes part in chloride transport.

**Alt A: The total pore volume takes part; i.e.:**

$$\delta_0 = K \cdot (W/C - 0.19 \cdot \alpha) / (W/C + 0.32) \quad (A14)$$

The diffusion coefficient  $\delta_{eff}$  is obtained by inserting equation (A9) and (A14) in (A8):

$$\delta_{eff} = K \left\{ \frac{(W/C - 0.19 \alpha)}{(W/C + 0.32)} \right\} / \left\{ \left[ \frac{(c_{b,gel}/c) 1.25 \alpha \cdot 10^3}{[W/C - 0.19 \alpha]} + 1 \right] \right\} \quad (A15)$$

**Alt B: Only the capillary pore volume takes part; i.e.:**

$$\delta_0 = K \cdot (W/C - 0.39 \cdot \alpha) / (W/C + 0.32) \quad (A16)$$

The diffusion coefficient  $\delta_{eff}$  is obtained by inserting equation (A10) and (A16) in equation (A8):

$$\delta_{eff} = K \left\{ \frac{(W/C - 0.39 \alpha)}{(W/C + 0.32)} \right\} / \left\{ \left[ \frac{(c_{b,gel}/c) 1.25 \alpha \cdot 10^3}{[W/C - 0.39 \alpha]} + 1 \right] \right\} \quad (A17)$$

The calculated diffusion coefficient for 75% degree of hydration is shown in Table A3.

Table A3: The **absolute** effective chloride diffusion coefficient. Data from Table A1 and A2.  
Degree of hydration 0.75.

Free chloride c mole/litre	$\delta_{\text{eff}}$ equation (A15)			$\delta_{\text{eff}}$ equation (A17)		
	w/c 0.4	w/c 0.5	w/c 0.6	w/c 0.4	w/c 0.5	w/c 0.6
0.2	0.080·K	0.123·K	0.165·K	0.0164·K	0.0481·K	0.0836·K
0.4	0.108·K	0.162·K	0.215·K	0.0239·K	0.0658·K	0.114·K
0.8	0.134·K	0.200·K	0.265·K	0.299·K	0.0835·K	0.140·K

Data in Table A3 are also shown in Figures A8, A9 and A10.

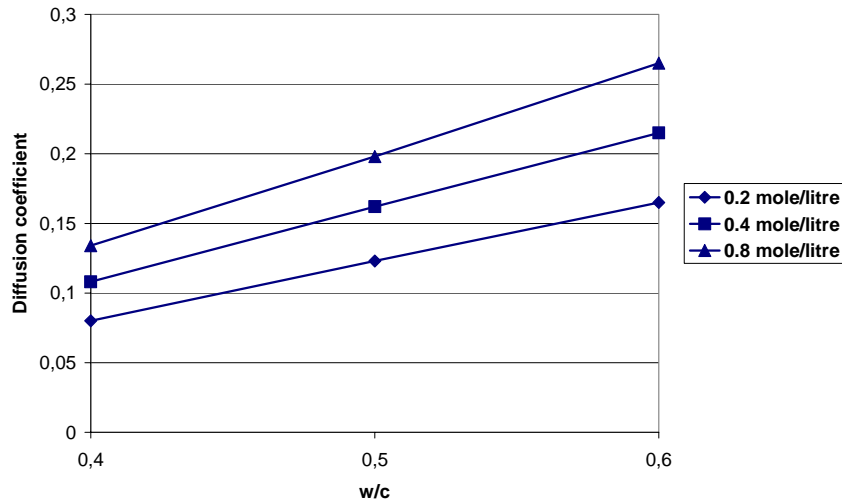


Figure A8: The effective diffusion coefficient as function of the w/c-ratio. All pore water takes place in chloride transport; equation (A15). The values shall be multiplied by the coefficient K. Degree of hydration 0.75.

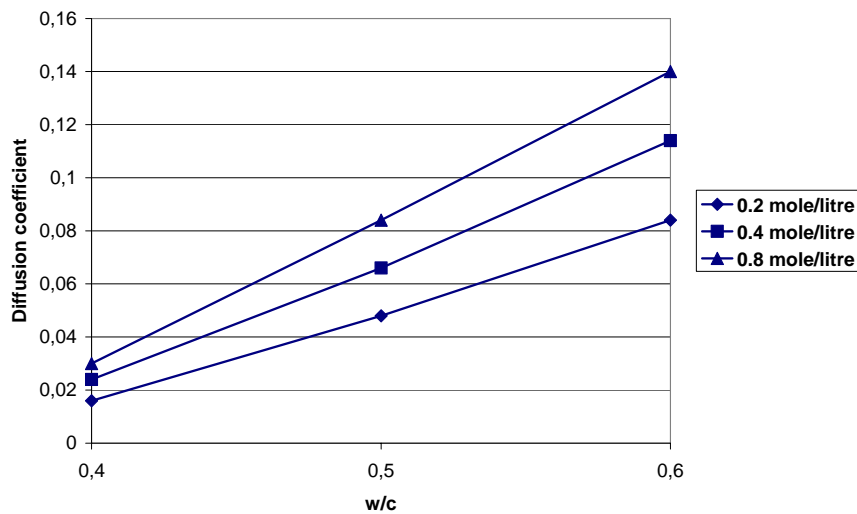


Figure A9: The effective diffusion coefficient as function of the w/c-ratio. Only capillary pore water takes place in chloride transport; equation (A17). The values shall be multiplied by the coefficient K. Degree of hydration 0.75.

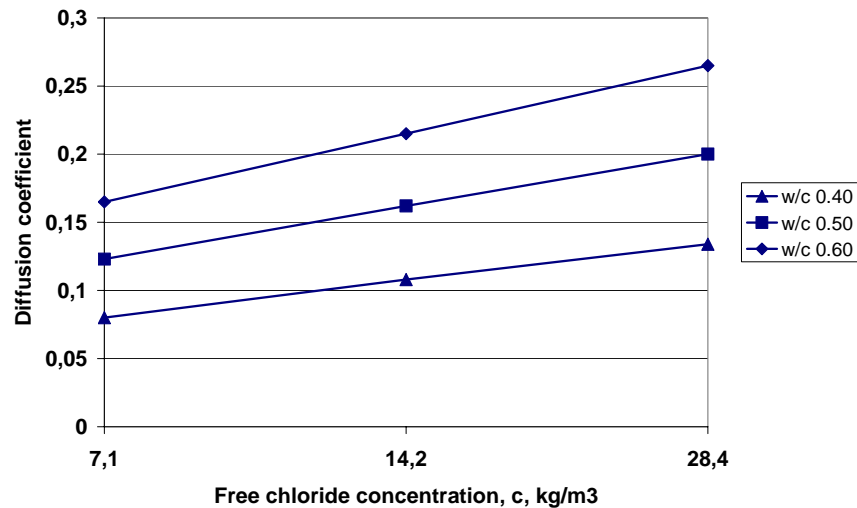


Figure A10: The effective diffusion coefficient as function of the concentration of free chloride. All pore water takes place in chloride transport; equation (A15). The values shall be multiplied by the coefficient K. Degree of hydration 0.75.

The coefficient K should be the same for all w/c-ratios and all degrees of hydration. A value of K can be calculated from known effective diffusion coefficients of concrete. For mature concrete with w/c 0.40 the effective diffusion coefficient in sea water is about  $5 \cdot 10^{-12} \text{ m}^2/\text{s}$ . The chloride concentration is about 0.5 mole/litre. Thus, from Table A3  $\delta_{\text{eff}}$  is about  $0.11 \cdot K$  or  $0.024 \cdot K$ .

This gives the following values of K :

**Alt 1: All pore water takes part in chloride transport:**

$$K = 5 \cdot 10^{-12} / 0.11 = 4.5 \cdot 10^{-11} \text{ m}^2/\text{s}$$

**Alt 2: Only capillary pore water takes part in chloride transport:**

$$K = 5 \cdot 10^{-12} / 0.024 = 2 \cdot 10^{-10} \text{ m}^2/\text{s}$$

The diffusivity of an ion in bulk water is normally of the order  $10^{-9} \text{ m}^2/\text{s}$ . The value of K is only 5% and 20% of that value. This discrepancy can, at least partly, be explained by the “tortuosity effect”, i.e. the fact that the ions do not move in straight paths, but have to move in a meandering path inside the pore system.

Using the values of K above, the effect of degree of hydration and w/c-ratio can be calculated by equations (A15) or (A17). This is shown by some examples.

**Example A3: Effect of the w/c-ratio on the diffusion coefficient**

*Assumptions*

- Degree of hydration 0.75
- Outer chloride concentration  $c=0.4$  mole/litre. Gives  $c_{b,gel}/c=9 \cdot 10^{-3}/14.2=6.3 \cdot 10^{-4}$  (Figure 4, Table A1)
- $K=4.5 \cdot 10^{-11} \text{ m}^2/\text{s}$



Equations (A15) and (A17) are applied:

$$\delta_{\text{eff}} = 4.5 \cdot 10^{-11} \cdot \left\{ \frac{(w/c - 0.14)/(w/c + 0.32)}{[6.3 \cdot 10^{-4} \cdot 1.25 \cdot 0.75 \cdot 10^3]/[w/c - 0.14] + 1} \right\}$$

$$\delta_{\text{eff}} = 2 \cdot 10^{-10} \cdot \left\{ \frac{(w/c - 0.29)/(w/c + 0.32)}{[6.3 \cdot 10^{-4} \cdot 1.25 \cdot 0.75 \cdot 10^3]/[w/c - 0.29] + 1} \right\}$$

The results are shown in the table and figure.

w/c	All pores eq (A15)		Capillary pores eq (A17)	
	$\delta_{\text{eff}} \text{ m}^2/\text{s}$	$\delta_{\text{eff}}$ in relation to w/c 0.40	$\delta_{\text{eff}} \text{ m}^2/\text{s}$	$\delta_{\text{eff}}$ in relation to w/c 0.40
0.4	$4.9 \cdot 10^{-12}$	1	$4.9 \cdot 10^{-12}$	1
0.5	$7.4 \cdot 10^{-12}$	1.5	$13.4 \cdot 10^{-12}$	2.7
0.6	$9.8 \cdot 10^{-12}$	2.0	$23.2 \cdot 10^{-12}$	4.7
0.7	$11.9 \cdot 10^{-12}$	2.4	$33.0 \cdot 10^{-12}$	6.7
0.8	$13.9 \cdot 10^{-12}$	2.8	$42.2 \cdot 10^{-12}$	8.6

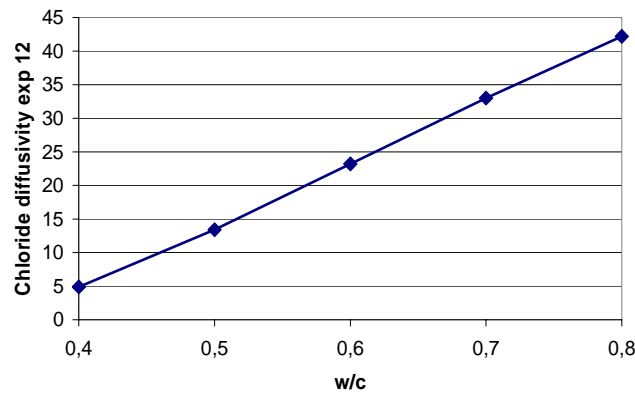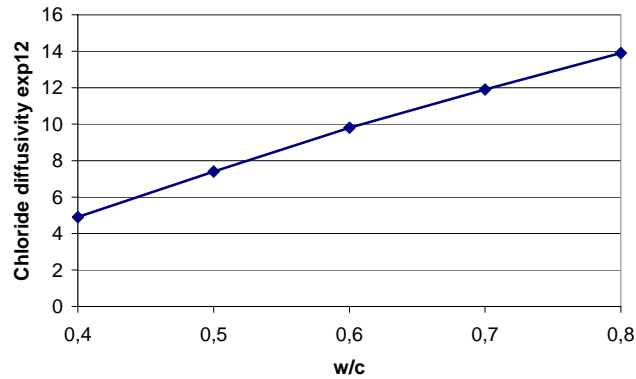

Upper figure: All pores take part in chloride transport  
 Lower figure: Only capillary pores take part in chloride transport

**Example A4: Effect of the degree of hydration on the diffusion coefficient**

*Assumptions*


- w/c-ratio 0.40
- Outer chloride concentration  $c=0.4$  mole/litre. Gives  $c_{b,ge}/c=9 \cdot 10^{-3}/14.2=6.3 \cdot 10^{-4}$  (Figure 4, Table A1)
- $K=4.5 \cdot 10^{-11}$  m<sup>2</sup>/s
- All pores are assumed to take part in chloride transport.

Equation (A15) is applied:

$$\delta_{eff} = 4.5 \cdot 10^{-11} \cdot \left\{ \frac{(w/c - 0.19\alpha)}{(w/c + 0.32)} \right\} / \left\{ \frac{[6.3 \cdot 10^{-4} \cdot 1.25\alpha \cdot 10^3]}{[w/c - 0.19\alpha]} + 1 \right\}$$

The results are shown in the table and figure.

Degree of hydration	$\delta_{eff}$ m <sup>2</sup> /s
0.25	$14 \cdot 10^{-12}$
0.50	$8.2 \cdot 10^{-12}$
0.75	$4.9 \cdot 10^{-12}$
1.00	$2.7 \cdot 10^{-12}$

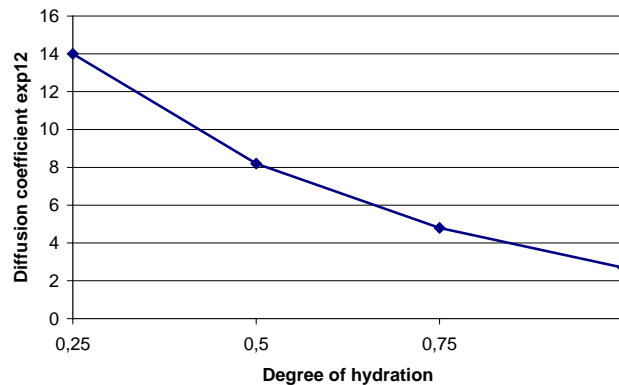

According to experimental data in Frederiksen et al. (1997) -see Figure A11- the diffusion coefficient is increased by a factor 3 at an increase of the w/c-ratio from 0.4 to 0.8 (from  $8 \cdot 10^{-12}$  to  $24 \cdot 10^{-12}$  m<sup>2</sup>/s). This is almost identical with the theoretical results in the example when *all pores* are supposed to be active in chloride transport.

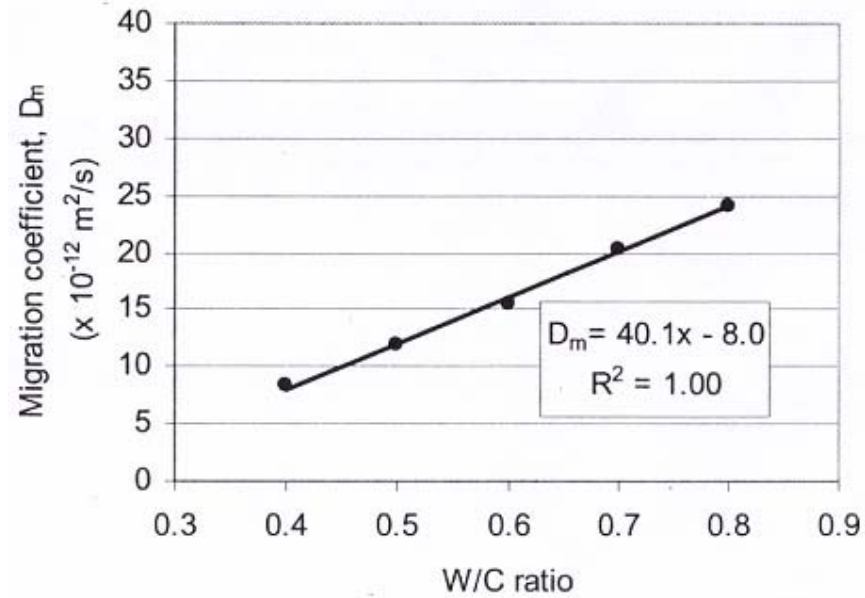


Figure A11: Experimental determination of the relation between the chloride migration coefficient and the water-cement ratio. Frederiksen et al. (1997)

### **A2.3 Imaginable effects of limestone filler**


As described in paragraph 4, limestone filler might affect the steady state diffusion coefficient  $\delta_0$ . Such an effect can be determined by the test described in paragraph 5.2. Any change in  $\delta_0$  caused by limestone filler will be revealed by a change in the coefficient K in equations (A15) and (A17).

As said in paragraph A1.3 limestone filler might also affect the porosity, but as a first approximation this is neglected. Thus, equations (A15) and (A17) can be assumed to be valid also for concrete with limestone filler, provided the effect of filler on the parameters  $\delta_0$  and  $c_{b,gel}$  are considered.


## ANNEX 3

### EVALUATION OF A DIFFUSION CELL TEST

Consider the diffusion cell below.

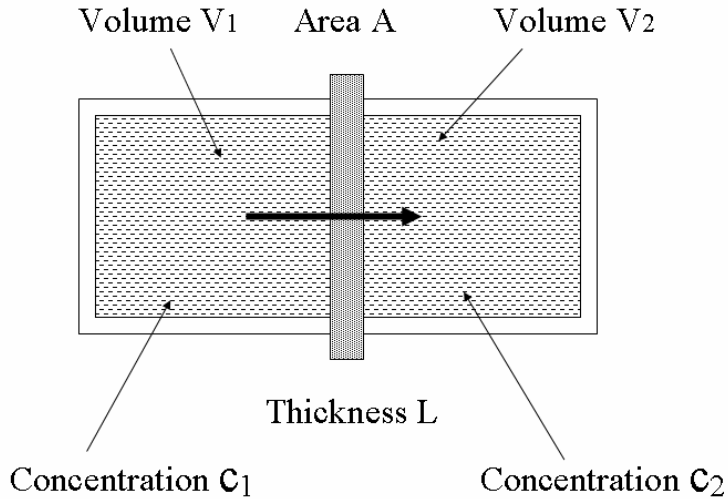

After an “incubation time”, during which chloride is bound in the sample, the rate of decrease in chloride concentration in chamber 1 equals the rate of chloride increase in chamber 2. Then steady state conditions are prevailing. The figure below shows the steady state flow. Flow is counted from time zero which corresponds to the first measurement of chloride concentration in the two chambers. At time 0 the concentration in chamber 1 is  $c_1=c_{1,0}$ . The concentration in chamber 2 is  $c_2=c_{2,0}$ . After the additional time  $\Delta t$  a chloride an additional steady state flow  $\Delta Q$  has taken place. The new chloride concentrations in the two chambers are  $c_1=c_{1,1}$  and  $c_2=c_{2,1}$ .

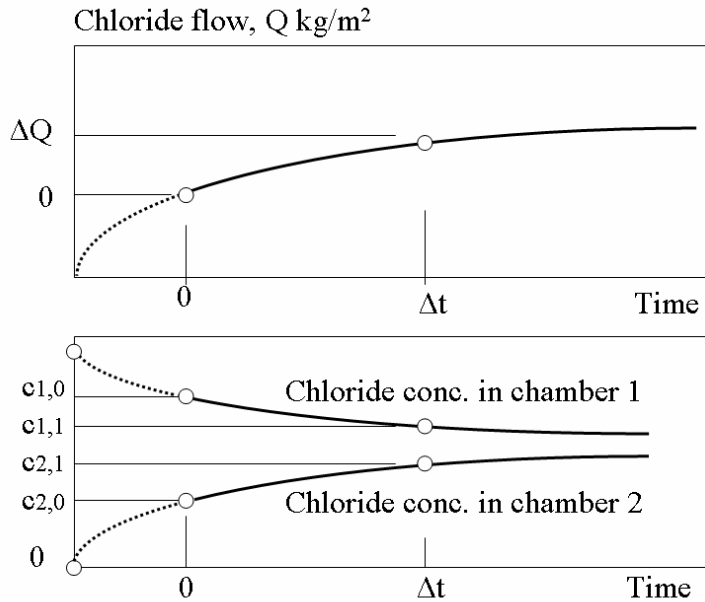

Chloride transport at steady state is:

$$dQ/dt=(\delta_0/L)(c_1-c_2) \quad (A18)$$

The concentrations in the two chambers are:

$$c_1 = c_{1,0} - Q \cdot A/V_1 \quad (A19)$$

$$c_2 = c_{2,0} + Q \cdot A/V_2 \quad (A20)$$

Where  $c_{1,0}$  and  $c_{2,0}$  are the “initial” concentrations in chambers 1 and 2.  $Q$  is the total flow from that point.

Combining the three equations give:

$$dQ/dt = (\delta_0/L)[(c_{1,0} - Q \cdot A/V_1) - (c_{2,0} + Q \cdot A/V_2)] \quad (A21)$$

Separation of the equation gives:

$$\int_0^{\Delta Q} dQ/[c_{1,0} - c_{2,0} - (A/V_1 + A/V_2)Q] = \int_0^{\Delta t} (\delta_0/L)dt \quad (A22)$$

Where  $\Delta Q$  is the chloride flow between the first observations of chloride at time 0 ( $c_{1,0}$  and  $c_{2,0}$ ) and the concentrations at time  $\Delta t$  ( $c_{1,1}$  and  $c_{2,1}$ ).

Integration gives:

$$-V_1 \cdot V_2 / [(V_1 + V_2)A] \cdot \ln[c_{1,0} - c_{2,0} - (A/V_1 + A/V_2)\Delta Q] + V_1 \cdot V_2 / [(V_1 + V_2)A] \cdot \ln[c_{1,0} - c_{2,0}] = (\delta_0/L) \cdot \Delta t \quad (A23)$$

or

$$\delta_0 = (L/\Delta t) \cdot V_1 \cdot V_2 / [(V_1 + V_2)A] \cdot \ln\{(c_{1,0} - c_{2,0}) / [c_{1,0} - c_{2,0} - (A/V_1)\Delta Q - (A/V_2)\Delta Q]\} \quad (A24)$$

According to equations (A19) and (A20) the following relations are valid:

$$(A/V_1)\Delta Q = c_{1,0} - c_{1,1} \quad (A25)$$

$$(A/V_2)\Delta Q = c_{2,1} - c_{2,0} \quad (A26)$$

Inserting these equations in equation (A24) gives:

$$\delta_0 = (L/\Delta t) \cdot V_1 \cdot V_2 / [(V_1 + V_2)A] \cdot \ln\{(c_{1,0} - c_{2,0}) / (c_{1,1} - c_{2,1})\} \quad (A27)$$

Thus, the diffusion coefficient can be determined by measurements of the chloride concentrations in the two chambers at two different occasions.

At steady state conditions the flow out from chamber 1 equals the flow into chamber 2. Therefore, there is a relation between the concentrations in the two chambers. Combining equations (A19) and (A20) gives the following relations:

$$c_{2,1} - c_{2,0} = (c_{1,0} - c_{1,1})(V_1/V_2) \quad (\text{A28})$$

$$c_{1,0} - c_{1,1} = (c_{2,1} - c_{2,0})(V_2/V_1) \quad (\text{A29})$$

These equations can be used for control that steady state has been reached.

Equation (A27) can be simplified when the two chambers are of equal volume, V:

$$\delta_0 = (L/\Delta t) \cdot V / (2A) \cdot \ln \{ (c_{1,0} - c_{2,0}) / (c_{1,1} - c_{2,1}) \} \quad (\text{A30})$$


### Example A5

A cylinder-shaped diffusion cell has the following dimensions, see the figure.

- Diameter of diffusion area: 15 cm
- Diffusion area, A:  $1.77 \cdot 10^{-2} \text{ m}^2$
- Chamber depth: 5 cm
- Chamber volumes, V:  $1.77 \cdot 10^{-2} \cdot 5 \cdot 10^{-3} = 8.9 \cdot 10^{-5} \text{ m}^3$
- The specimen thickness:  $L = 1 \text{ cm} = 10^{-2} \text{ m}$

The initial concentrations are:

- $c_{1,0} = 70 \text{ g/litre}$
- $c_{2,0} = 10 \text{ g/litre}$

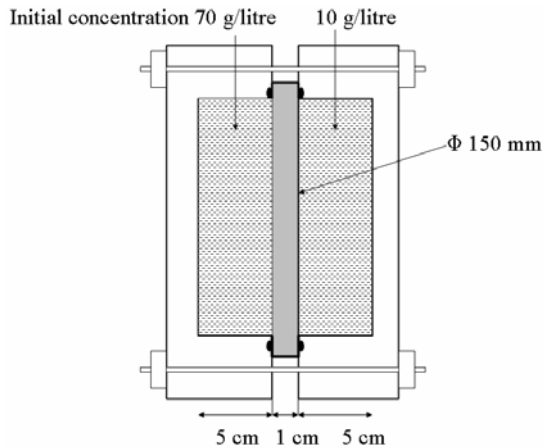

30 days ( $2.59 \cdot 10^6 \text{ s}$ ) after the first measurement the following concentrations are obtained:

- $c_{1,1} = 50 \text{ g/litre}$
- $c_{2,1} = 30 \text{ g/litre}$  (according to equation (A29) steady state has been reached)

The diffusion coefficient becomes:

$$\delta_0 = (10^{-2} / 2.59 \cdot 10^6) \cdot 8.9 \cdot 10^{-5} / (2 \cdot 1.77 \cdot 10^{-2}) \cdot \ln \{ (70 - 10) / (50 - 30) \} = 1.1 \cdot 10^{-11} \text{ m}^2/\text{s}$$

Concentrations  $c_{1,1}$  and  $c_{2,1}$  to be expected after an arbitrary duration  $\Delta t$  can be calculated by the following equation, provided the diffusivity is known:

$$c_{1,0}-c_{2,0}/(c_{1,1}-c_{2,1})=\exp\{\delta_0\cdot 2A\cdot\Delta t/(L\cdot V)\} \quad (\text{A31})$$

According to equations (A28) or (A29):

$$c_{1,1}=c_{1,0} - c_{2,1} + c_{2,0}$$

which gives:

$$c_{1,1}-c_{2,1} = \Delta c = (c_{1,0} - c_{2,1} + c_{2,0}) - c_{2,1}$$

from which:

$$c_{2,1} = (c_{1,0} + c_{2,0} - \Delta c) / 2 \quad (\text{A32})$$

and

$$c_{1,1} = \Delta c + c_{2,1} \quad (\text{A33})$$

#### **Example A6**

***The same as Example A5. The concentration curves are calculated***

*Example:* Calculation for  $\Delta t = 60$  days ( $5.18 \cdot 10^6$  s) is performed.

Equation (A31) gives:

$$(70-10)/(c_{1,1}-c_{2,1}) = \exp\{1.1 \cdot 10^{-11} \cdot 2 \cdot 1.77 \cdot 10^{-2} \cdot 5.18 \cdot 10^6 / (10^{-2} \cdot 8.9 \cdot 10^{-5})\} = 9.64$$


$$c_{1,1}-c_{2,1} = (70-10)/9.64 = 6.2 \text{ g/litre}$$

Equations (A32) and (A33) give:

$$c_{2,1} = (70+10-6.2)/2 = 36.9 \text{ g/litre}$$

$$c_{1,1} = 6.2 + 36.9 = 43.1 \text{ g/litre}$$

The expected chloride concentration curves for the two chambers are shown in the figure below.

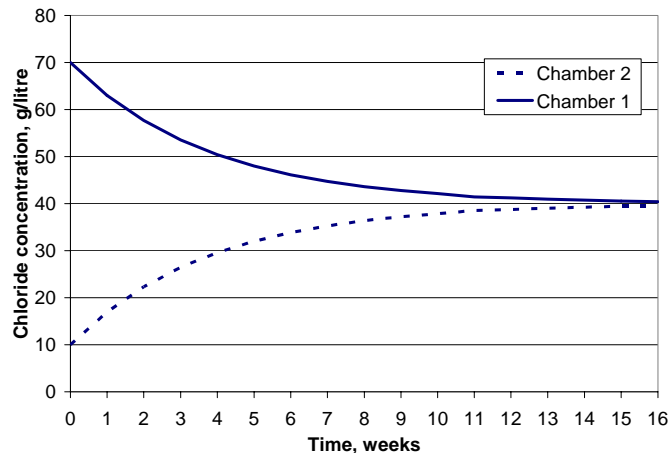

## ANNEX 4

### DETERMINATION OF THE “ACTIVE” POROSITY FOR DISSOLVING CHLORIDE

One possibility to determine the fraction of pore water participating in the dissolution of chloride is to use the hypothesis (strengthened by Figure 4) that a unit weight of the “cement gel” (hydration product) always binds the same amount of chloride at a given free chloride concentration. This quantity is denoted  $c_{b,gel}$  (g/g).

This means that the total amount of bound chloride  $Q_{bound}$  (g) can be determined by (for OPC):

$$Q_{bound} = c_{b,gel} \cdot Q_{gel}' = c_{b,gel} \cdot 1.25 \cdot \alpha \cdot C' \cdot V \quad (A34)$$

Where  $Q_{gel}'$  is the amount of cement gel in the specimen (g). It is given by equation (13).  $\alpha$  is the degree of hydration,  $C'$  is the cement content (g per  $cm^3$ ) and  $V$  the specimen volume ( $cm^3$ ).

The pore water quantity dissolving chloride  $w_w$  ( $cm^3=g$ ) is:

$$w_w = C' \cdot (W/C - \gamma \cdot \alpha) \cdot V \quad (A35)$$

Where  $0.19 < \gamma < 0.39$ .  $\gamma=0.19$  means that all pore water dissolves chloride while  $\gamma=0.39$  means that only capillary water is available as solvent. The equation is valid for OPC.

The free chloride content  $Q_{free}$  (g) becomes:

$$Q_{free} = c''' \cdot w_w = c''' \cdot C' \cdot (W/C - \gamma \cdot \alpha) \cdot V \quad (A36)$$

where  $c'''$  is the chloride concentration in the bath (the same as in the pore water) ( $g/cm^3$ )

The total chloride content is determined experimentally. It becomes:

$$Q_{tot} = Q_{bound} + Q_{free} = c_{b,gel} \cdot 1.25 \cdot \alpha \cdot C' \cdot V + c''' \cdot C' \cdot (W/C - \gamma \cdot \alpha) \cdot V \quad (A37)$$

From this equation the coefficient  $c_{b,gel}$  can be solved

$$c_{b,gel} = [Q_{tot} - c''' \cdot C' \cdot (W/C - \gamma \cdot \alpha) \cdot V] / [1.25 \cdot \alpha \cdot C' \cdot V] \quad (A38)$$

All parameters on the right hand side except  $\gamma$  are known. By testing many specimens with different w/c-ratio in a chloride solution of constant strength,  $c'''=constant$ , a value of  $\gamma$  that gives almost the same value of  $c_{b,gel}$  valid for the actual strength might be found.

For each experiment the relation between  $\gamma$  and  $c_{b,gel}$  is calculated. Theoretically, all these relations will intersect at one single value of  $\gamma$ . This value describes the fraction of pore water that is available for dissolving chloride. The principles are shown in Figure A12.

Note: Equation (13) and consequently equation (A34), and equation (A35) are supposed to be valid for OPC-concrete. Other cements can produce other types and other amount of hydration products and other porosity. Since the reaction products of limestone filler are assumed to be of marginal volume it is assumed that the equations can also be used for concrete with limestone filler. Therefore,  $\alpha$  expresses the degree of hydration of the OPC in the concrete.  $w/c$  in the equations is counted only on the OPC in the concrete.  $C$  is the OPC-content.

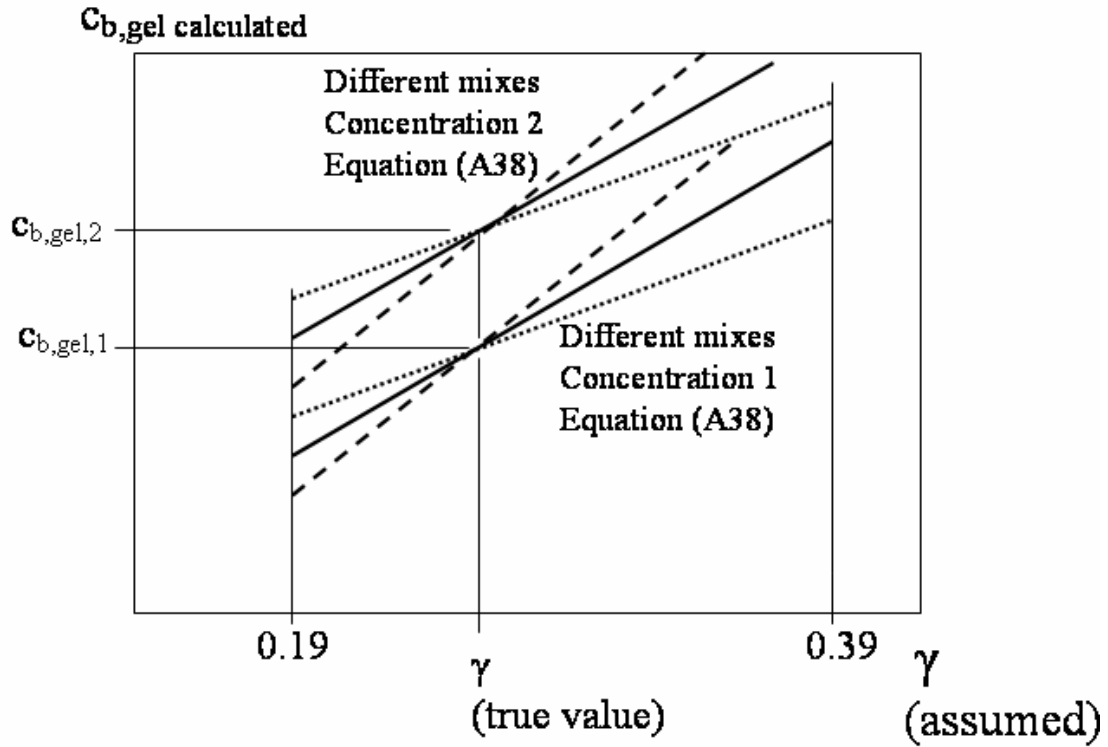


Figure A12: Determination of the coefficient  $\gamma$  in equation (A38).