



LUND UNIVERSITY

Thermoelectrically cooled THz quantum cascade laser operating up to 210 K

Bosco, L.; Franckié, M.; Scalari, G.; Beck, M.; Wacker, A.; Faist, J.

Published in:
Applied Physics Letters

DOI:
[10.1063/1.5110305](https://doi.org/10.1063/1.5110305)

2019

Document Version:
Peer reviewed version (aka post-print)

[Link to publication](#)

Citation for published version (APA):

Bosco, L., Franckié, M., Scalari, G., Beck, M., Wacker, A., & Faist, J. (2019). Thermoelectrically cooled THz quantum cascade laser operating up to 210 K. *Applied Physics Letters*, 115(1), Article 010601. <https://doi.org/10.1063/1.5110305>

Total number of authors:
6

General rights

Unless other specific re-use rights are stated the following general rights apply:

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

Read more about Creative commons licenses: <https://creativecommons.org/licenses/>

Take down policy

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

LUND UNIVERSITY

PO Box 117
221 00 Lund
+46 46-222 00 00

Thermoelectrically cooled THz quantum cascade laser operating up to 210 K

L. Bosco,^{1, a)} M. Franckić,¹ G. Scalari,¹ M. Beck,¹ A. Wacker,² and J. Faist¹

¹⁾ *Institute for Quantum Electronics, ETH Zurich, Auguste-Piccard-Hof 1, 8093 Zurich, Switzerland*

²⁾ *Mathematical Physics and Nanolund, Lund University, Box 118, 221 00 Lund, Sweden*

We present a terahertz quantum cascade laser operating on a thermoelectric cooler up to a record-high temperature of 210.5 K. The active region design is based on only two quantum wells and achieves high temperature operation thanks to a systematic optimization by means of a nonequilibrium Green's function model. Laser spectra were measured with a room temperature detector, making the whole setup cryogenic free. At low temperatures (~ 40 K), a maximum output power of 200 mW was measured.

Terahertz (THz) radiation is subject to a wide range of research and technological efforts¹, from solid state fundamental physics to biomedicine and astrophysics. Specifically, since materials such as textiles, plastics, coatings and biological tissues are transparent to THz radiation, this spectral region is also promising for a variety of non-invasive imaging and non-destructive quality assessment applications such as airport security screening and thickness coating measurements. In order to unlock the full potential of these applications on a large scale, compact and powerful THz sources are needed. A promising candidate is the quantum cascade laser (QCL)^{2,3}, a compact injection laser based on semiconductor heterostructures. THz QCLs have already shown high emitted powers (several hundred mW both in pulsed and continuous wave)^{4–6} and spectral coverage throughout the 1-6 THz range⁷ with single mode and broadband devices⁸. However, despite several efforts, to-date THz QCL operation is still restricted to cryogenic cooling and their maximum operating temperature is still below 200 K⁹. In this Letter we present a THz QCL operating up to 210 K, allowing the use of a small footprint, 4-stage Peltier cooler. In combination with a commercial DTGS detector, this constitutes a platform for THz spectroscopy completely free from any cryogenic and Helium-based (He-based) technology. For any given wavelength, resonator losses, and broadening lifetime, the ultimate temperature limit to QCL laser operation increases with the fraction of the electron population in the upper state¹⁰, as parasitic reabsorption by the free electrons participating to the transport and maintaining the electrical stability are the key source of optical losses¹¹. This line of reasoning provides an explanation for the general trend of THz QCL designs that has been towards reducing the number of states per period. This qualitative result is supported by the quantitative gain computations shown in Fig. 1(a), where the computed active region population and gain at 200 K of a selection of THz QCLs using different design schemes show a relative increase in the upper laser state (ULS) population (n_{ULS}) as the number of active states is reduced. This leads to both an increase in population inversion

and a reduction of intersubband re-absorption and justifies using this quantity as a performance indicator¹⁰. Early THz QCLs used the "bound-to-continuum" (BtC) scheme^{3,12–14}, where the upper laser state (ULS) is localized in one quantum well and population inversion is achieved by a combination of intersubband scattering and tunneling transitions. The main limitation resides in the re-absorption of photons by thermally populated states in the lower miniband, as evident by the negative gain in Fig. 1 (b). To avoid this problem, the "resonant phonon" 3-well scheme achieves efficient LLS extraction using only four states^{18,19}, by exploiting a single tunneling transition followed by resonant phonon emission. The scattering assisted (SA) injection design¹⁵, also with 4 active states per period, achieves similar performance. The minimum number of active states is three, limited by the electrical stability of the laser^{11,16}, and has been realized in two-quantum well designs^{17,20,21} with close-to-record temperature performance achieved recently^{22,23}. In fact, one might see the two quantum well active region as the structure closest to the original proposal from Kazarinov and Suris²⁴ which satisfies the electrical stability condition. The analysis in Fig. 1 compares the best devices obtained from different designs regardless to the emitted frequency and indicates that using the minimum number of states per period should lead the choice of design scheme for improving THz QCL temperature performance.

Nonequilibrium Green's function (NEGF) modeling has proven to be a powerful tool for optimizing THz QCL designs²². Owing to the significant computation times that come with such a complex model, we have performed a systematic optimization using the NEGF model of Ref. 26 in conjunction with an information algorithm with parallel trials for multi-variable, global extremum search²⁷ in order to increase the convergence rate. We optimized the maximum gain at a lattice temperature of 300 K, varying all four layers of the two-well design in a region around the best one from Ref. 22. In order to keep a manageable computing time, we limited the optimization to a photon energy of $\hbar\omega = 16$ meV and a bias of 52.5 mV/period (encompassing one LO phonon and one photon emission per period). We find that the gain is maximized for a shorter period length and thicker barriers compared to the nominal structure previously implemented. In particular, a reduction of $\sim 3\%$ in the

^{a)} Electronic mail: lbosco@phys.ethz.ch

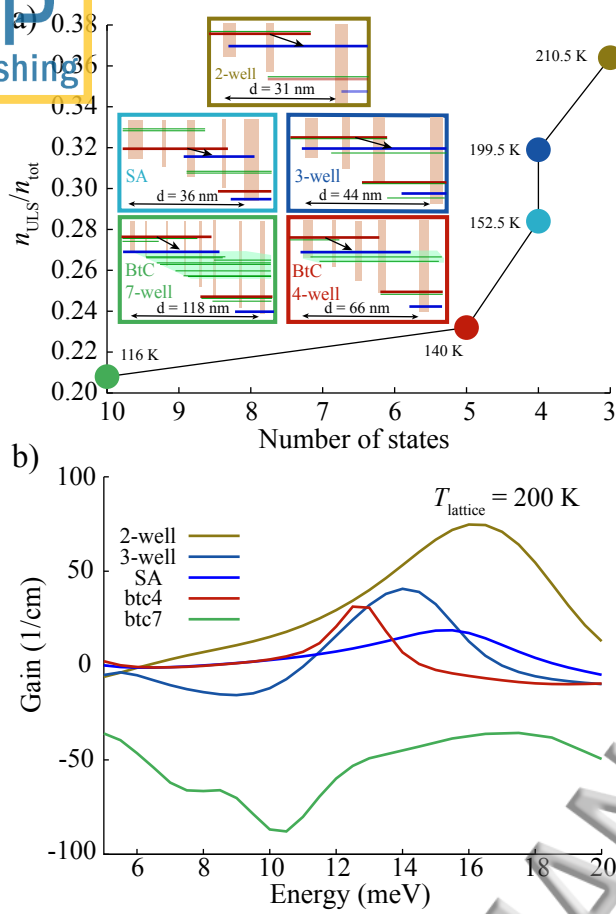


FIG. 1. (a) Relative density of the upper laser state (n_{uls}) calculated with a nonequilibrium Green's function (NEGF) model for five THz quantum cascade laser designs with different number of active states per period. Schematics of the simulated QCLs are shown in the five insets and represent 2-well, 3-well⁹, scattering-assisted (SA) injection²⁵, 4-well¹⁴ and 7-well¹³ bound-to-continuum (BtC) designs. The 2-well QCL is the layer presented in this work. For each design we show the upper laser state (ULS) in red, the lower laser state (LLS) in blue, and green lines indicate the other relevant states. The vertical bars show the barriers separating the quantum wells. (b) Comparison of simulated gain for the five designs. The fewer the states, the more concentrated the carriers are to the ULS, making gain exceed re-absorption.

period length is predicted to increase the gain from ~ 18 to ~ 25 cm⁻¹. The best design as predicted by the NEGF optimization has been grown by molecular beam epitaxy (MBE). As compared to our previous work²², a thicker (12 μ m) active region was grown in order to reduce the waveguide losses at the cost of slightly increased mirror losses for a given cavity length²⁸. The grown QCLs were processed as Cu-Cu waveguides using a thermocompressive bonding after the evaporation of 5 nm of Ta and 500 nm of Cu on the active region. As a top metal cladding, a layer of Ta/Cu/Ti/Au (5/50/20/200 nm) has been deposited and the sample has been dry etched in a Cl₂/Ar plasma using SiN_x as hard mask. Since the epitaxial

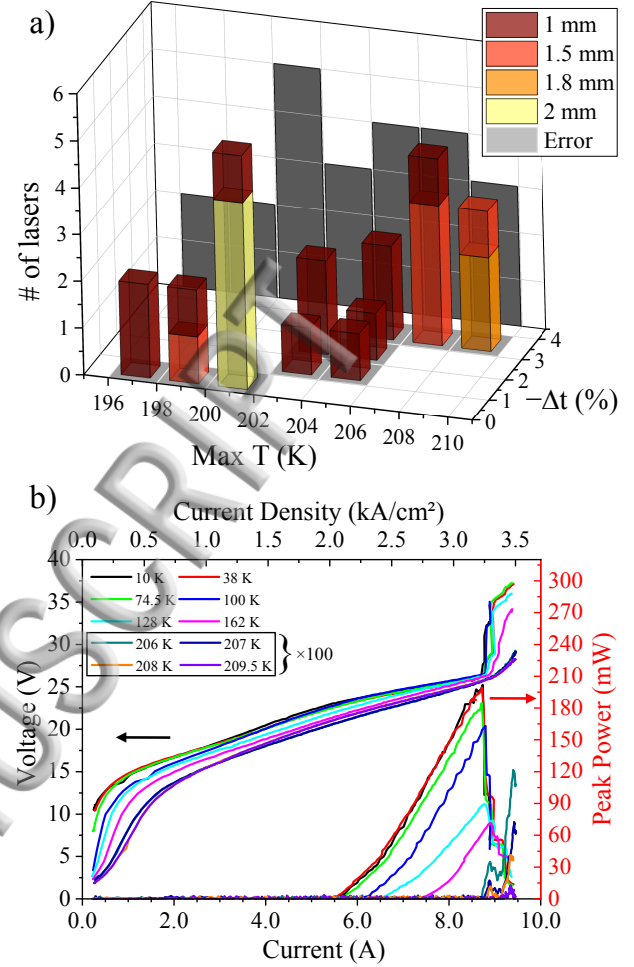


FIG. 2. a) 3D histogram of the statistics conducted over 23 lasers with a width of 150 μ m and a length between 1 and 2 mm, as specified by the color scale, versus the layer Δt . The projection in dark grey on the XY plane sums over all the thickness variation. b) LIV characteristic of the best device is shown, pumped electrically with 50 ns width pulses at 415 Hz, up to ~ 210 K.

layers grown on the 3" wafer exhibits a thickness gradient of approximately $\Delta t = -4\%$ from the center to the edge (calibrated through X-ray mapping), a period thickness span of $\sim 0 - 4\%$ compared to the nominal design is experimentally realized. The active region thickness was measured by high-resolution x-ray diffraction performing a 5 mm mesh mapping over the 3" wafer. A systematic characterization of the processed lasers in a He-cooled flow cryostat has confirmed the strong dependence of the laser performance on the active region thickness predicted by the simulations. The 3D histogram in Fig.2(a) reports the maximum temperature of all the 23 tested lasers with a width of 150 μ m and lengths between 1 and 2 mm with varying period thickness, exploring ranges of $\pm 0.5\%$. As confirmed by the simulations, the maximum operating temperature (T_{max}) improves when moving towards the edge of the wafer. The best device, found for $\Delta t \approx -3.5\%$, was 1.8 mm long

and biased up to a maximum temperature of ~ 210 K, as shown in Fig. 2(b). The structure sequence for this device is $3.2/6/79.9/19.0/84.0/29.0/51.6$, here expressed in Å, with barriers in bold face and the underlined well section doped to $n = 4.5 \times 10^{10} \text{ cm}^{-2}$. The band structure and energetically resolved carrier density of this device simulated with the NEGF model are shown in Fig. 3(a). The main difference with regards to the nominal design²² is a higher extraction energy $E_{\text{ex}} \approx 41$ meV and a slightly lower oscillator strength (although the latter is highly bias-dependent and therefore difficult to precisely define). This reduces non-radiative phonon emission from the upper laser state as well as thermal backfilling, improving the temperature resilience.

The laser was electrically driven with 50 ns wide pulses at a repetition frequency of 415 Hz. A pre-calibrated He-cooled Si bolometer has been used as a detector showing a peak power of ~ 200 mW and a threshold current density of 2 kA/cm^2 when the laser is operated at 10 K. The relatively high current density required for laser operation is a result of the optimization of the presented QCL being restricted to high-temperature operation and high output power. In order to limit the current density, the parasitic leakage into level 5 (discussed in some detail in Ref. 22) could be reduced. However, for the purpose of pulsed high-temperature operation, we find that this current channel has a small impact since less than 10% of the carriers reside in levels 4 and 5 even at 200 K.

As shown in Fig. 3(b-d), the device whose performances are reported in Fig. 2(b) is then tested on a four-stage cooler (model SP2394 from II-VI Marlow Industries), that reached a temperature as low as 195 K with a power consumption below 30 W. The temperature was measured using a NTC Thermistor (44000RC series from TE connectivity). As shown in Fig. 3(b), the light collected using an elliptical mirror is measured at different temperatures from 195 K up to 210.5 K as a function of current using a He-cooled Ge bolometer. The results confirm the performance recorded in the flow cryostat, with the difference of 1 K, corresponding to the accuracy of the silicon temperature sensor in the flow cryostat. The threshold current density exhibits an exponential temperature dependence with a characteristic temperature of $T_0 = 229$ K. Close to J_{max} the derivative of gain with respect to current density decreases and eventually crosses zero. Thus, in order to reach the threshold gain at temperatures approaching T_{max} a rapid increase in J_{th} with temperature is observed. The high value of T_0 demonstrates the potential of this active region design for high temperature operation, as a further reduction of 10% of the losses would increase the maximum operating temperature by potentially 20 K.

As we previously observed in Ref. 22, the simulated current agrees very well with the experimental one, and the bias is in reasonable agreement. The inset in Fig. 3(b) shows that also the agreement between the simulated peak gain frequency and the observed emission frequency of the laser are in excellent agreement. This confirms that the NEGF is a powerful tool for optimization of THz

QCLs, and the operation of the laser has been well understood. The discrepancy between the optimized (nominal) structure and the best (3.5% thinner) structure (which is also better in the NEGF model under a detailed analysis) can be explained by the restrictions imposed to the optimization, since the best structure operates at a higher bias (56 mV/period) and photon energy (16.5 meV). In accordance with previous results²², including a rudimentary form of electron-electron scattering²⁹ in the model (not shown) the current density changes negligibly while the gain is almost halved and red shifted by 1 meV at 200 K. We also find that the temperature degradation of the presented design is dominated by level broadening.²²

Laser spectra with the device operating on a Peltier cooler were performed using a commercial FTIR (Bruker Vertex 80V) equipped with a DTGS room temperature detector, making such setup fully cryogenic free. Spectra measured at different temperatures with a resolution of 0.2 cm^{-1} are reported in Fig. 3(a).

In conclusion, we have demonstrated the first operation of a THz QCL using thermo-electric cooling, and the first operation of a THz QCL above 200 K, with a peak power as high as 1.2 mW at 206 K, which allowed detection in a cryogenic-free system. The methodology employed in this work will likely lead to further improvements of this technology; pursuing better QCL designs, studying in depth the effect of other parameters, *e.g.* barrier height, doping position, and doping region width, as well as improving the Cu-Cu process is expected to lead to increased maximum operating temperatures and extracted optical power. The presented results pave the way towards a new generation of on-chip, portable THz devices based on high power THz coherent sources.

The authors would like to thank Dr. Keita Ohtani and Dr. Christopher Bonzon for their help in the initial stages of this project. This work is supported by the Horizon 2020 ERC grant project CHIC 724344, the Swedish Research Council (grant 2017-04287), as well as a grant from SFB 956 of the Deutsche Forschungsgemeinschaft.

¹S. S. Dhillon, M. S. Vitiello, E. H. Linfield, A. G. Davies, M. C. Hoffmann, J. Booske, C. Paoloni, M. Gensch, P. Weightman, G. P. Williams, E. Castro-Camus, D. R. S. Cumming, F. Simoens, I. Escorcia-Carranza, J. Grant, S. Lucyszyn, M. Kuwata-Gonokami, K. Konishi, M. Koch, C. A. Schmuttenmaer, T. L. Cocker, R. Huber, A. G. Markelz, Z. D. Taylor, V. P. Wallace, J. Axel Zeitler, J. Sibik, T. M. Korter, B. Ellison, S. Rea, P. Goldsmith, Ken B. Cooper, R. Appleby, D. Pardo, P. G. Huggard, V. Krozer, H. Shams, M. Fice, C. Renaud, A. Seeds, A. Stöhr, M. Naftaly, N. Ridler, R. Clarke, J. E. Cunningham, and M. B. Johnston. The 2017 terahertz science and technology roadmap. *Journal of Physics D: Applied Physics*, 50(4), 2017.

²J. Faist, F. Capasso, D.L. Sivco, C. Sirtori, A.L. Hutchinson, and A.Y. Cho. Quantum Cascade Laser. *Science*, 264(5158):553–556, 1994.

³R. Köhler, A. Tredicucci, F. Beltram, H. E. Beere, E. H. Linfield, A. Giles Davies, D. A. Ritchie, R. C. Iotti, and F. Rossi. Terahertz semiconductor-heterostructure laser. *Nature*, 417(6885):156–159, 2002.

⁴B. S. Williams. Terahertz quantum-cascade lasers. *Nature Photonics*, 1(517):517–525, 2007.

⁵L. Lianhe, L. Chen, J. Zhu, J. Freeman, P. Dean, A. Valavanis, A.G. Davies, and E.H. Linfield. Terahertz quantum cascade

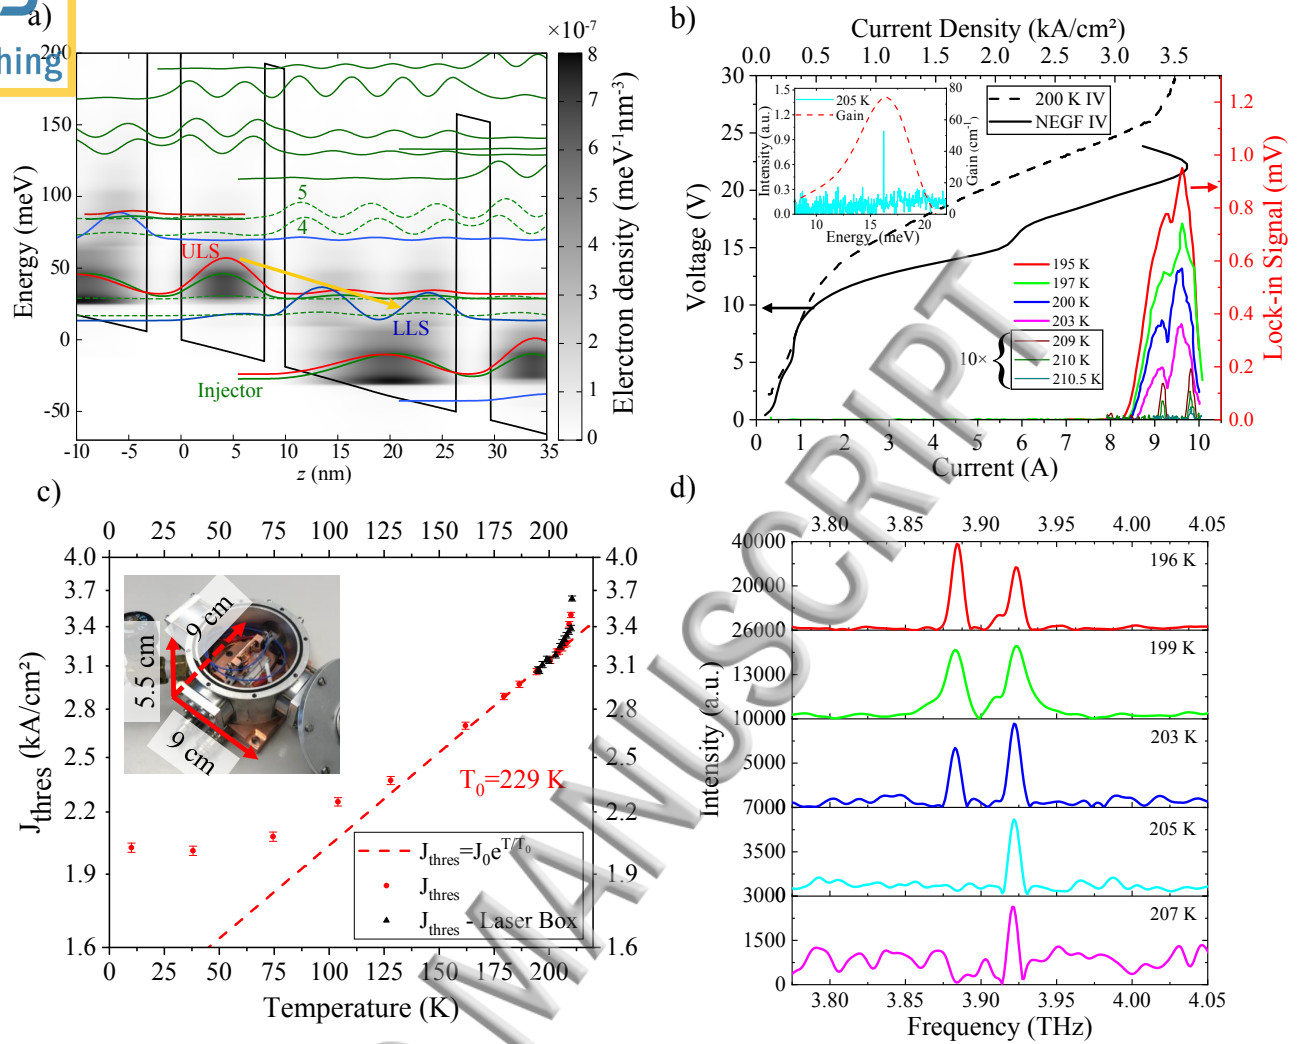


FIG. 3. a) Band structure of the GaAs/Al_{0.25}Ga_{0.75}As QCL with highest operating temperature with layer sequence (in Å with barriers in bold face) **32.6/79.9/19.0/84.0/29.0/51.6** where the underlined well section is doped to $n = 4.5 \times 10^{10} \text{ cm}^{-3}$, shown at a bias of 56 mV/period where the current density is maximal. The yellow arrow indicates the diagonal ($f_{\text{osc}} = 0.20$) laser transition from the upper (red) to the lower (blue) laser state. The green dashed lines indicate states in close resonance to the lower and upper laser states, respectively. The grey scale shows the electron density evaluated in the NEGF model at a lattice temperature of 200 K. b) LI curves obtained cooling down the laser in the laser box and detecting it using a He-cooled Ge bolometer. In dashed and solid black lines, a comparison between the measured IV and the simulated IV at a lattice temperature of 200 K is shown. The IV has been measured in a flow cryostat setup. In the inset, it is possible to see that the emitted frequency at 205 K fits the simulation prediction of the gain. c) T_0 fit of the threshold current density J_{thres} reported on a log scale. Fit is executed on data points collected in cryostat operation (red circles), but agrees well with the data collected during the thermoelectric cooling operation. A $T_0 = 229$ K is obtained. In inset, the laser box with Peltier cell and mounted QCL. The box footprint ($\sim 9 \times 9 \times 5.5 \text{ cm}^3$) is significantly reduced compared to a flow cryostat (even without taking into account the He dewar). At maximum capacity, the Peltier cell uses $\lesssim 30$ W to cool the laser down to 195 K. d) Spectra taken with the laser cooled down using a thermoelectric multistage cooler and using the DTGS room temperature detector of a Bruker Vertex 80 FTIR. Laser has been operated at maximum power.

lasers with >1 W output powers. *Electronics Letters*, 50(4):309–311, 2014.

⁶M. Brandstetter, C. Deutsch, M. Krall, H. Detz, D. C. Macfarland, T. Zederbauer, A. M. Andrews, W. Schrenk, G. Strasser, and K. Unterrainer. High power terahertz quantum cascade lasers with symmetric wafer bonded active regions. *Applied Physics Letters*, 103(17), 2013.

⁷C. Sirtori, S. Barbieri, and R. Colombelli. Wave engineering with THz quantum cascade lasers. *Nature Photonics*, 7(9):691–701,

2013.

⁸M. Rösch, G. Scalari, M. Beck, and J. Faist. Octave-spanning semiconductor laser. *Nature Photonics*, 9(1):42–47, 2014.

⁹S. Fathololoumi, E. Dupont, C.W.I. Chan, Z.R. Wasilewski, S.R. Laframboise, D. Ban, A. Mátyás, C. Jirauschek, Q. Hu, and H. C. Liu. Terahertz quantum cascade lasers operating up to ~ 200 K with optimized oscillator strength and improved injection tunneling. *Optics Express*, 20(4):3866, 2012.

¹⁰J. Faist. Wallplug efficiency of quantum cascade lasers: Criti-

- cal parameters and fundamental limits. *Applied Physics Letters*, 90(25):23–25, 2007.
- ¹¹J. Faist and G. Scalari. Unified description of resonant tunnelling diodes and terahertz quantum cascade lasers. *Electronics Letters*, 46:S46, 2010.
- ¹²G. Scalari, L. Ajili, J. Faist, H. Beere, E. Linfield, D. Ritchie, and G. Davies. Far-infrared ($\approx 87\ \mu\text{m}$) bound-to-continuum quantum-cascade lasers operating up to 90 K. *Applied Physics Letters*, 82(19):1–3, 2003.
- ¹³G. Scalari, N. Hoyler, M. Giovannini, and J. Faist. Terahertz bound-to-continuum quantum-cascade lasers based on optical-phonon scattering extraction. *Applied Physics Letters*, 86(18):1–3, 2005.
- ¹⁴M. I. Amanti, G. Scalari, R. Terazzi, M. Fischer, M. Beck, J. Faist, A. Rudra, P. Gallo, and E. Kapon. Bound-to-continuum terahertz quantum cascade laser with a single-quantum-well phonon extraction/injection stage. *New Journal of Physics*, 11, 2009.
- ¹⁵E. Dupont, S. Fatholouloumi, Z. R. Wasilewski, G. Aers, S. R. Laframboise, M. Lindskog, S. G. Razavipour, A. Wacker, D. Ban, and H. C. Liu. A phonon scattering assisted injection and extraction based terahertz quantum cascade laser. *Journal of Applied Physics*, 111(7), 2012.
- ¹⁶A. Wacker. Extraction-controlled quantum cascade lasers. *Applied Physics Letters*, 97(8):8–10, 2010.
- ¹⁷G. Scalari, M. I. Amanti, C. Walther, R. Terazzi, M. Beck, and J. Faist. Broadband THz lasing from a photon-phonon quantum cascade structure. *Optics express*, 18(8):8043–8052, 2010.
- ¹⁸H. Luo, S. R. Laframboise, Z. R. Wasilewski, G. C. Aers, H. C. Liu, J. C. Cao. Terahertz quantum-cascade lasers based on a three-well active module. *Applied Physics Letters*, 90(4):1–3, 2007.
- ¹⁹S. Kumar, Q. Hu, and J. L. Reno. 186 K operation of terahertz quantum-cascade lasers based on a diagonal design. *Applied Physics Letters*, 94(13):2–4, 2009.
- ²⁰G. Scalari, M. Amanti, R. Terazzi, M. Beck, and J. Faist. Two-well quantum cascade laser emitting from 2.7 to 4.1 THz. *Proceedings of the Tenth International Conference on Intersubband Transitions in Quantum Wells*, Montreal, Canada, September 2009, <http://www.itqw2009.com/index.php>
- ²¹S. Kumar, C. W. I. Chan, Q. Hu, and J. L. Reno. Two-well terahertz quantum-cascade laser with direct intrawell-phonon depopulation. *Applied Physics Letters*, 95(14):1–3, 2009.
- ²²M. Franckić, L. Bosco, M. Beck, C. Bonzon, E. Mavrona, G. Scalari, A. Wacker, and J. Faist. Two-well quantum cascade laser optimization by non-equilibrium Green's function modelling. *Applied Physics Letters*, 112(2), 2018.
- ²³A. Albo, Yuri V. Flores, Qing Hu, and John L. Reno. Two-well terahertz quantum cascade lasers with suppressed carrier leakage. *Applied Physics Letters*, 111(11):1–6, 2017.
- ²⁴R.F. Kazarinov and R.A. Suris. Possibility of the amplification of electromagnetic waves in a semiconductor with a superlattice. *Sov. Phys. Semicond.*, 5(4):707709, 1971.
- ²⁵S. G. Razavipour, E. Dupont, S. Fatholouloumi, C. W.I. Chan, M. Lindskog, Z. R. Wasilewski, G. Aers, S. R. Laframboise, A. Wacker, Q. Hu, D. Ban, and H. C. Liu. An indirectly pumped terahertz quantum cascade laser with low injection coupling strength operating above 150 K. *Journal of Applied Physics*, 113(20), 2013.
- ²⁶A. Wacker, M. Lindskog, and D. O. Winge. Nonequilibrium Green's function model for simulation of quantum cascade laser devices under operating conditions. *IEEE Journal on Selected Topics in Quantum Electronics*, 19(5):1–11, 2013.
- ²⁷Y. Sergeev and R. Strongin. A global minimization algorithm with parallel iterations. *USSR Computational Mathematics and Mathematical Physics*, 29(2):7–15, 1989.
- ²⁸S. Kohen, B. S. Williams, and Q. Hu. Electromagnetic modeling of terahertz quantum cascade laser waveguides and resonators. *Journal of Applied Physics*, 97(5), 2005.
- ²⁹D. O. Winge, M. Franckić, C. Verdozzi, A. Wacker, and M. F. Pereira. Simple electron-electron scattering in non-equilibrium Green's function simulations. *Journal of Physics: Conference Series*, 696(1), 2016.

